



Carbon nanotubes: revolutionizing construction materials for a sustainable future: A review

Khristina Maksudovna Vafaeva^{1,a}, Rachid Zegait^{*2,b}

¹Peter the Great St. Petersburg Polytechnic University, St. Petersburg, Russia

²Faculty of Science and Technology, Ziane Achour University of Djelfa, Djelfa, Algeria

Article Info

Abstract

Article history:

Received 18 Aug 2023

Accepted 13 Nov 2023

Keywords:

Carbon nanotubes;
Material enhancers;
Construction;
Ongoing research;
Building materials;
Mechanical properties

This review article explores the use of carbon nanotubes (CNTs) as material enhancers in construction and their advantages. It emphasizes ongoing research to gather accurate data on CNT-enhanced material properties and their role in creating more efficient and stronger building materials. The various methods of obtaining and incorporating CNTs into building materials, including chemical vapor deposition and electric arc synthesis, are discussed. A comparative analysis of building materials with and without CNTs is presented to examine their characteristics. The article also discusses future prospects for CNTs in various industries. The study aims to investigate experimental methods for obtaining CNTs, their properties, and their introduction into building materials. The research methodology involves studying literature sources, analyzing experimental results, and examining the structural, mechanical, and electronic properties of CNTs. Analytical methods based on scientific articles and publications related to CNTs in construction were used to ensure the article's reliability, validity, completeness, and objectivity. The research highlights CNTs' potential as material enhancers in construction, owing to their unique mechanical properties, such as high strength, stiffness, and corrosion resistance. Specific studies demonstrating the use of CNTs to increase the strength of concrete and other construction materials are provided, indicating the promising application of CNTs in future construction projects. However, technical challenges must be addressed, and appropriate standards and regulations should be developed before practical implementation.

© 2023 MIM Research Group. All rights reserved.

1. Introduction

The global construction industry is undergoing a paradigm shift as sustainability takes center stage in the pursuit of a greener and more environmentally conscious future [1]. Traditional construction materials like concrete and steel have long been essential for infrastructure development but contribute to environmental issues due to their carbon emissions and resource depletion [2,3]. To address sustainability concerns, carbon nanotubes (CNTs) have emerged as a groundbreaking alternative [4]. CNTs are microscopic cylindrical structures composed of carbon atoms, offering extraordinary mechanical, electrical, and thermal properties [5]. They are exceptionally strong yet lightweight, allowing for efficient load distribution and enhanced durability [6]. Integrating CNTs in construction materials provides several advantages. Their use significantly reduces the carbon footprint, as they enhance structural integrity and require less material, lowering energy consumption and greenhouse gas emissions during production and transportation [7,8]. CNTs also enable the development of self-sensing and self-healing materials, allowing real-time monitoring of structural health and microcrack repair, extending material lifespan, and reducing maintenance needs [9]. Furthermore, CNTs offer opportunities for energy-efficient infrastructure through enhanced

*Corresponding author: zegait.rachid@gmail.com, r.zegait@univ-djelfa.dz,

^a orcid.org/0000-0002-7422-5494; ^b orcid.org/0000-0001-7976-0595

DOI: <http://dx.doi.org/10.17515/resm2023.42ma0818rv>

Res. Eng. Struct. Mat. Vol. x Iss. x (xxxx) xx-xx

electrical conductivity for energy storage systems and smart grid technologies, and thermal conductivity for insulation materials, optimizing energy consumption in buildings [10,11].

While CNTs show immense promise, challenges like large-scale production, cost-effectiveness, and environmental risks must be addressed [12]. Continued research and collaboration between academia, industry, and policymakers are essential to unlock their full potential and pave the way for a sustainable future.

The unique properties of CNTs extend beyond construction, finding applications in various industries to improve material strength, deformability, and durability [13,14]. Their integration into construction materials creates new composites with enhanced characteristics, such as increased strength and reduced shrinkage in concrete. Functional coatings with properties like waterproofing, fire resistance, and corrosion protection can improve the quality and lifespan of construction materials [15,16]. The literature highlights the extensive research into CNTs in construction, showcasing their potential to revolutionize the field and create materials and structures with improved properties and efficiency. Nanotechnology, including CNTs, has opened exciting possibilities for the construction industry, enabling the development of innovative materials and structures [17,18]. Numerous review articles delve deeply into specific directions. For instance, Norizan et al. [19] provides a comprehensive review of existing research and introduces novel findings on the functionalization of carbon nanotubes to enhance their sensitivity and selectivity in detecting various chemical compounds. This advancement holds potential applications in diverse fields, including medicine, environment, and industry. The article highlights the significant role of carbon nanotubes as chemical sensors, emphasizing that functionalization can significantly enhance their performance and detection efficiency.

Garg et al. [20] explores the utilization of carbon nanotubes as strengthening agents in composite materials. The authors examine various methods for obtaining and evaluating carbon nanotubes, as well as their application in composite materials to enhance mechanical properties. The article discusses the potential advantages and limitations of integrating carbon nanotubes into composite materials.

Similarly, Anzar et al. [21] offers an overview of the diverse applications of carbon nanotubes in biomedicine. This encompasses their use as nanovectors for drug delivery, materials for tissue engineering, biomarkers, and various other applications. Fiyadh et al. [22] review different adsorption methods, investigate the mechanisms of interaction between carbon nanotubes and heavy metals, and provide an overview of parameters influencing adsorption efficiency, such as nanotube size, shape, pH of the medium and metal concentration. They further explore the application of carbon nanotubes in removing heavy metals from water solutions, soil, and wastewater.

Sajid et al. [23] present an overview of various applications of carbon nanotube-based adsorbents in water purification, including the removal of organic and inorganic pollutants, heavy metals, pharmaceuticals, and other harmful substances. The article discusses the interaction mechanisms between carbon nanotubes and water pollutants, encompassing adsorption and ion exchange processes.

The impact of carbon nanotubes on concrete properties is also examined in [24]. The review summarizes existing research on the use of carbon nanotubes in concrete and their influence on its mechanical and physicochemical properties. Various methods of incorporating carbon nanotubes into the concrete matrix, such as mixing, spraying, and modified nanotube application, are discussed, along with the effects on strength, elasticity, fracture resistance, and other mechanical properties of concrete.

Franklin et al. [25] primarily focuses on the assembly and modification techniques of carbon nanotube transistors, as well as the underlying principles of their electronic performance. The

authors also address issues related to enhancing the efficiency and stability of carbon nanotube transistors. Additionally, the article presents examples of their applications in diverse fields, including electronics.

Alsubaie et al. [26] explores the vibration response of functionally graded carbon nanotube-reinforced composite (CNTRC) beams using a higher-order shear deformation beam theory. The beams are reinforced with single-walled carbon nanotubes in a polymer matrix and supported by a viscoelastic foundation. Various reinforcement distribution patterns and porosity distributions are considered. The study incorporates damping coefficient, Winkler's, and Pasternak's parameters to analyze viscosity effects on the foundation. Results indicate that adding a damping coefficient enhances vibration performance, especially with increased spring constant factors. The fundamental frequency rises with higher porosity coefficients, suggesting a significant impact of porosity on beam vibrational characteristics [26].

Madenci et al. [27] investigates the application of carbon nanotubes (CNTs) in strengthening polymer matrix composites through experimental tensile testing and fabrication of carbon nanotube reinforced composite (CNTRC) beams. The study explores various micromechanical models to optimize the mechanical properties of CNTRC materials. The research concludes that the optimal CNT amount for reinforcing composite beams is 0.3%, as higher concentrations lead to reduced tensile capacity. A comparison between experimental results and Finite Element Models using ABAQUS demonstrates good conformance. The study also evaluates Young's Moduli using the prediction models Halpin-Tsai and Mixture-Rule, revealing accurate predictions by Halpin-Tsai and significantly lower accuracy with Mixture-Rule [27].

Zhang et al. [28] investigates the wave propagation behavior of carbon nanotube reinforced composite (CNTRC) beams on an elastic foundation, employing various higher order shear deformation beam theories such as Euler and Timoshenko theories. Wave equations for CNTRC beams are derived using the Euler-Lagrange principle, and the relationship between wave number and circular frequency is established through the eigenvalue method. Phase and group velocities are determined as functions of wave number, and material properties of CNTRC beams are estimated using the mixture rule. Comparative analysis with Euler and Timoshenko beam theories is conducted to validate findings. The mathematical model is numerically verified against existing results, and the study explores the impact of CNT enhancement modes, volume fraction, spring factor, and other factors on CNTRC beam wave propagation behaviors [28].

Mangalasseri et al. [29] delves into the energy harvesting properties of a magneto-electro-elastic cantilever beam enhanced with carbon nanotubes (CNT) during transverse vibration. Employing a lumped parameter model to mathematically represent the coupled multiphysics problem, the study explores the impact of factors like CNT distribution, substrate material, and length-to-thickness ratio on energy harvesting behavior. The research aims to enhance comprehension of smart material-based energy harvesting systems, specifically those reinforced with CNT, offering potential implications for the design and analysis of CNT-based smart structures [29].

Arshid et al. [30] explores the vibration analysis of functionally graded microplates with polymeric nanocomposite patches, incorporating porosity and hygrothermal effects. The microplates feature three layers, including an FG porous core and piezoelectric nanocomposite face sheets with stiffness-enhancing CNTs. Using a quasi-3D shear deformation theory and modified couple stress theory, the equations of motion are derived. Figure-presented results allow assessment of material properties, geometry, foundation moduli, and hygrothermal effects on vibrational behavior. Findings indicate that increasing CNT volume fraction improves mechanical properties, subsequently raising natural

frequency. Notably, the study emphasizes the substantial impact of accounting for the hygrothermal environment in analyzing these structures [30].

Huang et al. [31] introduces a size-dependent model for analyzing the static stability of doubly curved micro-panels made of advanced composites reinforced with carbon-based materials. The research combines a seven-unknown shear deformation theory in curvilinear coordinates with a non-classical approach to assess the mechanical performance of micro-size shells accurately. Utilizing a virtual work of Hamilton statement and an analytical technique based on double-Fourier series, the study analyzes micro shells with fully simply supported conditions at edges. Results show that CNTs reinforced composite curved shells exhibit a hardening response under buckling, with the critical buckling load highest for spherical panels, followed by elliptical, cylindrical, and hyperbolic panels. Moreover, changes in CNTs weight fraction significantly impact the static stability characteristics of CNTs reinforced composite curved size-dependent shells [31].

Heidari et al. [32] addresses the need to enhance the realism of engineering models for nanocomposites, critiquing past studies that assumed idealized properties of carbon nanotubes (CNTs). The study focuses on incorporating real-world complexities like nanotube waviness, defects, and aggregation observed in experiments. It introduces size effects into nanocomposite models, validating their accuracy through comparisons with experimental data and theoretical models. The article presents numerical examples illustrating buckling behaviors of nanocomposites, emphasizing the application of nonlocal theory to account for size effects. Overall, it is the first comprehensive exploration of these aspects, providing a crucial reference for future research in nanocomposite materials [32].

Undertaking a comprehensive review in the field of carbon nanotube applications within building materials is justified by several compelling reasons. First, it offers a methodical framework for gathering and comparing data from a myriad of sources. This systematic approach enhances comprehension by researchers and engineers as they navigate the wealth of available information. Second, the review serves as a spotlight on the pivotal challenges confronted by those working with carbon nanotubes in building materials. Through this scrutiny, critical obstacles come to the fore, pinpointing areas ripe for further exploration and unveiling the realm's untapped potential.

Furthermore, this review becomes a tapestry that weaves together diverse data from research articles, patents, and technical reports. This comprehensive mosaic fosters a panoramic understanding while circumventing potential distortions from cherry-picked examples.

Despite the extensive research into carbon nanotubes, there are a number of gaps in this area. The first shortcoming is the lack of wider comparative research comparing the properties of many building materials with and without CNTs. This limits the ability to make an objective comparison and identify clear benefits of using CNTs in construction. Therefore, more detailed studies based on comparative analysis can be a valuable contribution to the field. In addition, a more detailed discussion of the technical issues and challenges associated with the industrial scaling up of CNT production and its economic feasibility is essential for the practical introduction of CNTs in the construction industry and requires further research and development. In light of the above, this study also aims to fill knowledge gaps and present new results related to the use of CNTs in construction. This review can also provide recommendations on how to overcome current technical and environmental challenges to ensure a more sustainable and efficient use of CNTs in the construction industry.

This review also covers all aspects of CNT properties and their impact on construction materials, allowing us to assess the full potential of CNTs and their applicability in various construction industries. Additionally, previous studies may be limited in their methodology and scope. Some may be based on a small sample of data or use outdated data analysis

methods and tools. This paper improves the methodological approach using modern data analysis tools and a wide range of literature sources to obtain more comprehensive and reliable results.

The practical significance of this review article lies in its ability to systematically inform interested industries and to move towards a more sustainable future by exploring the potential use of CNTs as material amplifiers. The article highlights the problems that need to be solved before practical implementation and gives an idea of current research in this area.

2. Methodology

This section provides a comprehensive outline of the study's methodology. It begins with the careful formulation of research goals and objectives. A thorough search of scientific literature is conducted using Scopus and Google Scholar databases to gather a wide range of relevant works. The collected data undergo meticulous analysis using Python and VOSviewer software. Python is employed for data processing, statistical analyses, and result visualization, while VOSviewer aids in creating a visual representation of the literature landscape, highlighting key themes and authors. The study then delves into diverse methods for carbon nanotube production, including CVD, electrochemical deposition, and mechanical stretching, alongside insights from illustrative studies. Catalysts for CVD are scrutinized for their impact on nanotube formation. Strategies for integrating carbon nanotubes into building materials are explored, covering blending, coating, and functionalized nanotube incorporation, with a focus on enhanced properties. The research tasks encompass defining goals, selecting methods, investigating nanotube properties, and processing results. This culminates in drawing meaningful conclusions from the accumulated data and comparative analyses. The following steps outline the methodological process (Fig 1) :

2.1. Literature Search

A thorough literature search was conducted using two primary databases : the Scopus bibliographic and abstract database and the Google Scholar search engine. The search was performed by employing a combination of relevant keywords and phrases related to the research topic. The selected keywords were carefully chosen to ensure a comprehensive coverage of the relevant literature.

2.2. Data Extraction

After obtaining the search results, data from the Scopus database was downloaded in the RIS format (Research Information Systems) to facilitate further analysis. The RIS format is widely used for bibliographic data exchange and is compatible with various data analysis tools.

2.3. Data Analysis in Python

Data analysis was performed using the Python programming language, leveraging its powerful libraries for data manipulation and analysis. The bibliographic data downloaded in the RIS format was processed and cleaned to ensure the accuracy and consistency of the dataset. Python's data analysis libraries, such as Pandas and NumPy, were utilized for data cleaning, transformation, and preparation.

2.4. VOSviewer Analysis

In addition to the Python-based data analysis, the data was also imported into VOSviewer, a powerful bibliometric analysis software. VOSviewer allowed us to create visual representations of the co-occurrence of keywords, authors, and publications within the dataset. This analysis provided valuable insights into the most prominent research themes, patterns, and interconnections among different concepts.

2.5. Integration of Results

The findings from both the Python-based data analysis and the VOSviewer analysis were integrated to create a comprehensive picture of the literature landscape related to the research topic. The combined results enabled us to identify key research trends, influential authors, and significant clusters of related publications.

2.6. Interpretation and Discussion

The interpreted results from the data analysis were discussed in the context of the research objectives and existing literature. The implications of the findings were critically analyzed to draw meaningful conclusions and identify potential areas for future research.

By adopting this methodological approach, the study aimed to ensure a robust and systematic exploration of the existing literature and provide a solid foundation for the subsequent stages of analysis and discussion.

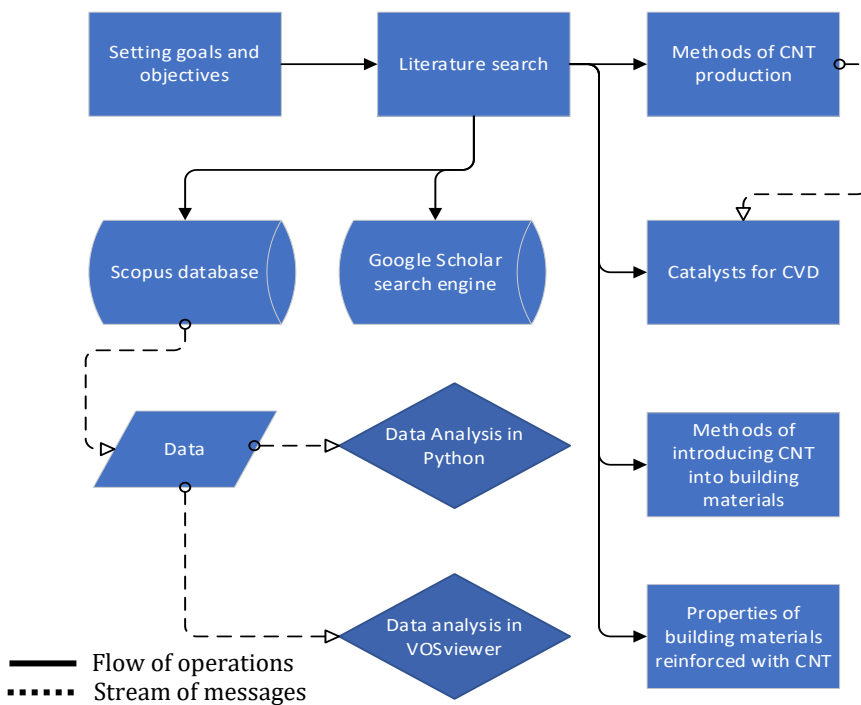


Fig. 1. Methodology flowchart

3. Results and Discussion

3.1 CNTs Analysis in Research Literature: 2019-2023

To gather relevant information, a literature search was conducted using the Scopus bibliographic and abstract database, as well as the Google Scholar search engine. The search results were visualized using the VOSviewer software, which facilitated the analysis of keywords found in the publications. The data covered a significant number of articles for 2019-2023: a total of 57,633 articles were found. Of these, 11,816 articles for 2019 were used in visualization and analytics, 20,000 articles (due to the fact that Scopus database allows you to upload no more than 20,000 results to one file at a time) for 2020 (a total of 23,520 articles were found in 2020), 20,000 articles for 2021 year (23,580 articles were found), 20,000

articles for 2022 (24,490 articles were found) and 20,000 articles for 2023 (22,237 articles were found). This comprehensive study of research articles highlights the growing interest and importance of carbon nanotubes in various fields, including construction.

Figure 2 illustrates the distribution of frequently encountered keywords in publications over time. These keywords include nanocomposites, single-walled CNTs, polymers, supercapacitors, heat resistance, tensile strength, and other relevant terms. On the other hand, Figure 3 presents the clustering results of the same search query.

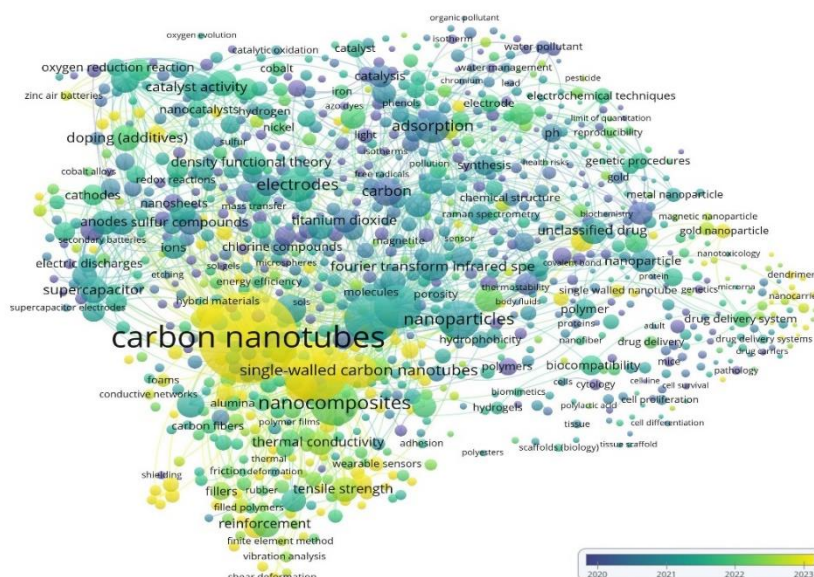


Fig. 2. Search results for "carbon nanotubes" in Scopus

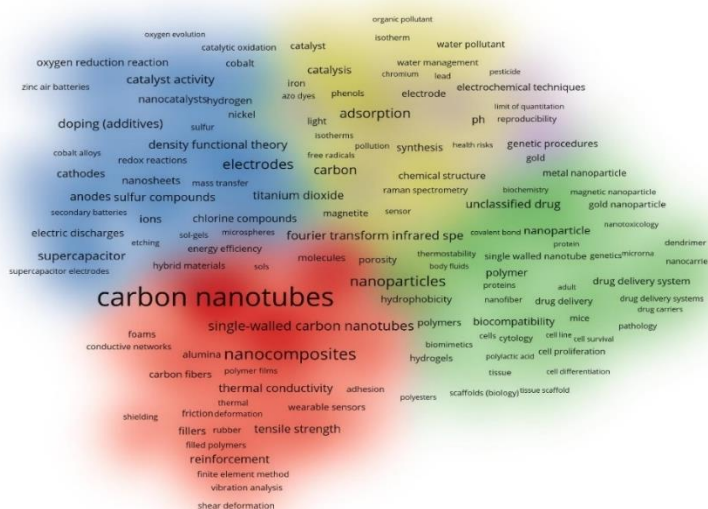


Fig. 3. Results of the "carbon nanotubes" search query in Scopus by cluster

A set of articles published between 2019 and 2023 related to the query "carbon nanotubes" was extracted. Subsequently, an analysis was conducted using Python scripts, and the Pandas and Matplotlib libraries were employed to process and visualize the data.

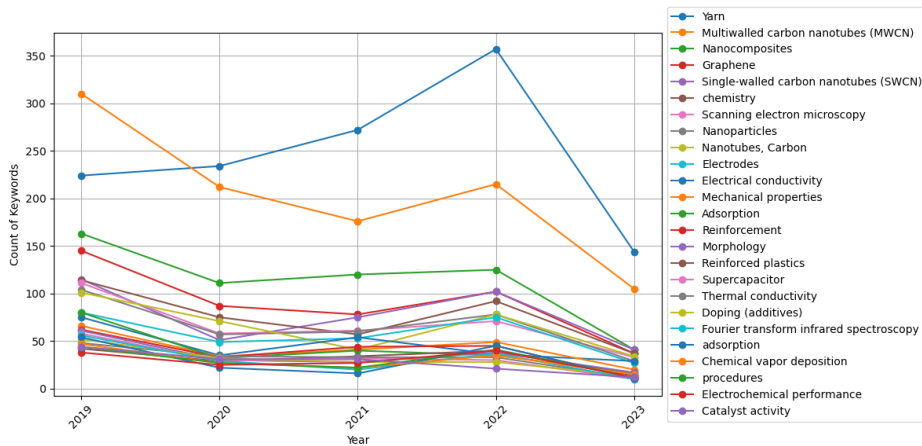


Fig. 4. Results of keyword analysis by articles

Figure 4 depicts the distribution of the 25 most frequent keywords in the articles, categorized by year (Fig 4). The results presented in Figure 4 were generated by excluding certain words from the search, namely "Review", "Article", "Priority journal", "Controlled study", "Graphene", "Carbon nanotubes", "Nanotechnology", and "Nanoparticle". These words were excluded due to their high frequency and tendency to appear in nearly all articles. Conversely, Figure 6 showcases a histogram containing all keywords, including the highly frequent ones, presenting the grouping of the 15 most frequent keywords by publication year.

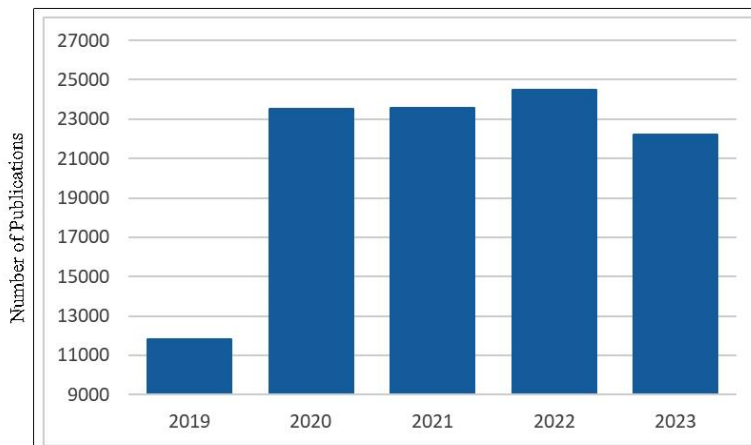


Fig. 5. Number of articles by year

Figure 5 shows a histogram of the total number of publications for the query "carbon nanotubes" in the Scopus database. As can be seen in Figure 5, the number of articles for this query peaks in 2022. The number of articles shows a decrease in 2023. This decrease in 2023 can be explained by the fact that the data only cover the period up to September 2023, which is not the full year of data collection.

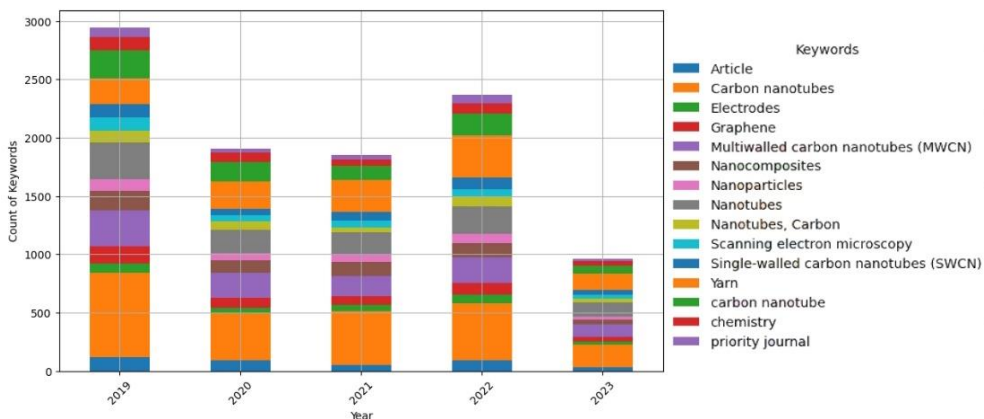


Fig. 6. The most high-frequency keywords

Using the Jupyter Notebook web development tool and the Word Cloud library, word clouds were generated to visualize the search results. The word cloud of frequently encountered words in the abstracts of review articles is displayed in Figure 7a, while Figure 7b presents the word cloud of high-frequency keywords. A cloud of words frequently found in the abstracts of all reviewed articles is shown in Figure 8a, and a cloud of high-frequency keywords is shown in Figure 8b. These visual representations offer an intuitive means to observe the prominence and relevance of various words within the search results.

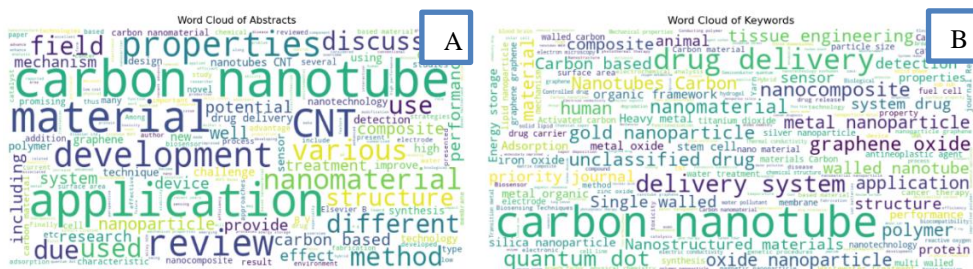


Fig. 7. Word cloud (a) abstracts of review articles, (b) keywords



Fig. 7. Word cloud (a) abstracts of all articles, (b) keywords

3.2 Methods of CNT production

CNT production methods encompass various techniques used to create carbon-based nanotubes. Among them, the most common methods include hydrocarbon pyrolysis, laser ablation of graphite, electric arc synthesis, and chemical vapor deposition (CVD).

Hydrocarbon pyrolysis involves decomposing hydrocarbons into carbon and other byproducts to produce CNTs [33, 34]. This method is extensively utilized for large-scale CNT production. Pyrolysis of hydrocarbons, also known as pyrogenic synthesis, entails the decomposition of organic compounds into carbon, hydrogen, and oxygen at high temperatures. It is a widely employed approach for producing carbon nanomaterials like carbon nanotubes, fullerenes, and graphene.

Special equipment called a pyrolysis unit (Fig.8) is employed for the pyrolytic synthesis of hydrocarbons. The unit consists of a reaction chamber where the synthesis occurs and a gas supply system. To prevent contamination of nanomaterials, the reaction chamber is typically made of stainless steel or ceramics. The pyrolytic synthesis process initiates by heating the hydrocarbons to temperatures exceeding 700°C. At this temperature, the hydrocarbons decompose into carbon, hydrogen, and various gases. The carbon remains in the form of nanoparticles that subsequently aggregate.

One notable advantage of pyrolytic synthesis is its capability to produce carbon nanomaterials with high purity and uniformity. Furthermore, this method allows for control over the size and shape of the resulting nanomaterials. However, pyrolytic synthesis does have some drawbacks, such as high equipment costs and energy consumption. Additionally, the hydrocarbon pyrolysis method may not be suitable for producing all types of CNTs and may be limited in cases where specific properties are desired (e.g. high electrical conductivity or resistance to oxidation).

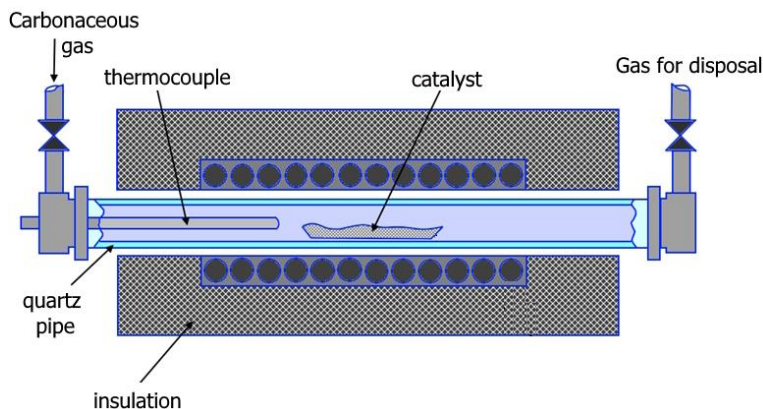


Fig. 8. Schematic diagram of a horizontal batch reactor for pyrolysis of carbon-bearing gases [35]

Laser ablation of graphite involves the use of powerful laser radiation to evaporate and subsequently condense graphite in a vacuum (Figure 9). This process breaks down graphite crystals into individual carbon atoms, which then assemble into nanoparticles [36, 37].

Laser ablation of graphite is capable of producing ultra-dispersed carbon nanostructures, including carbon nanotubes, carbon nanofibers, carbon nanoribbons, and more. These nanomaterials possess unique properties such as high electrical conductivity and mechanical strength, making them highly promising for diverse applications. Additionally, laser ablation of graphite is an environmentally friendly method as it does not require the use of chemicals or high temperatures, thus making it attractive for industries like automotive, aviation, and space.

However, one of the main challenges associated with laser ablation is the difficulty in controlling the process of obtaining carbon nanostructures. The high temperature and pressure generated during ablation make it challenging to precisely control the size and shape

of the resulting nanoparticles. This variability can impact the properties and application of the nanotubes. Another drawback is the high cost of laser ablation equipment and materials. This method necessitates expensive laser equipment and specialized materials like graphite. Moreover, the ablation process itself is time-consuming and energy-intensive. Low productivity can also be considered a disadvantage of laser ablation. While this method produces carbon nanostructures with a high degree of purity and uniformity, it may be less efficient compared to other nanoparticle production methods.

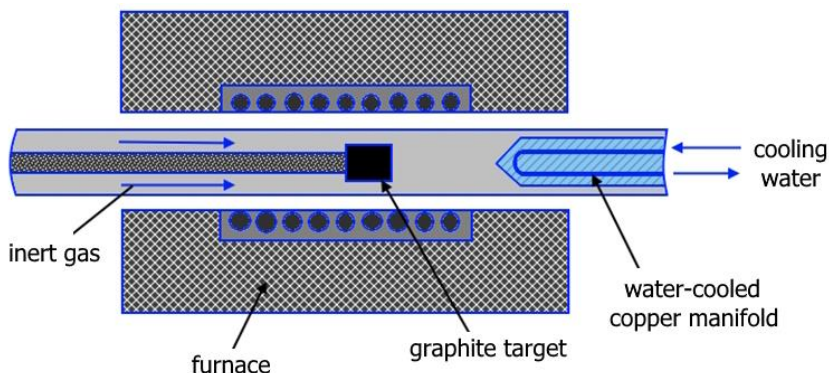


Fig. 9. Schematic diagram of a machine for CNT production by laser ablation [35]

In a study conducted by the authors [38], they successfully synthesized graphene sheets in two stages at room temperature and normal pressure. The process involved laser ablation of graphite, followed by repeated irradiation of suspensions after removing the graphite target. X-ray analysis confirmed the production of different carbon materials.

Several factors influence the synthesis of carbon nanotubes through laser ablation, including temperature, catalyst selection, choice of inert gas, laser power, wavelength, pressure, and fluid dynamics near the carbon target [39]. These parameters must be carefully controlled during the synthesis of CNTs.

Electric arc synthesis is another method utilized for producing CNTs. This technique involves the use of an electric arc to heat and melt a metal catalyst such as graphite or nickel (Fig.10). The molten metal is then cooled and crystallized, resulting in the formation of nanotubes. During the synthesis process, the nanotubes emerge from the catalyst and are collected in bundles, which can be subsequently cleaned and shaped to the desired size and form. The main advantages of electric arc synthesis for CNTs are its simplicity, speed, and controllability. Additionally, this method does not require the use of expensive catalysts, thereby reducing production costs.

Electric arc synthesis offers a versatile approach for producing various carbon nanomaterials, including carbon nanotubes and carbon nanoparticles, with diverse sizes and shapes. Despite its drawbacks such as high energy consumption and low yield, it remains a widely employed method in scientific and industrial fields involved in the synthesis and application of carbon nanomaterials [40, 41].

Chemical vapor deposition (CVD) is one of the most prevalent methods for producing carbon nanotubes [43, 43]. It enables the synthesis of large-diameter and high-purity CNTs. CVD involves the decomposition and condensation of organic compounds in the gas phase onto a catalyst surface at high temperatures.

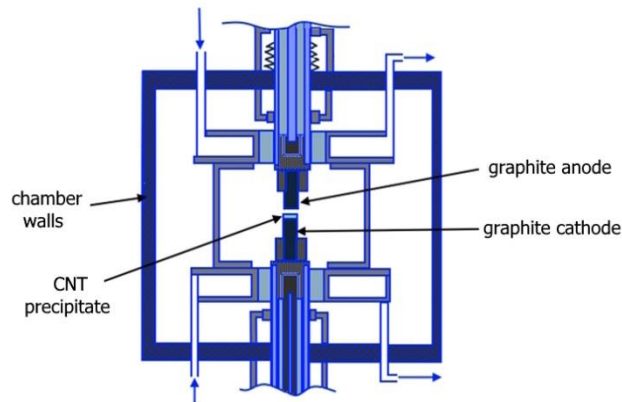


Fig. 10 Schematic diagram of a plant for producing CNT by electric arc synthesis [35]

In CVD, specialized reactors are employed where high temperatures (typically ranging from 700 to 1,000 degrees Celsius) and pressures are maintained (Figure 11). The reactor is filled with a gas mixture comprising a reagent (e.g., benzene or acetylene) and a catalyst (commonly graphite or nickel). At elevated temperatures, the reagent decomposes into gaseous products, which subsequently condense on the catalyst's surface. This process leads to the formation of nanotubes that accumulate on the surface and continue to grow until they reach a specific diameter.

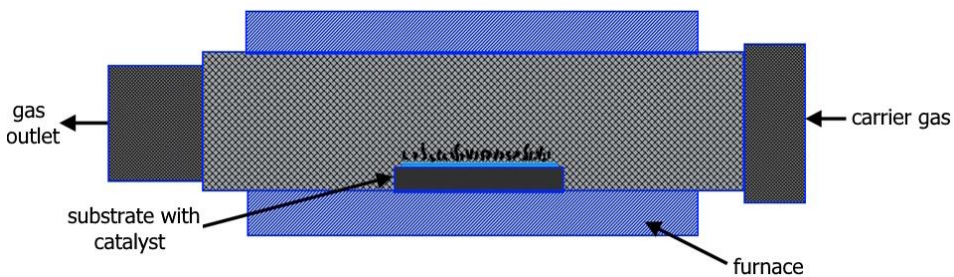


Fig. 11 Chemical vapor deposition (CVD) method [44]

Chemical vapor deposition (CVD) is not only utilized for producing carbon nanotubes but also for other types of carbon nanomaterials, including amorphous carbon and carbon nanoparticles. The method offers the advantage of controlling the size and shape of the resulting structures by adjusting process parameters such as temperature, pressure, and gas mixture composition. CVD is capable of generating nanotubes with varying diameters and shapes, making it a versatile technique for numerous applications.

CVD finds applications in various fields, including microelectronics. In microelectronics, CVD is employed for producing integrated circuits and other electronic devices. The method of CVD offers several advantages:

Precise control: CVD allows for meticulous control over the size and shape of nanomaterials through precise adjustment of process parameters.

High purity: CVD produces nanomaterials with high purity and low impurity concentrations due to its robust process control.

Convenience and efficiency: The CVD process are easily automated, enabling precise adjustment of process parameters. Moreover, the method is highly efficient, yielding significant volumes of nanomaterials.

Unique properties: CVD-derived nanomaterials often exhibit distinctive physical and chemical properties that are not typically observed in materials produced through other methods.

Thus, chemical vapor deposition is a powerful and effective approach for producing carbon nanomaterials with exceptional properties, making it a popular choice in scientific research [45, 46]. For instance, a study [47] compared single-walled carbon nanotubes produced via CVD with those obtained using an improved electric arc synthesis method. The results revealed that CVD-produced nanotubes exhibited superior dispersion into thin fibers, even at the monolayer level.

In another work [48], mechanical properties and corrosion resistance of composites reinforced with CVD-produced carbon nanotubes at varying mass fractions (0.1%, 0.2%, and 0.5%) were investigated. The study determined that the most corrosion-resistant structure was achieved in composites reinforced with 0.2% CNTs.

Chemical Mechanical Exfoliation (CME) is a method for producing high-purity carbon nanotubes (CNTs) through a combination of chemical and mechanical processes. The process involves the preparation of graphite as a starting material, followed by chemical functionalization to facilitate subsequent processing. Mechanical exfoliation, which can be achieved through various methods, separates graphite layers and forms CNTs. Purification and characterization complete the process, providing high-quality CNTs with controlled properties [49–52].

The **Floating Catalyst Method** utilizes catalyst nanoparticles suspended in a gaseous carbon source to produce high-quality CNTs. The process involves catalyst preparation, reactor installation, catalyst suspension in a carrier gas, introducing the carbon source, catalytic growth, nanotube recovery, and post-treatment. This method offers controlled CNT production with various properties but requires careful control of catalyst parameters and addressing potential impurities [53–55].

The **Template-Assisted Growth** method directs CNT growth using templates with defined nanopores. Steps include template preparation, catalyst deposition, introducing a carbon source, nanotube growth within the template's nanopores, template removal, and post-treatment [56–59]. This method provides precise control over CNT diameter, length, and alignment and is compatible with various substrates [60].

Plasma Enhanced Chemical Vapour Deposition (PECVD) is a technique for creating Uniform Nanotube Arrays (UNAs) via plasma-assisted chemical reactions [61–65]. It involves substrate preparation, precursor gas introduction, plasma discharge, thin film deposition, and post-processing. PECVD offers controlled UNA production, uniform characteristics, and versatility across different substrates for applications in various industries [66–68].

Electrochemical Deposition (ECD) is another method for producing UNAs on a conductive substrate through an electrochemical cell [69–71]. It involves substrate preparation, immersion in an electrolyte solution, application of an electric potential, nanotube growth, and post-processing [72–74]. ECD allows precise control over nanotube dimensions and produces uniform arrays for applications in energy storage, catalysis, sensors, and electronics [75–79].

Solvothermal Method: This method involves a hydrothermal reaction in a solvent at high temperatures and pressures to synthesize CNTs with controlled properties and structures [80–84]. The process includes precursor preparation, reactor setup, sealing, reaction and

growth, cooling, product recovery, and post-treatment [85–88]. It shows promise for CNT synthesis but has limitations such as cost, complexity, and environmental impact [89–96].

Mechano-thermal Synthesis: This approach combines mechanical activation and thermal treatment to produce highly ordered and crystalline CNTs [97–99]. Mechanical forces are used to break down precursor carbon materials, creating amorphous carbonaceous precursors [100–102]. Subsequent thermal treatment at high temperatures transforms these precursors into well-aligned CNTs [103,104]. Challenges include the need for precise control of mechanical activation and high-temperature processing [105,106].

Flame Synthesis: This technique uses a controlled combustion process to generate CNTs by decomposing precursor solutions in a high-temperature flame [97,106,107]. It offers continuous and scalable production, allowing adjustments in CNT size, diameter, and structure. Challenges include controlling CNT growth and dealing with unwanted byproducts [106,108,109].

Chemical Vapor Infiltration (CVI): CVI involves the deposition of carbon atoms onto a substrate through the controlled decomposition of gaseous precursors [110–112]. It allows for versatile, large-scale production, and the ability to tailor CNT properties. Deposition conditions impact growth rate, structural characteristics, and alignment [113–116].

Electrolysis: The Electrolysis method applies an electric current to a carbonaceous electrode immersed in an electrolyte solution [117,118]. This process leads to the direct synthesis of CNTs, providing control over their growth conditions and properties [119,120]. Challenges include low yield, slow growth rates, and the need to control CNT morphology and purity [121–123].

Understanding the advantages and disadvantages of various CNT production methods is crucial for selecting the most suitable approach for specific tasks. Table 1 provides an overview of CNT production methods, offering brief descriptions of their principles of action along with their advantages and disadvantages. The benefits and disadvantages mentioned in this table are not exhaustive and may vary depending on specific process parameters and conditions.

Table 1. Methods of CNT production

The method	Principle of operation	Benefits	Disadvantages
Pyrolysis of hydrocarbons [124–132]	Decomposition of organic compounds at high temperature	Low cost, high performance, scalability, good controllability of process parameters	CNTs may contain impurities, which can reduce their quality and properties; small diameter of CNTs; CNTs may be less resistant to oxidation than nanotubes produced by other methods
Laser ablation of graphite [106,133–138]	Effects of laser radiation on carbon materials	Possibility to produce single- and multi-layer CNTs of different shapes, high purity	High equipment costs, limited product volume, difficulty in controlling process parameters
Electric arc fusion [139–145]	Heating of carbon materials in an electric arc	Production of various sizes of CNTs, high synthesis rate	Limited size, need for inert gases, high cost, risk of CNT damage
Chemical vapor deposition (CVD) [146–154]	Reaction between a carbon source and other reagents in the gas phase	Ability to produce CNTs on different substrates, control of size and shape of nanostructures, high productivity, scalability	Risk of reaction byproducts that can adversely affect the quality of the resulting tubes, difficulty in setting up the process

The method	Principle of operation	Benefits	Disadvantages
Chemical Mechanical Exfoliation (CME) [155–160]	Mechanical exfoliation of layered carbon materials	Simple and low-cost method, production of high-quality CNTs with good crystallinity	Limited scalability, difficulty in achieving uniformity in CNT properties
Floating Catalyst Method [55,161–168]	Suspension of catalyst nanoparticles in a gaseous carbon source	Production of single- and multi-walled CNTs, high purity, control over diameter and alignment	High equipment costs, limited product volume, difficulty in controlling process parameters
Template-Assisted Growth [58,59,169–175]	Utilization of templates or nanopores to direct CNT growth	Precise control over diameter, length, and alignment of CNTs, scalability	Template removal can be challenging, limited choice of template materials
Plasma Enhanced Chemical Vapor Deposition (PECVD) [63,65,176–179]	Chemical reaction in a plasma environment	High deposition rate, good control over CNT properties, compatibility with various substrates	Plasma-induced damage to CNTs, requirement for specialized equipment
Electrochemical Deposition [180–185]	Electrochemical reaction for CNT growth on a conductive substrate	Controlled growth of CNTs, precise control over dimensions and alignment	Limited scalability, potential for electrode contamination
Solvothermal Method [84,186–192]	Hydrothermal reaction in a solvent at high temperatures and pressures	Synthesis of CNTs with regulated properties and structures	Limited scalability, high temperature and pressure requirements
Mechano-thermal Synthesis [97,193–198]	Combination of mechanical activation and thermal treatment	Production of highly ordered and crystalline CNTs, scalability	Potential for impurities, careful control of mechanical activation parameters required
Flame Synthesis [199–205]	Controlled combustion of hydrocarbon or carbon-containing precursors	Continuous production, control over CNT size and structure, in situ functionalization	Challenges in controlling CNT growth and uniformity, potential formation of unwanted byproducts

The characteristics of nanotubes obtained can vary based on the method used and process conditions. In conclusion, each of these methods possesses its own advantages and disadvantages, and the selection of a specific method depends on the particular requirements and production conditions.

For instance, pyrolysis of hydrocarbons is the most commonly employed method; however, it may result in the formation of impurities and structural defects in the nanotubes. Laser ablation of graphite yields nanotubes with high purity but necessitates costly equipment. Electric arc synthesis produces nanotubes with larger diameters but incurs high energy costs. Chemical vapor deposition allows for precise control over the structure and properties of nanotubes.

Therefore, the choice of CNT production method should be justified and based on a compromise between quality requirements and economic efficiency.

3.3. Catalysts for CVD

Chemical vapor deposition (CVD) is a widely employed and cost-effective technique for manufacturing carbon nanotubes (CNTs). During CVD, CNTs are synthesized by depositing the dissociation products of hydrocarbons onto a metal catalyst that serves as a "seed," followed by the growth of nanotubes on the catalyst surface.

The selection of a suitable catalyst plays a crucial role in achieving efficient CNT generation through the CVD method. An ideal catalyst should possess a high surface area, acting as the active center for chemical reactions, and offer a sufficiently high temperature for carbide decomposition. These catalysts can also be employed in the synthesis of other carbon nanostructures like graphene or fullerenes. The choice of catalyst depends on the desired structure and properties of the nanoparticles.

Chemical vapor deposition catalysts are primarily composed of metals or their oxides and are instrumental in expediting the formation of carbon nanostructures. Nickel is one of the most commonly used catalysts for CVD, enabling the synthesis of CNTs with high purity and uniform structure. Other metals such as copper, chromium, and molybdenum are also utilized as catalysts. Additionally, carbon precursors like graphite or CNTs can function as catalysts for CNT synthesis.

For instance, a copper-based catalyst can be employed in CNT synthesis. When a carbon-containing gas such as acetylene is heated, nanotubes form on the copper surface, which can then be separated from the catalyst for various applications.

Numerous catalysts are employed for CNT production via CVD under diverse conditions. These catalysts include metals like iron (Fe), nickel (Ni), cobalt (Co), their alloys, as well as surface-modified metals and their oxides.

While iron and nickel were initially the most prevalent catalysts for CNT production through CVD, researchers have been exploring more effective catalysts in recent years to achieve high-quality CNTs [206–208]. Studies indicate that iron alloys with other metals such as copper (CuFe) or cobalt (FeCo) can enhance productivity and purity during the CVD process. In CVD, carbon nanomaterials are formed by the interaction between carbon and various gases, typically hydrogen, carbon monoxide, or acetylene. Catalysts can comprise metals, oxides, hydroxides, or other substances, accelerating the decomposition of carbon-containing gases into carbon atoms and molecules, which subsequently combine into nanostructures.

The choice of catalyst depends on the desired properties of the resulting nanomaterials and the specific synthesis conditions. Ongoing advancements in catalyst research for CNT production via chemical vapor deposition allow for continual updates and improvements to this method [209–218]. It is important to select the most appropriate catalyst for specific process conditions and the desired properties of the nanotubes.

Table 2 below presents catalysts and their properties for CVD. However, it is worth noting that the size and quality of CNTs may slightly vary depending on process conditions such as temperature, pressure, and gas mixture composition. The first column of Table 2 denotes the catalyst (or elemental basis for combined catalysts) with corresponding references to studies utilizing them for CNT production. The subsequent columns in Table 2 provides general information and characteristics of each catalyst, independent of the referenced studies in the first column. This is because catalyst properties can differ based on the process conditions of vapor deposition, including temperature and pressure. Therefore, selecting the most suitable catalyst for specific process conditions and desired nanotube properties is crucial.

Table 2. CVD catalysts

Catalyst	Diameter of nanotubes	Quality of nanotubes	Features
Ferrocene [219-221]	~ 10-20 nm	Low	Ferrocene-based nanotubes are not only of low quality, but also heterogeneous in width. It is quite unstable and can form a heterogeneous film.
Ni [222-224]	~ 10-100 nm	High	Ni-based nanotubes are of high quality and have a single-wall structure. Quite cheap and widespread catalyst. Provides high quality nanotubes and very few defects in the structure.
Co [225,226]	~ 5-50 nm	Very high	Co-derived nanotubes are of very high quality and have a single-wall structure, which makes them possible for use in electronics. It is also a cheap catalyst.
Fe [227-230]	~ 10-100 nm	Average	Fe-based nanotubes are of average quality and may contain additional defects in the structure. It is chemically stable but forms a lower quality film than Ni, Co.
Al [231,232]	~ 10-60 nm	Average	Al-based nanotubes are of average quality and may contain additional defects in the structure. It is not the best catalyst, but can be used to produce nanotubes of a certain type.
Pt [233,234]	~5-50 nm	Very high	One of the best sparse catalysts: provides very high quality and purity of nanotubes.
Pd [235,236]	~5-50 nm	Very high	Similar to Pt in its characteristics, but cheaper.
Ti [237]	~5-100 nm	Average	Provides good quality nanotubes and a structure different from that obtained with other catalysts.
Mo [238]	~5-50 nm	Average	It can be used to produce multiwalled nanotubes.
Cu [239-242]	~5-50 nm	High	It has high catalytic activity for CVD reaction. It can be used to produce nanotubes of different materials.
Au [243,244]	~5-50 nm	Low	It is not the best catalyst for the CVD reaction and is not normally used for producing nanotubes.
Co Ni Au [235]	Various sizes	Miscellaneous	Combinations of catalysts can combine the advantages of different materials. For example, the combination of Co and Ni gives very good nanotube quality, and the combination of Ni and Au gives good charge transfer properties.

The table 2 clearly illustrates the substantial variation in cost, nanotube quality, and defectiveness among catalysts. The selection of a specific catalyst depends on numerous factors, including availability and cost. For instance, Fe serves as an inexpensive catalyst, enabling the production of nanotubes at low temperatures and pressures. However, the resulting nanotubes exhibit lower quality and often contain numerous defects. On the other hand, Pt is highly expensive but yields high-quality nanotubes with a low defect rate. Moreover, catalysts can be combined to enhance results [246-249]. For example, the combination of Ni and Co yields nanotubes of the highest quality and low defect levels,

whereas the combination of Cu and Ni enables the production of nanotubes with diverse materials.

This section provides a concise overview of catalysts utilized in the CVD method, underscoring their significant influence on the properties of carbon nanotubes. Consequently, selecting an appropriate catalyst becomes crucial in achieving desired carbon nanotube properties, such as size and structure, and should align with specific requirements.

3.4. Methods of Introducing CNT Into Building Materials

The incorporation of carbon nanotubes (CNTs) into building materials has emerged as a novel and increasingly popular strategy for enhancing their mechanical and physical properties. Recent years have witnessed numerous studies exploring the utilization of CNTs in diverse building materials, including concrete and reinforced polymers [250,251].

Mechanical introduction stands out as one of the primary approaches for integrating CNTs into building materials. This method involves simply adding nanotubes to the material during its preparation in the form of dust, powder, or liquid. To ensure a more uniform dispersion of CNTs within the material, techniques such as ultrasonic or magnetic treatment can be employed [252–254]. Ultrasonic processing facilitates the pulverization of CNT particles, leading to their more even distribution throughout the material. Similarly, magnetic treatment can be utilized to fractionate CNT particles into smaller sizes, thereby enhancing their dispersion within the material [255,256].

In addition to mechanical introduction, other processing techniques can be employed to enhance the efficacy and quality of the CNT incorporation process. Surfactant functionalization is one such method, where surfactants are used to improve the wettability of CNTs, allowing for better dispersion within the matrix [257–261]. Sonication, which utilizes high-frequency sound waves, can also be used to break up CNT agglomerates and ensure better dispersion [262–265].

The specific method of incorporating CNTs into building materials depends on the desired properties and operating conditions. For example, in the case of concrete, CNTs can be added as nano powders or through the creation of functional coatings [266–268]. This helps improve the strength, corrosion resistance, and shrinkage reduction of the concrete. For materials like bricks and glass, functional coatings and nano powder addition can enhance properties such as fire resistance, thermal insulation, transparency, and scratch resistance [269,270].

In the case of metals, including steel and aluminum, CNTs can be introduced through the addition of nano powders or by creating functional coatings [271,272]. This improves the durability and corrosion resistance of the metals [273–275]. Plastic materials can also benefit from the addition of CNTs in the form of a liquid additive, which enhances wear resistance and durability [276,277]. Similarly, the addition of CNT powder to rubber materials improves wear resistance and elasticity [278–280].

These examples highlight the versatility of CNT incorporation, as different materials can be enhanced by utilizing CNTs in various ways. The selection of materials and the specific method of introducing CNTs depend on the desired improvements and the specific requirements of each application. Continued research and collaboration among material scientists, engineers, and industry professionals will drive further advancements in this field, opening up new possibilities for the construction industry.

In essence, the mechanical introduction of CNTs represents one of the most commonly employed methods for their incorporation into building materials, with additional processing techniques employed to enhance the efficacy and quality of the process. Table 3 provides a concise overview of exemplary building materials exhibiting improved properties, along with the prevalent methods employed for incorporating CNTs into their structural composition.

Table 3. Construction materials with improved CNT properties

Construction materials	Improved properties	Methods of introducing CNT into building materials
Concrete [281–286]	Strength, corrosion resistance, shrinkage reduction	Adding nanopowders, creating functional coatings
Brick [287–291]	Resistance to fire, improved thermal insulation	Creating functional coatings, adding nanopowders
Glass [292–296]	Transparency, scratch resistance	Adding nanopowders, creating functional coatings
Metal [297–302]	Durability, corrosion resistance	Adding nanopowders, creating functional coatings
Plastic [303–307]	Resistance to wear and tear, durability	CNT liquid additive
Rubber [308–315]	Wear resistance, elasticity	Addition of CNT powder

These examples provide a glimpse into the diverse range of materials that can be enhanced by incorporating Carbon Nanotubes (CNTs). The selection of materials and the method of introducing CNTs depend on specific requirements and operating conditions governing each case.

CNTs offer tremendous potential in strengthening building materials by augmenting their mechanical properties, including increased strength, stiffness, impact resistance, and abrasion resistance. Furthermore, CNTs can impart electrical or thermal properties to materials, thereby expanding their functionality. However, the practical utilization of CNTs beyond the confines of laboratory settings is still constrained. One of the primary challenges involves achieving a uniform dispersion of CNTs within the material while preventing their aggregation, as such clustering can substantially compromise the material's quality [316–317].

Presently, nanotechnology finds active application across various industries. One significant application area involves the modification of building materials to enhance their properties. This section elucidates the methods employed for introducing CNTs into building materials and explores their potential application in creating efficient and secure building structures.

3.4.1. Mechanical Methods

One approach for incorporating carbon nanotubes (CNTs) into building materials is through mechanical methods. These methods rely on simple mechanical processes to introduce CNTs into the structure of the material.

Ultrasonic dispersion is a technique where CNTs are dispersed within a material using ultrasonic waves. The waves create cyclic compression and tension zones in the material, resulting in the dispersion of nanoparticles. This method is highly efficient and produces nanometer-sized particles, enabling the production of materials with enhanced strength and durability. For instance, researchers [318] investigated the impact of multi-walled carbon nanotubes (MWNTs) with varying internal diameters on the mechanical properties and microstructure of cement-based materials. Ultrasonic dispersion was employed to uniformly distribute MWNTs within the cement-based materials. Experimental results demonstrated that increasing the diameter of MWNTs modified the flexural and compressive strength of cement-based materials.

Ultrasonic dispersion is a widely used method for incorporating carbon nanotubes (CNTs) into building materials. This process involves subjecting CNTs to high-frequency sound waves (typically in the range of 20-100 kHz) to break up agglomerates and disperse individual CNTs throughout the material matrix. The equipment used includes a sonicator, which generates the sound waves, and a vessel containing the material to be dispersed. The power output and frequency depend on the application and material properties[319,320].

Ultrasonic dispersion not only breaks up agglomerates but can also functionalize CNTs by introducing chemical groups onto their surfaces. This enhances their compatibility with the matrix and improves mechanical properties. The smaller size of dispersed CNTs (typically tens of nanometers) leads to a more homogeneous distribution within the matrix.

One advantage of ultrasonic dispersion is its ability to achieve a more uniform dispersion of CNTs, enhancing the mechanical properties of the material. It also reduces agglomeration of CNTs, preventing the formation of large clusters that could negatively impact the material's properties.

Furthermore, ultrasonic dispersion enhances the interfacial bonding between CNTs and the material matrix, improving load transfer and the overall integrity of the composite material.

Mechanical activation is another method where the material is mechanically loaded to activate the surface and create defects. These defects, including dislocations, voids, and microcracks, facilitate strong bonding between CNTs and the building material, resulting in a composite material with improved strength and durability [321,322]. Researchers [323] investigated various modified cement composites produced through mechanical activation. They utilized superplasticizers and CNTs with different structures and functionalities as modifiers. The study revealed that the bio resistance coefficient values of cement composite samples obtained by mechanically activating the binder and incorporating superplasticizers were 13% higher than those of the control composition.

Mechanical exposure involves saturating the material with CNTs using moving parts such as mills or mixers. This method generates high mechanical energy, breaking down the CNTs into nanometer-sized particles that then penetrate the material. By employing this approach, it is possible to produce materials with enhanced strength and durability while minimizing the quantity of CNTs required [324–326].

Overall, the utilization of mechanical methods for introducing CNTs into building materials enables the creation of materials with nanoparticle reinforcement, resulting in improved strength and durability. However, achieving the maximum effect requires careful selection of the optimal component ratios and material processing techniques.

3.4.2. Electrochemical Methods

Electrochemical techniques offer highly effective means of incorporating carbon nanotubes (CNTs) into various building materials, including concrete, asphalt, and polymer composites. One such technique is the electrochemical deposition of thin carbon films onto the material surface. This process involves depositing carbon nanoparticles onto the material surface by applying an electric current in a solution containing suitable reagents [327–329]. The method finds wide application in diverse fields, including electronics, catalysis, cosmetics, as well as scientific research in nanotechnology and materials science.

Electrochemical carbon deposition has proven beneficial in several areas. Firstly, it can be used to coat electrodes, thereby enhancing their conductivity in different devices and systems [330,331]. Secondly, carbon coatings serve as catalysts on material surfaces, improving the efficiency of processes such as electrolysis or gas synthesis. Additionally, carbon coatings find application in the production of electronic components like supercapacitors and solar cells.

The advantages of electrochemical carbon deposition include precise control over the deposition process, the ability to create thin, uniform, and high-quality carbon films, cost-effectiveness compared to other coating methods, and the potential to modify the properties of carbon coatings to suit specific needs [332–334]. However, there are also certain limitations associated with this technique. It requires careful adjustment of the deposition process to achieve the desired surface properties, and there may be defects in the film

structure that could impact its properties. Furthermore, there are limitations on the types of materials onto which the coating can be applied.

Kim et al. demonstrated the use of a chemical deposition method to enhance the performance of a fuel cell electrode by employing CNTs and a Pt catalyst as the foundation. Their results indicated that the number of catalytic centers in Pt/CNTs obtained through electrochemical deposition was approximately three times higher [335]. Another study by Lee et al. proposed an efficient and practical approach for creating a new composite comprising ultrathin nanowire films by combining an assembly process with cost-effective electrochemical deposition technology [336].

Electrodeposition, another method for introducing CNTs into building materials, involves embedding CNTs into the material surface through an electrochemical reaction. The process utilizes an electric field to deposit CNTs onto the material surface. CNTs, serving as nanoparticles, enhance the properties of building materials that typically consist of metallic or polymeric components. The electrodeposition process begins with the preparation of a solution containing CNTs, which is then placed in an electrolytic bath. The material is immersed in the bath and connected to an electrode, while another electrode connected to an electric current source is positioned adjacent to the material. Subsequently, the electrodeposition process initiates, resulting in the deposition of CNTs onto the material surface.

This method offers advantages such as simplicity and the ability to control material conductivity by adjusting the CNT concentration in the solution. Additionally, materials obtained through CNT electrodeposition exhibit good shape and size matching, reducing the likelihood of defects [337,338]. However, this method has drawbacks, including a relatively low CNT concentration compared to other CNT introduction methods and the requirement for specialized equipment, making it a relatively complex process.

3.4.3. Chemical Methods

Chemical techniques offer a range of possibilities for incorporating Carbon Nanotubes (CNTs) into building materials, resulting in the development of materials with exceptional properties, including enhanced strength, thermal conductivity, and electrical conductivity. However, each method possesses its own set of advantages and disadvantages, and the selection of a specific technique depends on the intended purposes and requirements of the manufactured materials.

One such method is chemical deposition, which involves depositing a CNT solution onto the surface of the material [339–341]. This process begins by preparing a solution containing CNTs in a specialized liquid, typically ethylene glycol or other solvents. Various application techniques such as spraying or dripping are employed to apply the nanotube solution onto the material's surface.

Another method, known as metal fusion, employs the combination of different metals to coat the material's surface. This technique involves mixing CNTs with metal powders and subjecting them to high temperatures to form a composite material. Metal fusion exhibits notable advantages, including high wear resistance and excellent thermal conductivity, making it suitable for the production of construction materials like metal structures and pipelines.

The metal fusion method finds extensive use in modern industries, enabling the production of high-quality composite materials with unique properties unattainable by conventional carbon steels and other materials [342–345]. The process of metal alloying comprises several steps:

Alloy preparation: Various methods, such as mechanical mixing of metal powders with CNTs in a ball mill, are utilized to create a homogeneous mixture.

Material formation: The mixture from the previous step is heated to temperatures typically exceeding 1000 degrees Celsius, causing the metal powders and CNTs to merge and form a homogenous material with the desired properties.

Heat treatment: Heat treatment is necessary to enhance the material's mechanical properties and harden it. The composite material is subjected to specific temperatures during heat treatment and subsequently cooled down.

The advantages of the metal fusion method for building material production are numerous. These include high resistance to wear and mechanical damage, excellent thermal conductivity, significant resistance to corrosion and chemical reactions, and the ability to produce composite materials in various shapes and sizes.

In summary, chemical methods, such as chemical deposition and metal fusion, allow for the integration of CNTs into building materials, offering exceptional properties [346–349]. The choice of method depends on specific requirements, with metal fusion providing excellent wear resistance, thermal conductivity, corrosion resistance, and versatility in creating composite materials with unique shapes and sizes.

3.4.4. Physical Deposition Methods

Physical deposition methods for carbon nanotubes (CNTs) encompass a range of technologies and processes utilized to distribute nanotubes onto the surfaces of building materials.

Ion-beam deposition is a technological process that employs ion streams to generate thin coatings on material surfaces [350,351]. The process initiates by producing a high-frequency flux of ions dispersed in a gas medium, typically within a vacuum. The flux is then directed towards the substrate where the coating is intended to adhere. The ion flux is separated into positive and negative ions.

The distinctive feature of ion-beam deposition lies in the ability to precisely control the size, energy, and velocity of the ions. This enables the production of thin coatings with thicknesses ranging from fractions of a micron to several micrometers. When the ion flux impacts the material surface, it induces various chemical reactions and alterations in the CNT molecules, resulting in the formation of a thin layer on the material surface. These coatings can be created from a diverse range of materials, including ceramics, metals, plastics, and glass [352–355].

Ion-beam deposition finds extensive applications in the manufacturing of various devices such as microprocessors, sensors, optical devices, and more [356–358]. During the ion-beam deposition process, several factors need to be considered, including ion energy, the type of ions employed, the deposition medium, and the pressure within the vacuum chamber.

Magnetron sputtering is a technology employed to produce thin coatings on diverse material surfaces [359–362]. In this process, materials are atomized within a vacuum and then deposited onto the target surface. Special generators generate electric and magnetic fields within the working chamber to initiate the sputtering process. Atomized materials find applications in various industries, including electronics production, solar cells, medical products, and others. Magnetron sputtering enables the production of coatings with different characteristics based on specific requirements [363–365].

In a particular study [366], the authors discussed various applications of magnetron sputtering in the development of crucial materials for lithium batteries, categorized according to battery components such as electrode materials and solid electrolytes. The authors also proposed future prospects to drive the advancement of magnetron sputtering technology.

Vacuum cathode discharge represents one of the methods for growing CNTs on material surfaces [367,368]. It involves utilizing a vacuum chamber with a cathode composed of graphite or other carbon materials. When a high-frequency discharge passes through the

chamber between the anode and cathode, CNTs begin to grow on the cathode's surface. The key advantage of this method is the ability to create CNTs with predetermined characteristics, including length, diameter, and structure. Additionally, this method is relatively straightforward and controllable.

However, there are also certain disadvantages. The CNT growth procedure within the vacuum chamber requires significant energy and time, which poses challenges for scaling up this method for industrial applications. Furthermore, the equipment cost for vacuum cathode discharge is relatively high. Nevertheless, vacuum cathode discharge remains an effective method for CNT creation in specific applications such as electronics, catalysis, and other fields [369,370].

3.4.5. Nanotechnology Methods

Electron beam lithography represents a cutting-edge technology used to fabricate micro- and nanostructures through controlled local treatment of a material's surface with an electron beam [371–374]. By employing this technology, carbon nanotubes (CNTs) can be incorporated into construction materials to enhance their mechanical properties. The process of introducing CNTs using electron beam lithography involves several key stages:

- **Surface Preparation:** The material's surface is meticulously cleaned and machined to create a specific pattern suitable for CNT integration.
- **Applying Resist:** A resist material, capable of undergoing changes when exposed to an electron beam, is applied onto the material's surface.
- **Exposure:** An electron beam is precisely directed onto the resist-coated surface, resulting in the formation of the desired pattern.
- **Manifestation:** The resist material that has been exposed to the electron beam is selectively removed from the areas corresponding to the pattern.
- **Application of CNTs:** A solution containing CNTs is applied onto the material's surface, specifically targeting the created pattern. This procedure reinforces the mechanical properties of the material at the required locations.
- **Cleaning:** Excess resist and any remaining residues are thoroughly eliminated from the material's surface.

This method of material reinforcement enables the production of lightweight yet robust and durable materials suitable for various construction applications [375,376]. Electron beam lithography serves as an effective approach to bolster building materials, facilitating the creation of more dependable and long-lasting structures [377–379].

Another technique involves incorporating CNTs into construction materials using a paramagnetic filler, which operates on the principles of electromagnetic induction [380–382]. Initially, CNTs are synthesized via chemical vapor deposition (CVD) using a suitable catalyst. Subsequently, the dispersion of CNTs in a solution containing a paramagnetic filler is performed to generate a nanocomposite. In some cases, the CNTs are treated with the paramagnetic filler before dispersion. The nanocomposite undergoes further treatment using an electromagnetic field created through electromagnetic induction. The paramagnetic filler within the solution responds to the induction field and adheres to the CNTs, resulting in the formation of an electromagnetic composite.

Consequently, a composite material comprising CNTs embedded with paramagnetic fillers is obtained [383–385]. This approach enhances the composite's magnetic susceptibility while simultaneously improving its mechanical and functional properties. The integration of CNTs using paramagnetic fillers presents a promising avenue for developing novel construction materials with enhanced characteristics. Although some of these methods can be expensive and require specialized equipment and expertise, they enable the creation of stronger and more flexible building materials utilizing the potential of CNTs.

Table 4. Methods of CNT introduction

Group	Methods	Principle of operation
Mechanical methods	Ultrasonic dispersion [386–388]	Mechanical impact creates pores in the material, where CNTs are then inserted
	Mechanical activation [307,389]	Mechanical impact creates pores and cracks in the material, where CNTs are then introduced
	Mechanical impact [390–393]	Mechanical impact creates additional spaces for nanotubes
Electrochemical methods	Electrochemical deposition [394–398]	An electrochemical process using a metallic cathode that serves as a current-carrying element
	Electrodeposition [399–403]	Using electrodeposition to create a thin layer of carbon inside the material
Chemical methods	Chemical deposition [404–407]	Using catalysts to create CNTs
	Metal alloying method [408–412]	A method that uses metal fusion to create organic compounds, which are then replaced by CNTs
Physical deposition methods	Ion Beam Deposition [378,413–416]	Using ion-beam deposition to create a thin layer of carbon on a material surface
	Magnetron sputtering [417–422]	Using magnetron sputtering of carbon to create a film on the material surface
	Vacuum cathode discharge [360,416]	Using vacuum cathodic discharge to create a thin layer of carbon on the material surface
Nanotechnology methods	Electron beam lithography [375,378,424,425]	Using a lithographic process to create microchannels on the material surface, where CNTs are then added
	Nanotubes with paramagnetic filler [385,426–429]	Using paramagnetic particles to trap CNTs in solution and direct them to the surface of the building material. The nanotubes then remain on the surface of the material and form a protective layer

Integrating carbon nanotubes (CNTs) into building materials offers numerous advantages, such as enhanced strength, increased resistance to corrosion and wear, and improved thermal insulation properties [340,430–433]. However, prior to their utilization in construction, extensive research and testing are imperative to ensure both their safety and effectiveness.

The study of CNT properties and their application in building materials is a rapidly advancing field in science and technology. Within this realm, the exploration of methods for incorporating CNTs into building materials holds considerable significance as a subject of investigation.

To summarize, the methods employed to introduce CNTs into building materials exhibit considerable potential for creating more robust and long-lasting materials. Nonetheless, it is essential to consider the specific characteristics of each method and assess its efficacy under distinct conditions. Furthermore, continuous research in this domain is vital to develop novel approaches and optimize existing ones, ultimately achieving optimal outcomes.

3.5. Properties of Building Materials Reinforced with CNT

In the past few years, there has been a growing interest among engineers and scientists in enhancing the quality of building materials to ensure better protection and durability for

structures against external forces. One promising avenue of research involves the incorporation of carbon nanotubes (CNTs) to reinforce these materials [434–438]. In this section, we will explore the characteristics of building materials that are strengthened by CNTs. It is important to note that the concentration of CNTs and other relevant parameters can have a significant impact on the properties of these materials. Gaining a thorough understanding of these properties can be valuable for the development of novel materials that can construct more dependable and long-lasting buildings and structures. Nonetheless, it is crucial to consider the issues of economic feasibility and environmental safety when pursuing these advancements.

3.5.1. Mechanical Properties

The reliability and durability of construction materials heavily rely on their mechanical properties. A promising area of research in this field involves the utilization of Carbon Nanotubes (CNTs) to enhance the strength of materials.

Strength: Research studies indicate that the incorporation of CNTs into building materials can substantially enhance their strength. Factors such as the concentration of nanotubes, their position within the material matrix, and the size of the matrix particles have a significant influence on strengthening the material. Furthermore, nanotubes can mitigate thermal stresses caused by temperature fluctuations, which further contributes to the material's strength.

Shi et al.[439] outlines the principal characteristics of carbon nanotubes/nanofibres, the techniques for dispersing CNTs in cement-based materials, and the properties of CNT-based materials following modification with cement. The study affirm that the inclusion of CNT enhances the mechanical characteristics of cementitious materials.

The investigation of Jung et al. [440] employed diverse quantities of CNTs (0, 0.2, 0.5, 0.8, 1.0 and 2.0 weight percent). Prior research has indicated that introducing CNTs into cement-based materials can enhance their mechanical characteristics and cut down on porosity. Nevertheless, surpassing a certain concentration result in a decline in compressive strength.

Research conducted by Thomoglou et al. [441] suggests that the optimal amount of CNTs in cement mortar can provide improvements in various mechanical properties. Specifically, it was found that the incorporation of 0.2 wt% MWCNTs resulted in an increase in flexural strength by approximately 5.7%, compressive strength by 18.4%, 6.2%, and 8.8% for nano-, micro- and hybrid-modified cement mortars, respectively, compared to conventional mortars. These findings highlight the potential of CNTs in enhancing the mechanical performance of construction materials.

Stiffness: The introduction of CNTs can also increase the stiffness of building materials. Numerous experiments have demonstrated that as the concentration of nanotubes increases, the stiffness of the material also increases. Moreover, the deformation mechanisms induced by the presence of nanotubes can enhance the material's overall stiffness.

Kumar et al.[442] introduces the dynamic stiffness method (DSM) as a tool for analyzing the vibrations of multilayered plates containing carbon nanotubes (CNTs). The authors apply the Vitruvian-William method to solve the frequency-dependent stiffness matrix, allowing for an examination of the effects of various parameters on the plate and layer configuration. The findings from this study can be valuable for the design of multilayered FG-CNT structures, providing insights into optimizing their vibrational characteristics and performance.

Li et al. [443], the authors focus on the enhancement of compressive stiffness in graphene aerogels using a unique approach inspired by the structure of leaves. By incorporating carbon nanotubes (CNTs) into the aerogel matrix, they create a new material called CNT-interlayered graphene aerogels (CSGAs) through the process of freeze drying. The researchers conduct

compression tests and observe that the presence of CNTs effectively reinforces the mechanical support of the aerogels, with the properties of CSGAs being influenced by the content of CNTs. Furthermore, molecular dynamics modeling reveals that an optimal concentration of CNTs forms a stable mesh structure, thereby preventing deformation of graphene nanosheets during bending. This study presents a promising strategy for the design of highly efficient graphene-based nanomaterials, thereby expanding the range of potential applications for these materials.

Fracture Resistance: CNTs can enhance the fracture resistance of building materials. For instance, studies have shown that carbon nanotubes can absorb impact energy and localize material damage [444–447]. This characteristic proves particularly valuable in safeguarding buildings and structures from the detrimental effects of explosions or natural disasters.

Table 5 presents a summary of the mechanical properties of CNT-enhanced materials in comparison to conventional building materials. The table encompasses four key characteristics of the materials: compressive strength, tensile strength, wear resistance, and corrosion resistance. According to the table, materials treated with CNTs exhibit significantly higher compressive strength, tensile strength, and wear resistance when compared to most industrial construction materials. However, it is important to note that the properties of improved CNT materials can vary considerably depending on the specific type of material and the technology employed.

Table 5. Characteristics of the properties of building materials with CNT

Characteristics	Most building materials	Materials improved by CNT
Compressive strength [448–452]	Relatively low	Up to 4 times higher
Tensile strength [453–458]	Relatively low	Up to 10 times higher
Resistance to wear and tear [459–465]	Relatively low	Up to 5 times higher
Corrosion resistance [466–475]	Relatively low	Above

Studies of the properties of building materials reinforced with CNTs show that this approach can significantly improve their mechanical properties. Positive effects can manifest themselves in the strength, stiffness, and resistance to failure of the materials. Understanding these properties may lead to the creation of more reliable and durable building materials for various objects and structures.

3.5.2. Thermal Properties

Enhancing the thermal properties of building materials is crucial for efficient energy utilization and ensuring comfort inside structures. Factors such as heat transfer, thermal insulation, and thermal stability greatly influence the performance of materials. One approach to improving these properties is through the incorporation of Carbon Nanotubes (CNTs).

CNTs possess exceptional thermal conductivity, and when integrated into materials, they can significantly enhance their ability to conduct heat. This improved thermal conductivity facilitates better temperature control within buildings, leading to reduced heating and air conditioning costs. By introducing CNTs, the overall thermal conductivity of the material increases, leveraging the exceptional thermal conductivity of CNTs themselves.

Consequently, the use of CNTs in building materials enhances their thermal properties, enabling more efficient utilization of energy resources and improving comfort levels indoors. Additionally, CNTs exhibit high thermal stability, resulting in increased thermal stability of

the building materials. This enhancement improves the overall performance and prolongs the service life of the materials. For example, concrete structures containing CNTs display enhanced resistance to fire and other hazards due to their improved ability to withstand higher temperatures.

Shin et al.[476] discuss the development of three types of thermoplastic polyurethane composites (TPU) based on carbon nanotubes (CNTs) to create lightweight, flexible, and heat-conducting materials for electromagnetic interference (EMI) protection. The composites were developed using a solution blending technique with non-solvent induced phase separation (NIPS). The study investigates the impact of CNTs of different lengths on EMI shielding, electrical conductivity, and thermal conductivity. The composite with long CNTs (10 wt.%) demonstrated remarkable EMI shielding efficiency of 42.5 dB and an electrical conductivity of 1.9×10^{-3} S/cm, while the composite with short CNTs exhibited a thermal conductivity of 0.51 W/mK, with a thermal conductivity enhancement exceeding 145% compared to pure TPU. The inclusion of long-length CNTs facilitated the formation of interconnected conductive networks within the TPU matrix, improving mechanical properties, EMI shielding, and electrical properties. Conversely, short CNTs showed significant electromechanical characteristics and heat transferability. The composites also demonstrated high sensitivity to electrical conductivity and minimal changes in EMI shielding effectiveness during repeated bending cycles. This study provides insights into different types of CNT-based TPU composites for superior EMI protection and thermal regulation in next-generation wearable and stretchable electronics.

In another related study of Jin et al. [477], the development of highly thermally conductive polymer composites with excellent dielectric and mechanical properties for electronic devices is discussed. The researchers incorporated boron nitride, graphene nanoplatelets, and carbon nanotubes into a polycarbonate matrix to enhance thermal conductivity, dielectric constant, and mechanical properties. The resulting composite exhibited a 647% increase in thermal conductivity, a 50-fold increase in dielectric constant, and improvements in yield strength, elongation at break, fracture toughness, and notched impact strength. Moreover, the composite displayed reduced ignitability and remarkable anti-dripping performance. This research presents an effective strategy for fabricating dielectric thermal conductive polymer composites with excellent properties for electronic devices.

Furthermore, incorporating CNTs in building materials can increase their heat capacity. This feature is particularly advantageous for constructing structures capable of absorbing and storing heat, effectively reducing heating costs.

Overall, the utilization of CNTs in building materials offers several benefits, including efficient energy utilization and improved comfort within buildings.

To further illustrate the impact of enhanced nanotechnology (CNTs) on thermal properties, Table 6 provides information on various materials. The table includes five different materials: polymer composites, ceramics, metals, concrete, and glass. Each material is presented with its thermal properties before and after the incorporation of CNTs. The first column displays the material names, while the second and third columns present the respective thermal properties before and after the inclusion of CNTs. The table also includes various parameters related to the thermal properties of the materials.

Table 6. Thermal properties of building materials with CNT

Material	Thermal properties without CNT	Improved thermal properties using CNTs
Polymer composites [478–483]	May have limited thermal stability	The use of CNTs significantly improves thermal stability, reduces thermal conductivity and increases material strength
Ceramics [484–489]	Has high thermal resistance, but often does not have high strength	Use of CNTs increases material strength and thermal resistance
Metals [490–493]	Can have relatively high thermal conductivity and low thermal stability	Use of CNTs increases material strength and thermal resistance
Concrete [494–500]	Has low thermal stability and limited strength	The use of CNTs can increase the strength of the material and improve its thermal stability
Glass [501–506]	Fragile material that does not have high thermal resistance	The use of CNT significantly increases the strength of the material and its thermal stability

3.5.3. Electrical And Magnetic Properties

The introduction of CNTs into construction materials can lead to a change in their electrical properties. This is due to the fact that CNTs have high electrical conductivity. For example, in the work [507] experiments were conducted on cylindrical concrete samples containing different CNT content up to 0.04%, in which the effect of an alternating magnetic field on the strength was evaluated. Magnetization of samples containing 0.02% CNT gave higher strength than the introduction of 0.04% CNT without magnetization.

By the authors [508] studied the effect of temperature and water content on the electrical conductivity of cement mortar with different sizes of carbon nanotubes and revealed the effect of CNT size on the electrical conductivity of cement mortar. The results show that small diameter CNTs best improve the electrical conductivity of cement mortar. The electrical conductivity of cement mortar with different diameters of carbon nanotubes positively correlates with water content, and as the diameter of carbon nanotubes in the sample decreases, the effect of water content on the electrical conductivity of carbon nanotube cement mortar becomes less.

Corrosion resistance. CNTs can improve the corrosion resistance of construction materials such as metals, concrete and ceramics. CNTs can be added to building materials in the form of a nanofiller that forms a protective layer on the surface of the material. This layer prevents water, acids and other aggressive media from penetrating the interior of the material and protects it from corrosion [509,510].

Table 7 presents the results of studies related to the introduction of CNTs into various materials. Various materials such as concrete, epoxy, wood, rubber, brick, ceramic, steel and asphalt coating were investigated with respect to their properties after the introduction of CNT in different concentrations.

Recent research findings have demonstrated the positive impact of incorporating carbon nanotubes (CNTs) into various materials. This inclusion has led to enhancements in mechanical properties, as well as safeguarding against corrosion and fungal growth. However, determining the optimal concentration of CNTs in each material necessitates further investigation. These research outcomes serve as a foundation for subsequent studies and the optimization of materials containing CNTs. The integration of CNTs can substantially enhance the properties of diverse materials, ultimately contributing to the development of more robust and secure structures in the future.

The utilization of CNTs in building materials holds both economic and environmental advantages. On one hand, CNTs can augment the properties of construction materials, rendering them stronger, more corrosion-resistant, wear-resistant, and durable. Consequently, this can significantly diminish the costs associated with repairing and replacing such structures, thereby proving cost-effective. Additionally, CNTs can enhance the thermal characteristics of materials, facilitating energy savings and reduced expenditures on heating and air conditioning.

Nevertheless, the production of CNTs can be expensive and resource-intensive, potentially escalating the costs of CNT-infused building materials. Moreover, it is crucial to consider environmental factors, such as the ecological and health impacts of producing and utilizing such materials. Certain methods employed in CNT production may generate hazardous waste, emissions, and even disrupt ecosystems. Consequently, economic and environmental aspects must be carefully evaluated when employing CNTs to strengthen building materials. Striking a balance between economic efficiency and environmental safety is imperative when selecting construction materials.

Table 7. Construction materials with CNT

Material	CNT content	Short Description	Source
Concrete	0.10 wt.%, 0.15 wt.%	CNTs have been found to slow the propagation of microcracks by forming bridges through microcracks in concrete.	[511]
	0, 0.03, 0.08, 0.15, 0.25 wt%	The results showed that concrete prepared with high CNT content of 0.15 and 0.25 wt% increased flexural strength by more than 100% compared to concrete with 0% CNT.	[512]
	0.03 to 0.5 wt%	The results showed that 0.03% CNTs with long-term treatment increased the compressive, flexural, and tensile strength of conventional concrete by 23, 29, and 20%. The analysis also showed that using less CNTs (0.03 and 0.08 wt%) gave higher strength results regardless of the nanofiber treatment.	[513]
	0.05-0.1 wt%	It has been demonstrated that 0.05-0.1% CNTs effectively improve the tested properties, increasing the compressive, bending and cleavage strength as well as the fracture energy and modulus of elasticity by up to 23%, 18%, 27%, 42% and 15%, respectively.	[514]
	0.01, 0.02 , 0.03 wt%	The results of the experimental work showed that the introduction of CNT led to an increase in the compressive and tensile strength of the samples compared with the control sample.	[515]
Epoxy	0.107, 0.213 and 0.425 vol.%	The maximum synergistic effect of carbon and ceramic fillers on the dielectric properties of the epoxy-based composite was detected at a CNT content of 0.213 vol.%.	[516]
	0.1, 0.5 and 1 wt%	The results showed that the greatest improvement in the mechanical properties of the CNT/epoxy resin composite was observed in the sample with 0.5 wt% CNT, which had a tensile strength of 61 MPa and Young's modulus equal to 1.8 GPa.	[517]
	0.50 wt%	The tensile strength and toughness of epoxy nanocomposites with 0.50 wt% MWNTs improved by 21% and 46%, respectively, compared to conventional epoxy.	[518]
Wood	0.2%	Antifungal tests showed that stronger growth inhibition was obtained for samples treated with 0.2%	[519]

Material	CNT content	Short Description	Source
		MWNT, ZnO + solution. The most effective treatment is a concentration of 0.2% nanocomposite applied with a brush. Thus, protection of wood against mold and fungi was achieved, while providing improved mechanical strength and water protection properties.	
Silicone Rubber	1.25, 5.5, 7.5, 9.5 wt%	The results show that the proposed mixed carbon nanoconductive silicone rubber has good properties and great application prospects.	[520]
Brick	0.01%	The compression strength of the MUNT-added bricks was 53.9% and 45.52% higher compared to commercially available and traditional bricks.	[521]
Ceramics	0.1, 4 wt%	The thermal conductivities of nanocomposites with different amounts of carbon nanotubes (0, 1 and 4 wt%) were investigated. Thermal conductivity increases with increasing temperature, 1 wt% CNT/silica nanocomposite provides the highest thermal conductivity.	[522]
Steel	0.05, 0.1, 0.3, 0.5 wt%	Among all the samples tested, the lowest corrosion rate was achieved at 0.1 wt% CNT nanofluid, while the highest value was obtained at 0.5 wt% CNT nanofluid. At higher CNT concentrations, the accumulated CNTs can form active anode sites and increase the corrosion rate.	[523]
	0.2, 0.5, 1.0, 2.0 wt%	The composite samples showed increased wear resistance compared to the primary and commercial grades.	[524]
Asphalt surface	0.1, 0.5, 1 wt%	The study demonstrates that the introduction of CNT into asphalt cement improves asphalt concrete performance in both hot and cold weather, which in turn extends pavement life and saves maintenance costs.	[525]

Therefore, the utilization of CNTs to reinforce building materials represents a promising frontier in modern engineering. This technology presents unique opportunities to enhance material properties, including strength and fracture resistance. However, the successful implementation of this technology necessitates further research on the economic and environmental efficiency of producing and employing CNT-infused materials. Overall, the integration of CNTs in building materials instills hope for the creation of more durable and safer structures in the future.

3.6. Challenges and Future Directions in CNT Applications for Building Materials

The production and application of Carbon Nanotubes (CNTs) in building materials face several significant challenges. While CNTs hold immense promise for revolutionizing the construction industry, these challenges must be addressed for their widespread adoption. Here are some of the key issues:

- **Large-Scale Production and Cost:** Achieving large-scale production of high-quality CNTs at a reasonable cost is a major challenge. Current methods, like chemical vapor deposition (CVD), have issues with efficiency, high synthesis temperatures, and limited control over properties.
- **Control of CNT Growth:** Precise control over the growth process is needed to prevent the formation of unwanted carbon structures alongside desired CNTs, as these impurities can affect properties of construction materials.

- **Uniform Dispersion:** Ensuring uniform dispersion of CNTs within construction materials is crucial. Agglomeration can affect mechanical performance and poses health and safety risks to workers.
- **Interface Bonding:** Establishing a robust interface between CNTs and the matrix is essential for maintaining mechanical strength.
- **Health and Safety Risks:** The potential health and safety risks associated with CNTs must be carefully managed.
- **Long-Term Stability and Durability:** Evaluating the long-term performance of CNT-based composites under different environmental conditions is crucial to ensure durability.
- **Cost-Effectiveness:** The high cost of CNTs, processing steps, and potential alterations needed for large-scale production can impact economic feasibility.

To overcome these challenges and fully realize the potential of CNT-based building materials, recommendations for future research and development include:

- **Optimization of CNT Dispersion Techniques:** Investigate innovative dispersion methods to prevent agglomeration, such as functionalization, surfactants, and advanced mixing techniques.
- **Enhancement of Interfacial Bonding:** Develop strategies for improving the bond between CNTs and the matrix to optimize mechanical properties.
- **Scalable Production Processes:** Explore cost-effective synthesis methods and processing approaches that can be scaled up without compromising CNT quality.
- **Safety and Environmental Impact Assessment:** Thoroughly assess health and safety risks, develop safety protocols, and conduct environmental impact assessments.
- **Multifunctional Material Development:** Explore the potential for multifunctional CNT-based building materials, such as self-healing, self-cleaning, or thermal regulation capabilities.
- **Long-Term Durability Studies:** Conduct studies to evaluate the long-term stability and durability of CNT-based building materials under various environmental conditions.

4. Conclusions

CNTs have exceptional mechanical properties, making them attractive for construction. Adding CNTs to concrete enhances its strength and durability. However, challenges include higher material costs and the need for specialized methods to ensure proper distribution. Establishing standards and regulations for safety and reliability is crucial. Further research will determine better techniques for incorporating CNTs into building materials. Utilizing CNTs in construction has the potential to create more resilient structures.

The optimal concentration of CNTs to enhance the properties of different materials is also a crucial consideration and may vary depending on the material type and desired characteristics. Here are a few examples:

Polymeric materials: For polymers like polyethylene or polypropylene, an optimal concentration ranging from 0.5% to 5% is typically recommended. This concentration range achieves improved mechanical properties such as strength and stiffness, along with enhanced thermal and electrical conductivity. In the case of elastomers, such as rubber materials, the optimal CNT concentration is generally lower, usually between 0.1% to 1%, which enhances the elastic and mechanical properties, such as resistance to rupture and deformation.

Metallic materials: In the case of metals like aluminum or iron, the optimal concentration of CNTs typically falls within the range of 0.5% to 2%. Incorporating CNTs within metallic materials can enhance their strength, hardness, thermal conductivity, and electrical

conductivity. It is also important to ensure proper dispersion of CNTs in the metal matrix to achieve homogeneity and uniform reinforcement of properties.

Ceramic materials: When it comes to incorporating carbon nanotubes (CNTs) into ceramic materials such as oxides, carbides, or nitrides, it is recommended to add them in the range of 1% to 10%. While this range can enhance properties such as strength, hardness, thermal conductivity, and dielectric properties, it is important to carefully consider the potential drawbacks. The use of a high concentration of 10% CNTs in ceramic materials can lead to increased brittleness, affecting the material's integrity and processing. Additionally, it should be noted that such a high concentration may also significantly impact the overall cost of the material. Given these considerations, it would be advisable to reassess and fine-tune this concentration range to strike a balance between material properties and cost-effectiveness.

The optimal concentration of CNTs can vary based on specific conditions. Further studies and laboratory experiments will aid in determining the optimal CNT concentration for particular materials. Advancements in catalyst development play a significant role in improving the chemical vapor deposition (CVD) process for producing high-quality CNTs. Catalysts influence the growth, structure, morphology, and properties of CNTs. One approach involves employing novel catalysts based on metals or alloys such as nickel, iron, cobalt, molybdenum, and their compounds. These materials exhibit high activity and stability, contributing to more efficient CNT growth. Precious metal-based catalysts like platinum or palladium are also being explored to enhance CNT quality and achieve higher-quality single-layer and defect-free growth.

A comprehensive examination of catalyst shape and structure is crucial to optimize the CVD process and improve CNT quality. Studies have shown that the use of nanostructured catalysts, such as nanoparticles, nanowires, or nanofilms, facilitates more uniform and controlled CNT growth. Additionally, modifying the catalyst's surface with layers of other materials like oxides or carbides has been considered. This approach helps improve catalyst adhesion and stability, while also providing control over CNT growth. Optimizing the gas mixture composition used in the CVD process can significantly impact CNT growth and quality. The addition of different gases, such as hydrocarbons, inert gases, or decomposition intermediates, aids in controlling growth rate, structure, and dispersion of CNTs.

Practical applications of CNT-reinforced materials in construction include:

Concrete composites: CNTs can be employed to reinforce concrete, creating composite materials with high strength and resistance to breakage. This leads to improved mechanical properties of concrete.

Reinforcement of metal structures: Introducing CNTs into metal materials enhances their mechanical properties, such as strength and stiffness, thereby improving the reliability and durability of structures.

Heat and sound insulation: The use of CNTs in construction has the potential to improve heat and sound insulation properties. Despite encountering technical challenges, the utilization of CNTs in construction holds significant potential for creating stronger, more stable, and durable structures. Ongoing research and development efforts will enhance the technology and expand the use of CNTs in construction in the future.

References

- [1] Meena CS, Kumar A, Jain S, Rehman AU, Mishra S, Sharma NK, et al. Innovation in green building sector for sustainable future. *Energies*. 2022;15(18):6631.
- [2] Dabaieh M, Heinonen J, El-Mahdy D, Hassan DM. A comparative study of life cycle carbon emissions and embodied energy between sun-dried bricks and fired clay bricks. *Journal of Cleaner Production*. 2020;275:122998.

- [3] Razzaq A, Sharif A, Ozturk I, Skare M. Inclusive infrastructure development, green innovation, and sustainable resource management: evidence from China's trade-adjusted material footprints. *Resources Policy*. 2022;79:103076.
- [4] Jain N, Gupta E, Kanu NJ. Plethora of Carbon nanotubes applications in various fields–A state-of-the-art-review. *Smart Science*. 2022;10(1):1-24.
- [5] Gupta N, Gupta SM, Sharma SK. Carbon nanotubes: Synthesis, properties and engineering applications. *Carbon Letters*. 2019;29:419-447.
- [6] Zhang S, Hao A, Nguyen N, Oluwalowo A, Liu Z, Dessureault Y, et al. Carbon nanotube/carbon composite fiber with improved strength and electrical conductivity via interface engineering. *Carbon*. 2019;144:628-638.
- [7] Makul N. Modern sustainable cement and concrete composites: Review of current status, challenges and guidelines. *Sustainable Materials and Technologies*. 2020;25:e00155.
- [8] Kishore K, Pandey A, Wagri NK, Saxena A, Patel J, Al-Fakih A. Technological challenges in nanoparticle-modified geopolymer concrete: A comprehensive review on nanomaterial dispersion, characterization techniques and its mechanical properties. *Case Studies in Construction Materials*. 2023;e02265.
- [9] Mishra D, Yu J, Leung C. Self-sensing and Self-healing 'Smart'Cement-based Materials–A Review of the State of the Art.
- [10] Sun Z, Zhao L, Wan H, Liu H, Wu D, Wang X. Construction of polyaniline/carbon nanotubes-functionalized phase-change microcapsules for thermal management application of supercapacitors. *Chemical Engineering Journal*. 2020;396:125317.
- [11] Qin Z, Li M, Flohn J, Hu Y. Thermal management materials for energy-efficient and sustainable future buildings. *Chemical Communications*. 2021;57(92):12236-12253.
- [12] Mostafavi E, Irvani S, Varma RS, Khatami M, Rahbarizadeh F. Eco-friendly synthesis of carbon nanotubes and their cancer theranostic applications. *Materials Advances*. 2022;3(12):4765-4782.
- [13] Srinivasan V, Kunjiappan S, Palanisamy P. A brief review of carbon nanotube reinforced metal matrix composites for aerospace and defense applications. *International Nano Letters*. 2021;1-25.
- [14] Ali A, Koloor SSR, Alshehri AH, Arockiarajan A. Carbon Nanotube Characteristics and Enhancement Effects on the Mechanical Features of Polymer-based Materials and Structures–A Review. *Journal of Materials Research and Technology*. 2023.
- [15] Zhu Q, Chua MH, Ong PJ, Lee JJC, Chin KLO, Wang S, et al. Recent advances in nanotechnology-based functional coatings for the built environment. *Materials Today Advances*. 2022;15:100270.
- [16] Yang S, Bieliatynskiy A, Pershakov V, Shao M, Ta M. Asphalt concrete based on a polymer–bitumen binder nanomodified with carbon nanotubes for road and airfield construction. *Journal of Polymer Engineering*. 2022;42(5):458-466.
- [17] Mitchell S, Qin R, Zheng N, Pérez-Ramírez J. Nanoscale engineering of catalytic materials for sustainable technologies. *Nature Nanotechnology*. 2021;16(2):129-139.
- [18] Dhibar S. Unlocking the potential of molecular self-assembly: From nanotechnology to sustainable materials. *Nanostructure Studies and Applications*. 2023;1(1):2185.
- [19] Norizan MN, Moklis MH, Ngah Demon SZ, Halim NA, Samsuri A, Mohamad IS, et al. Carbon Nanotubes: Functionalisation and Their Application in Chemical Sensors. *RSC Advances*, Royal Society of Chemistry. 2020;10:43704–43732.
- [20] Garg A, Chalak HD, Belarbi MO, Zenkour AM, Sahoo R. Estimation of Carbon Nanotubes and Their Applications as Reinforcing Composite Materials–An Engineering Review. *Composite Structures*, Elsevier. 2021;272:114234.
- [21] Anzar N, Hasan R, Tyagi M, Yadav N, Narang J. Carbon Nanotube - A Review on Synthesis, Properties and Plethora of Applications in the Field of Biomedical Science. *Sensors International*. 2020;1:100003.
- [22] Fiyadh SS, AlSaadi MA, Jaafar WZ, AlOmar MK, Fayaed SS, Mohd NS, Hin LS, El-Shafie A. Review on Heavy Metal Adsorption Processes by Carbon Nanotubes. *Journal of Cleaner Production*. 2019;230:783–793.
- [23] Sajid M, Asif M, Baig N, Kabeer M, Ihsanullah I, Mohammad AW. Carbon Nanotubes-Based Adsorbents: Properties, Functionalization, Interaction Mechanisms, and Applications in Water Purification. *Journal of Water Process Engineering*. 2022;47:102815.
- [24] Zhang P, Su J, Guo J, Hu S. Influence of Carbon Nanotube on Properties of Concrete: A Review. *Construction and Building Materials*. 2023;369:130388.
- [25] Franklin AD, Hersam MC, Wong HSP. Carbon Nanotube Transistors: Making Electronics from Molecules. *Science, American Association for the Advancement of Science*. 2022;378:726–732.
- [26] Alsubaie AM, Alfaqih I, Al-Osta MA, Tounsi A, Chikh A, Mudhaffar IM, Tahir S. Porosity-Dependent Vibration Investigation of Functionally Graded Carbon Nanotube-Reinforced Composite Beam. *Computers and Concrete*. 2023;32:75–85.
- [27] Madenci E, Özkılıç YO, Hakamy A, Tounsi A. Experimental Tensile Test and Micro-Mechanic Investigation on Carbon Nanotube Reinforced Carbon Fiber Composite Beams. *Advances in Nano Research*. 2023;14:443–450.

- [28] Zhang YW, Ding HX, She GL, Tounsi A. Wave Propagation of CNTRC Beams Resting on Elastic Foundation Based on Various Higher-Order Beam Theories. *Geomechanics and Engineering*. 2023;33:381–391.
- [29] Mangalasseri Arjun Siddharth, et al. Vibration based energy harvesting performance of magneto-electro-elastic beams reinforced with carbon nanotubes. *Advances in Nano Research*. 2023;14(1):27.
- [30] Arshid E, Khorasani M, Soleimani-Javid Z, Amir S, Tounsi A. Porosity-Dependent Vibration Analysis of FG Microplates Embedded by Polymeric Nanocomposite Patches Considering Hygrothermal Effect via an Innovative Plate Theory. *Engineering with Computers*. 2022;38:4051–4072.
- [31] Huang Y, Karami B, Shahsavari D, Tounsi A. Static Stability Analysis of Carbon Nanotube Reinforced Polymeric Composite Doubly Curved Micro-Shell Panels. *Archives of Civil and Mechanical Engineering*. 2021;21:1–15.
- [32] Heidari F, Taheri K, Sheybani M, Janghorban M, Tounsi A. On the Mechanics of Nanocomposites Reinforced by Wavy/Defected/Aggregated Nanotubes. *Steel and Composite Structures*. 2021;38:533–545.
- [33] Shinde MP, Karpoomath R, Patole SP, Inamdar SN. Insights into the Formation of Multiwall Carbon Nanotubes Using Simple Flame Pyrolysis Method. *Materials Today: Proceedings*. Elsevier. 2023.
- [34] Bogdanova AR, Krasnikov DV, Khabushev EM, Ramirez B JA, Matyushkin YE, Nasibulin AG. Role of Hydrogen in Ethylene-Based Synthesis of Single-Walled Carbon Nanotubes. *Nanomaterials*. 2023;13:1504.
- [35] Tkachev AG, Zolotukhin IV. *Apparatura i Metody Sinteza Tverdotel'nykh Nanostruktur: Monografia. Mashinostroenie-1*. 2007;315.
- [36] Wei J, Yuan S, Zhang J, Zhou N, Zhang W, Li J, An W, Gao M, Fu Y. Removal Mechanism of SiC/SiC Composites by Underwater Femtosecond Laser Ablation. *Journal of the European Ceramic Society*. 2022;42:5380–5390.
- [37] Vaghri E, Khalaj Z, Dorrnanian D. Investigating the Effects of Different Liquid Environments on the Characteristics of Multilayer Graphene and Graphene Oxide Nanosheets Synthesized by Green Laser Ablation Method. *Diamond and Related Materials*. 2020;103:107697.
- [38] Hameed R, Khashan KS, Sulaiman GM. Preparation and Characterization of Graphene Sheet Prepared by Laser Ablation in Liquid. *Materials Today: Proceedings*. 2020;20:535–539.
- [39] Shoukat R, Khan MI. Carbon Nanotubes: A Review on Properties, Synthesis Methods and Applications in Micro and Nanotechnology. *Microsystem Technologies*. 2021;27:4183–4192.
- [40] Kaufmann Junior CG, Zampiva RYS, Anzanello MJ, Alves AK, Bergmann CP, Mortari SR. One-Step Synthesis of Carbon Nanoflowers by Arc Discharge in Water. *Ceramics International*. 2020;46:26229–26232.
- [41] Pak A, Ivashutenko A, Zakharova A, Vassilyeva Y. Cubic SiC Nanowire Synthesis by DC Arc Discharge under Ambient Air Conditions. *Surface and Coatings Technology*. 2020;387:125554.
- [42] Zulkimi MMM, Azis RS, Ismail I, Mokhtar N, Ertugrul M, Hamidon MN, Hasan IH, Yesilbag YO, Tuzluca FN, Ozturk G, Hasar UC. Enhancing Radar Absorption Performance of Sr-Hexaferrite by Hybridization with Coiled Carbon Nanotubes via Chemical Vapour Deposition Method. *Diamond and Related Materials*. 2023;137:110118.
- [43] Enrique Samaniego-Benítez J, García-García A, Ivette Rivera-Manrique S, Ramírez-Aparicio J. Multiwalled Carbon Nanotubes/Zeolite Composite for Dye Degradation under Sunlight. *Materials Today Communications*. 2023;35:106046.
- [44] Buranova, YS. Study of Nanotubes with Cobalt as a Filler using Transmission Electron Microscopy Methods. (In Russian). *Proceedings of the Moscow Institute of Physics and Technology*, 2011; 3(3), 30–41.
- [45] Furuse A, Stevic D, Fujisawa K, Kang CS, Hayashi T, Kaneko K. Oxidation-Aided Cap-Removal of Chemical Vapor Deposition-Prepared Single-Wall Carbon Nanotubes. *Adsorption*. 2023;29:1–7.
- [46] Wagner JB, Osman AM, Hendi A, Osman NMA. Multiwalled Carbon Nanotubes-Modified Metallic Electrode Prepared Using Chemical Vapor Deposition as Sequential Injection Analysis Detector for Determination of Ascorbic Acid. *Nanomaterials. Multidisciplinary Digital Publishing Institute*. 2023;13:1264.
- [47] Almarasy AA, Hayasaki T, Abiko Y, Kawabata Y, Akasaka S, Fujimori A. Comparison of Characteristics of Single-Walled Carbon Nanotubes Obtained by Super-Growth CVD and Improved-Arc Discharge Methods Pertaining to Interfacial Film Formation and Nanohybridization with Polymers. *Colloids and Surfaces A: Physicochemical and Engineering Aspects*. 2021;615:126221.
- [48] Say Y, Guler O, Dikici B. Carbon Nanotube (CNT) Reinforced Magnesium Matrix Composites: The Effect of CNT Ratio on Their Mechanical Properties and Corrosion Resistance. *Materials Science and Engineering: A*. 2020;798:139636.
- [49] Vaisman L, Wagner HD, Marom G. The Role of Surfactants in Dispersion of Carbon Nanotubes. *Advances in Colloid and Interface Science*. 2006;128–130:37–46.
- [50] Zhang R, Palumbo A, Kim JC, Ding J, Yang EH. Flexible Graphene-, Graphene-Oxide-, and Carbon-Nanotube-Based Supercapacitors and Batteries. *Annalen der Physik*. 2019;531:1800507.
- [51] Tran TT, Mulchandani A. Carbon Nanotubes and Graphene Nano Field-Effect Transistor-Based Biosensors. *TrAC Trends in Analytical Chemistry*. 2016;79:222–232.

- [52] Yang Z, Tian J, Yin Z, Cui C, Qian W, Wei F. Carbon Nanotube- and Graphene-Based Nanomaterials and Applications in High-Voltage Supercapacitor: A Review. *Carbon*. 2019;141:467–480.
- [53] Dong H, Zhang L, Liao Y, Huang K, Lian C, Zhou X, Zhang Z, Kauppinen EI, Wu Z-S. Floating Catalyst Chemical Vapor Deposition Patterning Nitrogen-Doped Single-Walled Carbon Nanotubes for Shape Tailorable and Flexible Micro-Supercapacitors. *Advanced Functional Materials*. 2023;33:2301103.
- [54] Abdullah HB, Ramli I, Ismail I, Yusof NA. Synthesis and Mechanism Perspectives of a Carbon Nanotube Aerogel via a Floating Catalyst Chemical Vapour Deposition Method. *Bulletin of Materials Science*. 2019;42:1–15.
- [55] Hou PX, Zhang F, Zhang L, Liu C, Cheng HM. Synthesis of Carbon Nanotubes by Floating Catalyst Chemical Vapor Deposition and Their Applications. *Advanced Functional Materials*. 2022;32:2108541.
- [56] Pavlenko V, Khosravi HS, Żółtowska S, Haruna AB, Zahid M, Mansurov Z, Supiyeva Z, Galal A, Ozoemena KI, Abbas Q, Jesionowski T. A Comprehensive Review of Template-Assisted Porous Carbons: Modern Preparation Methods and Advanced Applications. *Materials Science and Engineering: R: Reports*. 2022;149:100682.
- [57] Zuo H, Duan J, Lyu B, Lyu W, Li Y, Mei X, Liao Y. Carbon Nanotube Template-Assisted Synthesis of Conjugated Microporous Polytriphenylamine with High Porosity for Efficient Supercapacitive Energy Storage. *Macromolecular Rapid Communications*. 2023;2300238.
- [58] Kaur A, Bajaj B, Kaushik A, Saini A, Sud D. A Review on Template Assisted Synthesis of Multi-Functional Metal Oxide Nanostructures: Status and Prospects. *Materials Science and Engineering: B*. 2022;286:116005.
- [59] Qin T, Li F, Liu X, Yuan J, Jiang R, Sun Y, Zheng H, O'Mullane AP. Template-Assisted Synthesis of High-Efficiency Bifunctional Catalysts with Roller-Comb-like Nanostructure for Rechargeable Zinc-Air Batteries. *Chemical Engineering Journal*. 2022;429:132199.
- [60] Singh T, Mutreja V. Template Assisted Fabrication of Ordered Nanoporous Carbon Materials: A Review. *AIP Conference Proceedings*. 2023;2535.
- [61] Sun J, Rattanasawatesun T, Tang P, Bi Z, Pandit S, Lam L, Wasén C, Erlandsson M, Bokarewa M, Dong J, Ding F, Xiong F, Mijakovic I. Insights into the Mechanism for Vertical Graphene Growth by Plasma-Enhanced Chemical Vapor Deposition. *ACS Applied Materials and Interfaces*. 2022;14:7152–7160.
- [62] Sahoo S, Sahoo G, Jeong SM, Rout CS. A Review on Supercapacitors Based on Plasma Enhanced Chemical Vapor Deposited Vertical Graphene Arrays. *Journal of Energy Storage*. 2022;53:105212.
- [63] Xu K, Liu H, Shi YC, You JY, Ma XY, Cui HJ, Yan QB, Chen GC, Su G. Preparation of T-Carbon by Plasma Enhanced Chemical Vapor Deposition. *Carbon*. 2020;157:270–276.
- [64] Liu Y, He J, Zhang N, Zhang W, Zhou Y, Huang K. Advances of Microwave Plasma-Enhanced Chemical Vapor Deposition in Fabrication of Carbon Nanotubes: A Review. *Journal of Materials Science*. 2021;56:12559–12583.
- [65] Shrestha S, Parajuli S, Park J, Yang H, Cho TY, Eom JH, Cho SK, Lim J, Cho G, Jung Y. Improving Stability of Roll-to-Roll (R2R) Gravure-Printed Carbon Nanotube-Based Thin Film Transistors via R2R Plasma-Enhanced Chemical Vapor-Deposited Silicon Nitride. *Nanomaterials*. 2023;13:559.
- [66] Yuan G, Liu Z, Cao Z, Xie J, Li H, Li L, Sun Y, Tian Y. Direct Growth of Vertically Well-Aligned Carbon Nanotube Arrays on Atomic Layer Deposition of ZnO Films. *Chemical Physics Letters*. 2021;773:138602.
- [67] Bayram O, Igman E, Guney H, Demir Z, Yurtcan MT, Cirak C, Hasar UC, Simsek O. Graphene/Polyaniline Nanocomposite as Platinum-Free Counter Electrode Material for Dye-Sensitized Solar Cell: Its Fabrication and Photovoltaic Performance. *Journal of Materials Science: Materials in Electronics*. 2020;31:10288–10297.
- [68] Cheraghi E, Alexander LJ, Sun Y, Chen S, Yeow JTW. The Field Emission Properties of a New Design: Multi-Pixel Carbon Nanotube Field Emitters for Imaging Application. *Proceedings of the IEEE Conference on Nanotechnology*. 2019-July;572–575.
- [69] Moise CC, Mihai GV, Anicăi L, Monaico EV, Ursaki VV, Enăchescu M, Tiginyanu IM. Electrochemical Deposition of Ferromagnetic Ni Nanoparticles in InP Nanotemplates Fabricated by Anodic Etching Using Environmentally Friendly Electrolyte. *Nanomaterials*. Multidisciplinary Digital Publishing Institute. 2022;12:3787.
- [70] Sawal MH, Jalil AA, Khusnun NF, Hassan NS, Bahari MB. A Review of Recent Modification Strategies of TiO₂-Based Photoanodes for Efficient Photoelectrochemical Water Splitting Performance. *Electrochimica Acta*. 2023;467:143142.
- [71] Li X, Ming P, Ao S, Wang W. Review of Additive Electrochemical Micro-Manufacturing Technology. *International Journal of Machine Tools and Manufacture*. 2022;173:103848.
- [72] Luo H, Kaneti YV, Ai Y, Wu Y, Wei F, Fu J, Cheng J, Jing C, Yuliarto B, Eguchi M, Na J, Yamauchi Y, Liu S. Nanoarchitected Porous Conducting Polymers: From Controlled Synthesis to Advanced Applications. *Advanced Materials*. 2021;33:2007318.
- [73] Haryński Ł, Czyłkowski D, Hrycak B, Karczewski J, Gumieniak J, Kramek A, Ryl J, Grochowska K, Dors M, Siuzdak K. Nitrogen Plasma-Induced Crystallization of Anodic TiO₂ Nanotubes for Solar Photoelectrochemistry. *Applied Surface Science*. 2023;615:156472.

- [74] Eessaa AK, El-Shamy AM. Review on Fabrication, Characterization, and Applications of Porous Anodic Aluminum Oxide Films with Tunable Pore Sizes for Emerging Technologies. *Microelectronic Engineering*. 2023;279:112061.
- [75] Lv H, Pan Q, Song Y, Liu XX, Liu T. A Review on Nano-/Microstructured Materials Constructed by Electrochemical Technologies for Supercapacitors. *Nano-Micro Letters*. 2020;12:1–56.
- [76] Tian X, Wang Q, Zhao Q, Qiu L, Zhang X, Gao S. SILAR Deposition of CuO Nanosheets on the TiO₂ Nanotube Arrays for the High Performance Solar Cells and Photocatalysts. *Separation and Purification Technology*. 2019;209:368–374.
- [77] Yan Y, Xu Y, Zhao B, Xu Y, Gao Y, Chen G, Wang W, Xia B-Y. Bifunctional Nickel Ferrite-Decorated Carbon Nanotube Arrays as Free-Standing Air Electrode for Rechargeable Zn–Air Batteries. *Journal of Materials Chemistry A*. 2020;8(20):5070–5077.
- [78] Tong M.H, Chen Y.X, Lin S.W, Zhao H.P, Chen R, Jiang X, Shi H.Y, Zhu M.L, Zhou Q.Q, Lu C.Z. Synchronous Electrochemical Anodization: A Novel Strategy for Preparing Cerium Doped TiO₂ Nanotube Arrays toward Visible-Light PEC Water Splitting. *Electrochimica Acta*. 2023;463:142793.
- [79] Huang C.L, Chuah X.F, Hsieh C.T, Lu S.Y. NiFe Alloy Nanotube Arrays as Highly Efficient Bifunctional Electrocatalysts for Overall Water Splitting at High Current Densities. *ACS Applied Materials and Interfaces*. 2019;11(25):24096–24106.
- [80] Lin X, Wang Y, Zou M, Lan T, Ni Y. Electrochemical Non-Enzymatic Glucose Sensors Based on Nano-Composite of Co₃O₄ and Multiwalled Carbon Nanotube. *Chinese Chemical Letters*. 2019;30(6):1157–1160.
- [81] Fan H, Zhang X, Wang Y, Lang J, Gao R. Highly Conductive KNiF₃@carbon Nanotubes Composite Materials with Cross-Linked Structure for High Performance Supercapacitor. *Journal of Power Sources*. 2020;474:228603.
- [82] Gao P, Yin Z, Feng L, Liu Y, Du Z, Duan Z, Zhang L. Solvothermal Synthesis of Multiwall Carbon Nanotubes/BiOI Photocatalysts for the Efficient Degradation of Antipyrine under Visible Light. *Environmental Research*. 2020;185:109468.
- [83] Ye Q, Liu J, Lin L, Sun M, Wang Y, Cheng Y. Fe and P Dual-Doped Nickel Carbonate Hydroxide/Carbon Nanotube Hybrid Electrocatalysts for an Efficient Oxygen Evolution Reaction. *Nanoscale*. 2022;14(16):6648–6655.
- [84] Huo Y, Xiu S, Meng L.Y, Quan B. Solvothermal Synthesis and Applications of Micro/Nano Carbons: A Review. *Chemical Engineering Journal*. 2023;451:138572.
- [85] Danish MSS, Bhattacharya A, Stepanova D, Mikhaylov A, Grilli ML, Khosravy M, Senjyu T. A Systematic Review of Metal Oxide Applications for Energy and Environmental Sustainability. *Metals*. 2020;10(12):1604.
- [86] Kumar Y, Paswan KK, Nayan K, Pandurangappa G, Dwivedi D, Sangwai JS. Introduction to Functional Materials Synthesis, Properties, Environmental Sustainability, and General Applications. In: *Functional Materials for the Oil and Gas Industry: Characterization and Applications*. CRC Press; 2023. p. 1–22.
- [87] Ndilwana L, Raleie N, Dimpe KM, Ogutu HF, Oseghe EO, Motsa MM, Msagati TAM, Mamba BB. Sustainable Hydrothermal and Solvothermal Synthesis of Advanced Carbon Materials in Multidimensional Applications: A Review. *Materials*. 2021;14(18):5094.
- [88] Siwal SS, Kaur H, Saini AK, Thakur VK. Recent Progress in Carbon Dots-Based Materials for Electrochemical Energy Storage Toward Environmental Sustainability. *Advanced Energy and Sustainability Research*. 2022;3:2200062.
- [89] Fuku X, Dyosiba X, Iftikhar FJ. Green Prepared Nanomaterials from Various Biodegradable Wastes and Their Application in Energy. *Nano-Structures & Nano-Objects*. 2023;35:100997.
- [90] Xia W, Lau SK, Yong WF. Comparative Life Cycle Assessment on Zeolitic Imidazolate Framework-8 (ZIF-8) Production for CO₂ Capture. *Journal of Cleaner Production*. 2022;370:133354.
- [91] Mruthunjayappa MH, Kotrappanavar NS, Mondal D. New Prospects on Solvothermal Carbonisation Assisted by Organic Solvents, Ionic Liquids and Eutectic Mixtures – A Critical Review. *Progress in Materials Science*. 2022;126:100932.
- [92] Li W, Qian K, Yang Z, Ding X, Tian W, Chen D. Promotion Effect of Cobalt Doping on Microwave-Initiated Plastic Deconstruction for Hydrogen Production over Iron Catalysts. *Applied Catalysis B: Environmental*. 2023;327:122451.
- [93] Burkholder MB, Rahman FBA, Chandler EH, Regalbuto JR, Gupton BF, Tengco JMM. Metal Supported Graphene Catalysis: A Review on the Benefits of Nanoparticle Supported Specialty Sp² Carbon Catalysts on Enhancing the Activities of Multiple Chemical Transformations. *Carbon Trends*. 2022;9:100196.
- [94] Jiang M, Wang X, Xi W, Zhou H, Yang P, Yao J, Jiang X, Wu D. Upcycling Plastic Waste to Carbon Materials for Electrochemical Energy Storage and Conversion. *Chemical Engineering Journal*. 2023;461:141962.
- [95] Li X, Srinivas K, Ramadoss M, Ma F, Wang Y, Wang M, Yu H, Zhang Z, Wu Y, Chen Y. Carbon Nanotubes Supported Cs-Doped NiFe-Layered Double Hydroxide Nanosheets as Efficient Catalyst for Oxygen Evolution Reaction. *International Journal of Hydrogen Energy*.

- [96] Feng Y, Zeng A. Selective Liquid-Phase Oxidation of Toluene with Molecular Oxygen Catalyzed by Mn3O4 Nanoparticles Immobilized on CNTs under Solvent-Free Conditions. *Catalysts*. 2020;10(6):623.
- [97] Lim XX, Low SC, Oh W Da. A Critical Review of Heterogeneous Catalyst Design for Carbon Nanotubes Synthesis: Functionalities, Performances, and Prospects. *Fuel Processing Technology*. 2023;241:107624.
- [98] Boyrazlı M, Güler SH. Synthesis of Carbon Nanostructures from Corn Stalk Using Mechano-Thermal Method. *Journal of Molecular Structure*. 2020;1199:126976.
- [99] Alirezazadeh F, Alimohammadi E, Sheibani S, Rashchi F. A Comparative Study on the Photocatalytic Activity and Formation Mechanism of Nanostructured Cu2ZnSnS4 Prepared by Thermal and Mechano-Thermal Methods. *Materials Chemistry and Physics*. 2022;292:126856.
- [100] Tubtimkuna S, Danilov DL, Sawangphruk M, Notten PHL. Review of the Scalable Core-Shell Synthesis Methods: The Improvements of Li-Ion Battery Electrochemistry and Cycling Stability. *Small Methods*. 2023;7(2):2300345.
- [101] Maselugbo AO, Harrison HB, Alston JR. Boron Nitride Nanotubes: A Review of Recent Progress on Purification Methods and Techniques. *Journal of Materials Research*. 2022;37(24):4438–4458.
- [102] Al-Diabat AM, Algadri NA, Ahmad NM, Alrajhi AH, Abuelsamen A, Mohamed A, Ali A, Abdulrhman Al-Wasli S. Optimize the Properties of Carbon Nanotubes Synthesized Using a Microwave Oven.
- [103] Pund SN, Nagwade PA, Nagawade AV, Thopate SR, Bagade AV. Preparation Techniques for Zinc Ferrites and Their Applications: A Review. *Materials Today: Proceedings*. 2022;60:2194–2208.
- [104] Li X, Liu J, Zhu H. Functionalized and Environment-Friendly Carbon Materials for Flexible and Wearable Electronic Devices. In: *SPIE*. 2022;12164:162–174.
- [105] Mirabootalebi SO, Akbari GH, Babaheydari RM. Mass Production and Growth Mechanism of Carbon Nanotubes in Optimized Mechanochemical Method. *International Journal of Engineering, Materials and Energy Research Center*. 2021;34:2332–2340.
- [106] Rathinavel S, Priyadarshini K, Panda D. A Review on Carbon Nanotube: An Overview of Synthesis, Properties, Functionalization, Characterization, and the Application. *Materials Science and Engineering: B*. 2021;268:115095.
- [107] Zainal MT, Mohd Yasin MF, Wan Ali WFF, Tamrin KF, Ani MH. Carbon Precursor Analysis for Catalytic Growth of Carbon Nanotube in Flame Synthesis Based on Semi-Empirical Approach. *Carbon Letters*. 2020;30(6):569–579.
- [108] Hu X, Zuo D, Cheng S, Chen S, Liu Y, Bao W, Deng S, Harris SJ, Wan J. Ultrafast Materials Synthesis and Manufacturing Techniques for Emerging Energy and Environmental Applications. *Chemical Society Reviews*. 2023;52:1103–1128.
- [109] Amouzegar Z, Mollarasouli F, Asadi S, Fathi A, Ahmadi M, Afkhami A, Madrakian T. Nonconventional Applications of Nebulizers: Nanomaterials Synthesis. In: *Analytical Nebulizers: Fundamentals and Applications*. 2023;217–245.
- [110] Zhao Y, Dong S, Hu P, Zhao X, Hong C. Recent Progress in Synthesis, Growth Mechanisms, Properties, and Applications of Silicon Nitride Nanowires. *Ceramics International*. 2021;47(11):14944–14965.
- [111] Peters AB, Zhang D, Chen S, Ott C, Oses C, Curtarolo S, McCue I, Pollock T, Prameela SE. Materials Design for Hypersonics.
- [112] Xue J, Yin X, Cheng L. Induced Crystallization Behavior and EMW Absorption Properties of CVI SiCN Ceramics Modified with Carbon Nanowires. *Chemical Engineering Journal*. 2019;378:122213.
- [113] Natarajan B. Processing-Structure-Mechanical Property Relationships in Direct Formed Carbon Nanotube Articles and Their Composites: A Review. *Composites Science and Technology*. 2022;225:109501.
- [114] Li M, Song Y, Zhang C, Yong Z, Qiao J, Hu D, Zhang Z, Wei H, Di J, Li Q. Robust Carbon Nanotube Composite Fibers: Strong Resistivities to Protonation, Oxidation, and Ultrasonication. *Carbon*. 2019;146:627–635.
- [115] Aly K, Lubna M, Bradford PD. Low Density, Three-Dimensionally Interconnected Carbon Nanotube/Silicon Carbide Nanocomposites for Thermal Protection Applications. *Journal of the European Ceramic Society*. 2021;41:233–243.
- [116] Feng L, Fu Q, Song Q, Yang Y, Zuo Y, Suo G, Hou X, Zhang L, Ye X. A Novel Continuous Carbon Nanotube Fiber/Carbon Composite by Electrified Preform Heating Chemical Vapor Infiltration. *Carbon*. 2020;157:640–648.
- [117] Liu X, Licht G, Wang X, Licht S. Controlled Transition Metal Nucleated Growth of Carbon Nanotubes by Molten Electrolysis of CO2. *Catalysts*. 2022;12:137.
- [118] Arcaro S, Guaglianoni W, Alves AK, Bergmann CP. The Effect of CaCO3 in the Formation of Carbon Nanotubes via Electrolysis of Molten Li2CO3/CaCO3 Mixtures. *International Journal of Applied Ceramic Technology*. 2022;19(2):451–458.
- [119] Zailan Z, Tahir M, Jusoh M, Zakaria ZY. A Review of Sulfonic Group Bearing Porous Carbon Catalyst for Biodiesel Production. *Renewable Energy*. 2021;175:430–452.
- [120] Atiq Ur Rehman M, Chen Q, Braem A, Shaffer MSP, Boccaccini AR. Electrophoretic Deposition of Carbon Nanotubes: Recent Progress and Remaining Challenges. *International Materials Reviews*. 2021;66:533–562.

- [121] Liu X, Ren J, Licht G, Wang X, Licht S. Carbon Nano-Onions Made Directly from CO₂ by Molten Electrolysis for Greenhouse Gas Mitigation. *Advanced Sustainable Systems*. 2019;3:1900056.
- [122] Wang X, Licht G, Liu X, Licht S. CO₂ Utilization by Electrolytic Splitting to Carbon Nanotubes in Non-Lithiated, Cost-Effective, Molten Carbonate Electrolytes. *Advanced Sustainable Systems*. 2022;6:2100481.
- [123] Liu X, Licht G, Wang X, Licht S. Controlled Transition Metal Nucleated Growth of Carbon Nanotubes by Molten Electrolysis of CO₂.
- [124] Zahid MU, Pervaiz E, Hussain A, Shahzad MI, Niazi MBK. Synthesis of Carbon Nanomaterials from Different Pyrolysis Techniques: A Review. *Materials Research Express*. 2018;5:052002.
- [125] Vivekchand SRC, Cele LM, Deepak FL, Raju AR, Govindaraj A. Carbon Nanotubes by Nebulized Spray Pyrolysis. *Chemical Physics Letters*. 2004;386:313–318.
- [126] Jin YZ, Gao C, Hsu WK, Zhu Y, Huczko A, Bystrzejewski M, Roe M, Lee CY, Acquah S, Kroto H, Walton DRM. Large-Scale Synthesis and Characterization of Carbon Spheres Prepared by Direct Pyrolysis of Hydrocarbons. *Carbon*. 2005;43:1944–1953.
- [127] Cheng HM, Li F, Su G, Pan HY, He LL, Sun X, Dresselhaus MS. Large-Scale and Low-Cost Synthesis of Single-Walled Carbon Nanotubes by the Catalytic Pyrolysis of Hydrocarbons. *Applied Physics Letters*. 1998;72:3282–3284.
- [128] Lv X, Zhang T, Luo Y, Zhang Y, Wang Y, Zhang G. Study on Carbon Nanotubes and Activated Carbon Hybrids by Pyrolysis of Coal. *Journal of Analytical and Applied Pyrolysis*. 2020;146:104717.
- [129] Moothi K, Simate GS, Falcon R, Iyuke SE, Meyyappan M. Carbon Nanotube Synthesis Using Coal Pyrolysis. *Langmuir*. 2015;31:9464–9472.
- [130] Nebol'sin VA, Vorob'ev AY. Role of Surface Energy in the Growth of Carbon Nanotubes via Catalytic Pyrolysis of Hydrocarbons. *Inorganic Materials*. 2011;47:128–132.
- [131] Sárközi S, Sárközi Z, Kertész K, Koós AA, Osváth Z, Tapasztó L, Horváth ZE, Nemes-Incze P, Jenei IZ, Vértessy Z, Daróczy NS, Darabont A, Pana O, Biró LP. Synthesis of Carbon Nanotubes from Liquid Hydrocarbons Using a Spray-Pyrolysis Method. *Journal of Optoelectronics and Advanced Materials*. 2008;10:2307–2310.
- [132] Bajad GS, Vijayakumar RP, Gupta AG, Jagtap V, Singh YP. Production of Liquid Hydrocarbons, Carbon Nanotubes and Hydrogen Rich Gases from Waste Plastic in a Multi-Core Reactor. *Journal of Analytical and Applied Pyrolysis*. 2017;125:83–90.
- [133] Mehrabi M, Parvin P, Reyhani A, Mortazavi SZ. Hydrogen Storage in Multi-Walled Carbon Nanotubes Decorated with Palladium Nanoparticles Using Laser Ablation/Chemical Reduction Methods. *Materials Research Express*. 2017;4:095030.
- [134] Tarasenko N, Stupak A, Tarasenko N, Chakrabarti S, Mariotti D. Structure and Optical Properties of Carbon Nanoparticles Generated by Laser Treatment of Graphite in Liquids. *ChemPhysChem*. 2017;18:1074–1083.
- [135] Irimiciuc SA, Hodoroba BC, Bulai G, Gurlui S, Craciun V. Multiple Structure Formation and Molecule Dynamics in Transient Plasmas Generated by Laser Ablation of Graphite. *Spectrochimica Acta Part B: Atomic Spectroscopy*. 2020;165:105774.
- [136] Rode A, Sharma S, Mishra DK. Carbon Nanotubes: Classification, Method of Preparation and Pharmaceutical Application. *Current Drug Delivery*. 2017;15:620–629.
- [137] Shoukat R, Khan MI. Carbon Nanotubes: A Review on Properties, Synthesis Methods and Applications in Micro and Nanotechnology. *Microsystem Technologies*. 2021;27:4183–4192.
- [138] Ismail RA, Mohsin MH, Ali AK, Hassoon KI, Erten-Ela S. Preparation and Characterization of Carbon Nanotubes by Pulsed Laser Ablation in Water for Optoelectronic Application. *Physica E: Low-dimensional Systems and Nanostructures*. 2020;119:113997.
- [139] Gulati S, Kumar S, Mongia A, Diwan A, Singh P. Functionalized Carbon Nanotubes (FCNTs) as Novel Drug Delivery Systems: Emergent Perspectives from Applications. *Environmental Applications of Carbon Nanomaterials-Based Devices*. 2021;283–312.
- [140] Omoriyekomwan JE, Tahmasebi A, Dou J, Wang R, Yu J. A Review on the Recent Advances in the Production of Carbon Nanotubes and Carbon Nanofibers via Microwave-Assisted Pyrolysis of Biomass. *Fuel Processing Technology*. 2021;214:106686.
- [141] Li A, Zhou W, Xie M, Wang S, Wang S, Yang Y, Chen Y, Liu M. Preparation and Arc Erosion Behavior of AgNi10 Contact Material with Different Allotropes of Carbon Addition. *Diamond and Related Materials*. 2021;111:108141.
- [142] Shweta, Vishwakarma K, Sharma S, Narayan RP, Srivastava P, Khan AS, Dubey NK, Tripathi DK, Chauhan DK. Plants and Carbon Nanotubes (CNTs) Interface: Present Status and Future Prospects. *Nanotechnology: Food and Environmental Paradigm*. 2017;317–340.
- [143] Janett B, Gutierrez A, Dul S, Pegoretti A, Alvarez-Quintana J, Fambri L. Investigation of the Effects of Multi-Wall and Single-Wall Carbon Nanotubes Concentration on the Properties of ABS Nanocomposites. *C* 2021. 7:33.

- [144] Liu F, Wang Q, Tang Y, Du W, Chang W, Fu Z, Zhao X, Liu Y. Carbon Nanowires Made by the Insertion-and-Fusion Method toward Carbon-Hydrogen Nanoelectronics. *Nanoscale*. 2023;15:6143–6155.
- [145] Loayza CR, Cardoso DCS, Borges DJA, Castro AAF, Bozzi AC, Dos Reis MAL, Braga EM. Stainless Steel-CNT Composite Manufactured via Electric Arc Welding. *Materials & Design*. 2022;223:111169.
- [146] Jia Q, Zhou Y, Li X, Lindsay L, Shi L. Differential Multi-Probe Thermal Transport Measurements of Multi-Walled Carbon Nanotubes Grown by Chemical Vapor Deposition. *International Journal of Heat and Mass Transfer*. 2023;216:124535.
- [147] Rajab F. Effect of the Chemical Vapor Deposition Process on the Aspect Ratio of Vertically Aligned Carbon Nanotubes (VACNTs). *CMR Advances*. 2023;8:343–348.
- [148] Wang C, Wang Y, Jiang H. Continuous Growth of Carbon Nanotubes on Carbon Fiber Surface by Chemical Vapor Deposition Catalyzed by Cobalt with Thiourea. *ECS Journal of Solid State Science and Technology*. 2023;12:041003.
- [149] Zulkimi MMM, Azis RSR, Ismail I, Mokhtar N, Ertugrul M, Hamidon MN, Hasan IH, Yesilbag YO, Tuzluca FN, Ozturk G, Hasar UC. Enhancing Radar Absorption Performance of Sr-Hexaferrite by Hybridization with Coiled Carbon Nanotubes via Chemical Vapour Deposition Method. *Diamond and Related Materials*. 2023;137:110118.
- [150] Cheng F, Xu Y, Zhang J, Wang L, Zhang H, Wan Q, Xu S, Li W, Wang L, Huang Z. A Novel Flexible Carbon Fiber with Carbon Nanotubes Growing In-Situ via Chemical Vapor Deposition to Impregnate Paraffin for Thermal Energy Application. *Journal of Energy Storage*. 2023;68:107718.
- [151] Cheng F, Xu Y, Zhang J, Wang L, Zhang H, Wan Q, Li W, Wang L, Lv Z. Growing Carbon Nanotubes In-Situ via Chemical Vapor Deposition and Resin Pre-Coating Treatment on Anodized Ti-6Al-4V Titanium Substrates for Stronger Adhesive Bonding with Carbon Fiber Composites. *Surface and Coatings Technology*. 2023;457:129296.
- [152] ZHAO H, TU N, ZHANG W, ZHANG M, WANG J. Novel Synthesis of Silicon/Carbon Nanotubes Microspheres as Anode Additives through Chemical Vapor Deposition in Fluidized Bed Reactors. *Scripta Materialia*. 2021;192:49–54.
- [153] Zhang Y, Wang Q, Ramachandran CS. Synthesis of Carbon Nanotube Reinforced Aluminum Composite Powder (CNT-Al) by Polymer Pyrolysis Chemical Vapor Deposition (PP-CVD) Coupled High Energy Ball Milling (HEBM) Process. *Diamond and Related Materials*. 2020;104:107748.
- [154] Mittal G, Rhee KY. Chemical Vapor Deposition-Based Grafting of CNTs onto Basalt Fabric and Their Reinforcement in Epoxy-Based Composites. *Composites Science and Technology*. 2018;165:84–94.
- [155] Nekoueian K. Modification of Carbon-Based Electrodes Using Metal Nanostructures: Application to Voltammetric Determination of Some Pharmaceutical and Biological Compounds. *Lappeenranta-Lahti University of Technology LUT*.
- [156] Nie C, Ma L, Li S, Fan X, Yang Y, Cheng C, Zhao W, Zhao C. Recent Progresses in Graphene Based Bio-Functional Nanostructures for Advanced Biological and Cellular Interfaces. *Nano Today*. 2019;26:57–97.
- [157] Senthilkumar E, Shanmugharaj AM, Suresh Babu R, Sivagaami Sundari G, Thileep Kumar K, Raghu S, Kalaivani R. Development of Constructed Nanoporous Graphene-Modified Electrode for Electrical Detection of Folic Acid. *Journal of Materials Science: Materials in Electronics*. 2019;30:13488–13496.
- [158] Guo HW, Hu Z, Liu ZB, Tian JG. Stacking of 2D Materials. *Advanced Functional Materials*. 2021;31:2007810.
- [159] Bagyalakshmi S, Sivakami A, Pal K, Sarankumar R, Mahendran C. Manufacturing of Electrochemical Sensors via Carbon Nanomaterials Novel Applications: A Systematic Review. *Journal of Nanoparticle Research*. 2022;24:1–28.
- [160] Sharma VV, Gualandi I, Vlamidis Y, Tonelli D. Electrochemical Behavior of Reduced Graphene Oxide and Multi-Walled Carbon Nanotubes Composites for Catechol and Dopamine Oxidation. *Electrochimica Acta*. 2017;246:415–423.
- [161] Khoshnevis H, Tran TQ, Mint SM, Zadhoush A, Duong HM, Youssefi M. Effect of Alignment and Packing Density on the Stress Relaxation Process of Carbon Nanotube Fibers Spun from Floating Catalyst Chemical Vapor Deposition Method. *Colloids and Surfaces A: Physicochemical and Engineering Aspects*. Elsevier; 2018;558:570–578.
- [162] Dong L, Park JG, Leonhardt BE, Zhang S, Liang R. Continuous Synthesis of Double-Walled Carbon Nanotubes with Water-Assisted Floating Catalyst Chemical Vapor Deposition. *Nanomaterials*. Multidisciplinary Digital Publishing Institute; 2020;10:365.
- [163] Lee SH, Park J, Park JH, Lee DM, Lee A, Moon SY, Lee SY, Jeong HS, Kim SM. Deep-Injection Floating-Catalyst Chemical Vapor Deposition to Continuously Synthesize Carbon Nanotubes with High Aspect Ratio and High Crystallinity. *Carbon*. Pergamon; 2021;173:901–909.
- [164] Ahmad S, Liao Y, Hussain A, Zhang Q, Ding EX, Jiang H, Kauppinen EI. Systematic Investigation of the Catalyst Composition Effects on Single-Walled Carbon Nanotubes Synthesis in Floating-Catalyst CVD. *Carbon*. Pergamon; 2019;149:318–327.
- [165] Zhang Q, Wei N, Laiho P, Esko A, Kauppinen I. Recent Developments in Single-Walled Carbon Nanotube Thin Films Fabricated by Dry Floating Catalyst Chemical Vapor Deposition.

- [166] Duong HM, Tran TQ, Kopp R, Myint SM, Peng L. Direct Spinning of Horizontally Aligned Carbon Nanotube Fibers and Films From the Floating Catalyst Method. *Nanotube Superfiber Materials: Science, Manufacturing, Commercialization*. William Andrew Publishing; 2019;3–29.
- [167] Khoshnevis H, Mint SM, Yedinak E, Tran TQ, Zadhoush A, Youssefi M, Pasquali M, Duong HM. Super High-Rate Fabrication of High-Purity Carbon Nanotube Aerogels from Floating Catalyst Method for Oil Spill Cleaning. *Chemical Physics Letters*. North-Holland; 2018;693:146–151.
- [168] Tran TQ, Headrick RJ, Bengio EA, Myo Myint S, Khoshnevis H, Jamali V, Duong HM, Pasquali M. Purification and Dissolution of Carbon Nanotube Fibers Spun from the Floating Catalyst Method. *ACS Applied Materials and Interfaces*. American Chemical Society; 2017;9:37112–37119.
- [169] Suchitra SM, Udayashankar NK. Influence of Porewidening Duration on the Template Assisted Growth of Graphitic Carbon Nitride Nanostructures. *Materials Research Express*. IOP Publishing; 2018;5:015056.
- [170] Han M, Zhang X, Gao H, Chen S, Cheng P, Wang P, Zhao Z, Dang R, Wang G. In Situ Semi-Sacrificial Template-Assisted Growth of Ultrathin Metal–Organic Framework Nanosheets for Electrocatalytic Oxygen Evolution. *Chemical Engineering Journal*. Elsevier; 2021;426:131348.
- [171] Cossuet T, Rapenne L, Renou G, Appert E, Consonni V. Template-Assisted Growth of Open-Ended TiO₂ Nanotubes with Hexagonal Shape Using Atomic Layer Deposition. *Crystal Growth and Design*. American Chemical Society; 2021;21:125–132.
- [172] Li H, Liu YL, Jin H, Cao L, Yang H, Jiang S, He S, Li S, Liu K, Duan G. Bimetallic Salts Template-Assisted Strategy towards the Preparation of Hierarchical Porous Polyimide-Derived Carbon Electrode for Supercapacitor. *Diamond and Related Materials*. Elsevier; 2022;128:109283.
- [173] Wang C, Yan B, Zheng J, Feng L, Chen Z, Zhang Q, Liao T, Chen J, Jiang S, Du C, He S. Recent Progress in Template-Assisted Synthesis of Porous Carbons for Supercapacitors. *Advanced Powder Materials*. Elsevier; 2022;1:100018.
- [174] Taziwa R, Meyer E, Takata N. Structural and Raman Spectroscopic Characterization of C-TiO₂ Nanotubes Synthesized by a Template-Assisted Sol-Gel Technique. *Journal of Nanoscience & Nanotechnology Research*. 2017;1.
- [175] Yang G, Cheng F, Zuo S, Zhang J, Xu Y, Hu Y, Hu X. Growing Carbon Nanotubes In Situ Surrounding Carbon Fiber Surface via Chemical Vapor Deposition to Reinforce Flexural Strength of Carbon Fiber Composites. *Polymers*. Multidisciplinary Digital Publishing Institute; 2023;15:2309.
- [176] Simionescu OG, Brîncoveanu O, Romanițan C, Vulpe S, Avram A. Step-By-Step Development of Vertically Aligned Carbon Nanotubes by Plasma-Enhanced Chemical Vapor Deposition. *Coatings*. Multidisciplinary Digital Publishing Institute; 2022;12:943.
- [177] Yi K, Liu D, Chen X, Yang J, Wei D, Liu Y, Wei D. Plasma-Enhanced Chemical Vapor Deposition of Two-Dimensional Materials for Applications. *Accounts of Chemical Research*. American Chemical Society; 2021;54:1011–1022.
- [178] Yeh NC, Hsu CC, Bagley J, Tseng WS. Single-Step Growth of Graphene and Graphene-Based Nanostructures by Plasma-Enhanced Chemical Vapor Deposition. *Nanotechnology*. IOP Publishing; 2019;30:162001.
- [179] Thapa A, Neupane S, Guo R, Jungjohann KL, Pete D, Li W. Direct Growth of Vertically Aligned Carbon Nanotubes on Stainless Steel by Plasma Enhanced Chemical Vapor Deposition. *Diamond and Related Materials*. Elsevier; 2018;90:144–153.
- [180] Jabbar A, Yasin G, Khan WQ, Anwar MY, Korai RM, Nizam MN, Muhyodin G. Electrochemical Deposition of Nickel Graphene Composite Coatings: Effect of Deposition Temperature on Its Surface Morphology and Corrosion Resistance. *RSC Advances*. Royal Society of Chemistry; 2017;7:31100–31109.
- [181] Liu L, Mandler D. Using Nanomaterials as Building Blocks for Electrochemical Deposition: A Mini Review. *Electrochemistry Communications*. Elsevier; 2020;120:106830.
- [182] Hussain S, Erikson H, Kongi N, Merisalu M, Rähn M, Sammelselg V, Maia G, Tammeveski K. Platinum Particles Electrochemically Deposited on Multiwalled Carbon Nanotubes for Oxygen Reduction Reaction in Acid Media. *Journal of The Electrochemical Society*. The Electrochemical Society; 2017;164:F1014–F1021.
- [183] Arai S. Fabrication of Metal/Carbon Nanotube Composites by Electrochemical Deposition. *Electrochem*. Multidisciplinary Digital Publishing Institute; 2021;2:563–589.
- [184] Zhao G, Liu G. Electrochemical Deposition of Gold Nanoparticles on Reduced Graphene Oxide by Fast Scan Cyclic Voltammetry for the Sensitive Determination of As(III). *Nanomaterials*. Multidisciplinary Digital Publishing Institute; 2019;9:41.
- [185] Iffelsberger C, Ng S, Pumera M. Catalyst Coating of 3D Printed Structures via Electrochemical Deposition: Case of the Transition Metal Chalcogenide MoS_x for Hydrogen Evolution Reaction. *Applied Materials Today*. Elsevier; 2020;20:100654.
- [186] Cao Y, Moniri Javadhesari S, Mohammadnejad S, Khodadustan E, Raise A, Akbarpour MR. Microstructural Characterization and Antibacterial Activity of Carbon Nanotube Decorated with Cu Nanoparticles Synthesized by a Novel Solvothermal Method. *Ceramics International*. Elsevier; 2021;47:25729–25737.

- [187] Park SK, Sure J, Sri Maha Vishnu D, Jo SJ, Lee WC, Ahmad IA, Kim HK. Nano-Fe₃O₄/Carbon Nanotubes Composites by One-Pot Microwave Solvothermal Method for Supercapacitor Applications. *Energies*. MDPI AG; 2021;14:NA.
- [188] Wang Q, Li H, Yu X, Jia Y, Chang Y, Gao S. Morphology Regulated Bi₂WO₆ Nanoparticles on TiO₂ Nanotubes by Solvothermal Sb³⁺ Doping as Effective Photocatalysts for Wastewater Treatment. *Electrochimica Acta*. Pergamon; 2020;330:135167.
- [189] Liu X, Li G, Qian P, Zhang D, Wu J, Li K, Li L. Carbon Coated Li₃VO₄ Microsphere: Ultrafast Solvothermal Synthesis and Excellent Performance as Lithium-Ion Battery Anode. *Journal of Power Sources*. Elsevier; 2021;493:229680.
- [190] Gyulai G, Ouanzi F, Bertóti I, Mohai M, Kolonits T, Horváti K, Bószé S. Chemical Structure and in Vitro Cellular Uptake of Luminescent Carbon Quantum Dots Prepared by Solvothermal and Microwave Assisted Techniques. *Journal of Colloid and Interface Science*. Academic Press; 2019;549:150–161.
- [191] Zhao D, Liu X, Wei C, Qu Y, Xiao X, Cheng H. One-Step Synthesis of Red-Emitting Carbon Dots via a Solvothermal Method and Its Application in the Detection of Methylene Blue. *RSC Advances*. Royal Society of Chemistry; 2019;9:29533–29540.
- [192] Cao D, Wang Q, Wu Y, Zhu S, Jia Y, Wang R. Solvothermal Synthesis and Enhanced Photocatalytic Hydrogen Production of Bi/Bi₂MoO₆ Co-Sensitized TiO₂ Nanotube Arrays. *Separation and Purification Technology*. Elsevier; 2020;250:117132.
- [193] Al-Sakkaf MK, Basfer I, Iddrisu M, Bahadi SA, Nasser MS, Abussaud B, Drmosh QA, Onaizi SA. An Up-to-Date Review on the Remediation of Dyes and Phenolic Compounds from Wastewaters Using Enzymes Immobilized on Emerging and Nanostructured Materials: Promises and Challenges. *Nanomaterials*. Multidisciplinary Digital Publishing Institute; 2023;13:2152.
- [194] Dang Q, Lin H, Fan Z, Ma L, Shao Q, Ji Y, Zheng F, Geng S, Yang SZ, Kong N, Zhu W, Li Y, Liao F, Huang X, Shao M. Iridium Metallene Oxide for Acidic Oxygen Evolution Catalysis. *Nature Communications* 2021 12:1. Nature Publishing Group; 2021;12:1–10.
- [195] Reza MS, Afroze S, Kuterbekov K, Kabyshev A, Zh. Bekmyrza K, Haque MN, Islam SN, Hossain MA, Hassan M, Roy H, Islam MS, Pervez MN, Azad AK. Advanced Applications of Carbonaceous Materials in Sustainable Water Treatment, Energy Storage, and CO₂ Capture: A Comprehensive Review. *Sustainability* (Switzerland). MDPI; 2023;15:8815.
- [196] Nigam A, Kala S. Structural and Bioactive Properties of Iron Sulfide Nanoparticles Synthesized by Green-Route. *Materials Today: Proceedings*. Elsevier; 2022;66:2144–2151.
- [197] Patiño-Carachure C, Martínez-Vargas S, Flores-Chan JE, Rosas G. Synthesis of Carbon Nanostructures by Graphite Deformation during Mechanical Milling in Air. *Fullerenes, Nanotubes and Carbon Nanostructures*. Taylor & Francis; 2020;28:869–876.
- [198] Kumar S, Kumar Mahto R. Synthesis and Characterization of Low Dimensional Structure of Carbon Nanotubes. *International Journal of Science and Research Archive*. 2022;2022:571–582.
- [199] Lekshmi GS, Tamilselvi R, Prasad K, Bazaka O, Levchenko I, Bazaka K, Mohandas M. Growth of RGO Nanostructures via Facile Wick and Oil Flame Synthesis for Environmental Remediation. *Carbon Letters*. Springer; 2021;31:763–777.
- [200] Chang BP, Gupta A, Mekonnen TH. Flame Synthesis of Carbon Nanoparticles from Corn Oil as a Highly Effective Cationic Dye Adsorbent. *Chemosphere*. Pergamon; 2021;282:131062.
- [201] Wong HY, How HC, Ho JH. Chemical Kinetics Modelling for the Effect of Chimney on Diffusion Flame in Carbon Nanotubes Synthesis. *J Phys Conf Ser*. IOP Publishing. 2022;2169:012022.
- [202] Hammadi AH, Jasim AM, Abdulrazzak FH, Al-Sammarraie AMA, Cherifi Y, Boukherroub R, Hussein FH. Purification for Carbon Nanotubes Synthesized by Flame Fragments Deposition via Hydrogen Peroxide and Acetone. *Materials*. Multidisciplinary Digital Publishing Institute. 2020;13:2342.
- [203] Yang L, Yang J, Dong Q, Zhou F, Wang Q, Wang Z, Huang K, Yu H, Xiong X. One-Step Synthesis of CuO Nanoparticles Based on Flame Synthesis: As a Highly Effective Non-Enzymatic Sensor for Glucose, Hydrogen Peroxide and Formaldehyde. *J Electroanal Chem*. Elsevier. 2021;881:114965.
- [204] Hong H, Memon NK, Dong Z, Kear BH, Tse SD. Flame Synthesis of Gamma-Iron-Oxide (γ-Fe₂O₃) Nanocrystal Films and Carbon Nanotubes on Stainless-Steel Substrates. *Proc Combust Inst*. Elsevier. 2019;37:1249–1256.
- [205] Hamzah N, Yasin MFM, Yusop MZM, Zainal MT, Rosli MAF. Identification of Cnt Growth Region and Optimum Time for Catalyst Oxidation: Experimental and Modelling Studies of Flame Synthesis. *Evergreen, Novel Carbon Resource Sci*. 2019;6:85–91.
- [206] Zhan W, Ma L, Gan M, Ding J, Han S, Wei D, Shen J, Zhou C. MOF-Derived N-Doped Carbon Coated CoP/Carbon Nanotube Pt-Based Catalyst for Efficient Methanol Oxidation. *Int J Hydrogen Energy*. Pergamon. 2020;45:15630–15641.
- [207] Keteklahijani YZ, Arjmand M, Sundararaj U. Cobalt Catalyst Grown Carbon Nanotube/Poly(Vinylidene Fluoride) Nanocomposites: Effect of Synthesis Temperature on Morphology, Electrical Conductivity and Electromagnetic Interference Shielding. *ChemistrySelect*. John Wiley & Sons, Ltd. 2017;2:10271–10284.

- [208] Maruyama T, Kozawa A, Saida T, Naritsuka S, Iijima S. Low Temperature Growth of Single-Walled Carbon Nanotubes from Rh Catalysts. *Carbon*. Pergamon. 2017;116:128–132.
- [209] Sun X, Damma D, Cao Z, Alvarez NT, Shanov V, Arvanitis A, Smirniotis PG, Dong J. CO-Promoted Low-Temperature Conversion of CH₄ to Hydrogen and Carbon Nanotubes on Nanocrystalline Cr-Doped Ferrite Catalyst. *Catal Commun*. Elsevier. 2022;169:106475.
- [210] Mamat MS, Walker GS, Grant DM, Yaakob Y, Shaharun NA. Effect of the Reaction Temperature and Ethene/Hydrogen Composition on the Nanostructured Carbon Produced by CVD Using Supported NiFe₂O₄ as a Catalyst. *Results Phys*. Elsevier. 2020;19:103497.
- [211] Moon SY, Kim BR, Park CW, Lee SH, Kim SM. High-Crystallinity Single-Walled Carbon Nanotube Aerogel Growth: Understanding the Real-Time Catalytic Decomposition Reaction through Floating Catalyst Chemical Vapor Deposition. *Chem Eng J Adv*. Elsevier. 2022;10:100261.
- [212] Kadlečková M, Breza J, Jesenák K, Hubeňák M, Raditschová J, Bálintová M. Utilization of Catalytically Active Metals in Mining Waste and Water for Synthesis of Carbon Nanotubes. *Cleaner Eng Technol*. Elsevier. 2022;8:100459.
- [213] Sampaio EFS, Soares OSGP, Pereira MFR, Rodrigues CSD, Madeira LM. Fe-Containing Carbon-Coated Monoliths Prepared by CVD in Gaseous Toluene Abatement - Parametric Analysis of the Fenton Process. *Catal Today*. Elsevier. 2023;418:114143.
- [214] Sivamaran V, Balasubramanian V, Gopalakrishnan M, Viswabaskaran V, Rao AG. Combined Synthesis of Carbon Nanospheres and Carbon Nanotubes Using Thermal Chemical Vapor Deposition Process. *Chem Phys Impact*. Elsevier. 2022;4:100072.
- [215] Li M, Hachiya S, Chen Z, Osawa T, Sugime H, Noda S. Fluidized-Bed Production of 0.3 Mm-Long Single-Wall Carbon Nanotubes at 28% Carbon Yield with 0.1 Mass% Catalyst Impurities Using Ethylene and Carbon Dioxide. *Carbon*. Pergamon. 2021;182:23–31.
- [216] Alexander R, Khausal A, Bahadur J, Dasgupta K. Bi-Directional Catalyst Injection in Floating Catalyst Chemical Vapor Deposition for Enhanced Carbon Nanotube Fiber Yield. *Carbon Trends*. Elsevier. 2022;9:100211.
- [217] Chan KF, Maznam NAM, Hazan MA, Ahmad RNA, Sa'ari AS, Azman NFI, Mamat MS, Rahman MAA, Tanemura M, Yaakob Y. Multi-Walled Carbon Nanotubes Growth by Chemical Vapour Deposition: Effect of Precursor Flowing Path and Catalyst Size. *Carbon Trends*. Elsevier. 2022;6:100142.
- [218] Prabu S, Chiang KY. Highly Active Ni–Mg–Al Catalyst Effect on Carbon Nanotube Production from Waste Biodegradable Plastic Catalytic Pyrolysis. *Environ Technol Innov*. Elsevier. 2022;28:102845.
- [219] Shoukat R, Khan MI. Carbon Nanotubes/Nanofibers (CNTs/CNFs): A Review on State of the Art Synthesis Methods. *Microsyst Technol*. Springer Science and Business Media Deutschland GmbH. 2022;28:885–901.
- [220] Mubarak NM, Sahu JN, Karri RR, Abdullah EC, Tripathi M. Effect of Hydrogen Flow Rate on the Synthesis of Carbon Nanofiber Using Microwave-Assisted Chemical Vapour Deposition with Ferrocene as a Catalyst. *Int J Hydrogen Energy*. Pergamon. 2023;48:21332–21344.
- [221] Silva AA, Pinheiro RA, Trava-Airoldi VJ, Corat EJ. Influence of Catalyst Particles on Multi-Walled Carbon Nanotubes Morphology and Structure. *Taylor & Francis*. 2018;26:315–323.
- [222] He M, Wang X, Zhang L, Wu Q, Song X, Chernov AI, Fedotov PV, Obratsova ED, Sainio J, Jiang H, Cui H, Ding F, Kauppinen E. Anchoring Effect of Ni²⁺ in Stabilizing Reduced Metallic Particles for Growing Single-Walled Carbon Nanotubes. *Carbon*. Pergamon. 2018;128:249–256.
- [223] Liu X, Shen B, Wu Z, Parlett CMA, Han Z, George A, Yuan P, Patel D, Wu C. Producing Carbon Nanotubes from Thermochemical Conversion of Waste Plastics Using Ni/Ceramic Based Catalyst. *Chem Eng Sci*. Pergamon. 2018;192:882–891.
- [224] Lin J, Yang Y, Zhang H, Lin Q, Zhu B. Synthesis and Characterization of In-Situ CNTs Reinforced TiB₂-Based Composite by CVD Using Ni Catalysts. *Ceram Int*. Elsevier. 2018;44:2042–2047.
- [225] Keteklahijani YZ, Arjmand M, Sundararaj U. Cobalt Catalyst Grown Carbon Nanotube/Poly(Vinylidene Fluoride) Nanocomposites: Effect of Synthesis Temperature on Morphology, Electrical Conductivity and Electromagnetic Interference Shielding. *ChemistrySelect*. John Wiley & Sons, Ltd. 2017;2:10271–10284.
- [226] Su S, Wang Y, Qin J, Wang C, Yao Z, Lu R, Wang Q. Continuous Method for Grafting CNTs on the Surface of Carbon Fibers Based on Cobalt Catalyst Assisted by Thiourea. *J Mater Sci*. Springer New York LLC. 2019;54:12498–12508.
- [227] Sakurai S, Yamada M, He J, Hata K, Futaba DN. A Hydrogen-Free Approach for Activating an Fe Catalyst Using Trace Amounts of Noble Metals and Confinement into Nanoparticles. *J Phys Chem Lett*. American Chemical Society. 2022;13:1879–1885.
- [228] Verma B, Sewani H, Balomajumder C. Synthesis of Carbon Nanotubes via Chemical Vapor Deposition: An Advanced Application in the Management of Electroplating Effluent. *Environ Sci Pollut Res*. Springer. 2020;27:14007–14018.
- [229] Hoecker C, Smail F, Pick M, Boies A. The Influence of Carbon Source and Catalyst Nanoparticles on CVD Synthesis of CNT Aerogel. *Chem Eng J*.

- [230] Ostadhossein A, Yoon K, van Duin ACT, Seo JW, Seveno D. Do Nickel and Iron Catalyst Nanoparticles Affect the Mechanical Strength of Carbon Nanotubes? *Extreme Mech Lett. Elsevier*. 2018;20:29–37.
- [231] Shibuki S, Akashi T, Watanabe H. Effect of Catalyst Support Layers on Emissivity of Carbon Nanotubes Grown via Floating Catalyst Chemical Vapor Deposition. *Meas Sens. Elsevier*. 2022;24:100479.
- [232] ManasiParkhi M, K SB, Shah MM. Experimental Study on Synthesis of CNT Using Alumina Supported Catalyst by CVD Method. *Int J Innov Eng Res Technol. Novateur Publication*. 2015;1–4.
- [233] Fontana M, Ramos R, Morin A, Dijon J. Direct Growth of Carbon Nanotubes Forests on Carbon Fibers to Replace Microporous Layers in Proton Exchange Membrane Fuel Cells. *Carbon. Pergamon*. 2021;172:762–771.
- [234] Samad S, Loh KS, Wong WY, Lee TK, Sunarso J, Chong ST, Wan Daud WR. Carbon and Non-Carbon Support Materials for Platinum-Based Catalysts in Fuel Cells. *Int J Hydrogen Energy. Pergamon*. 2020;43:7823–7854.
- [235] Mishakov IV, Bauman YI, Brzhezinskaya M, Netskina OV, Shubin YV, Kibis LS, Stoyanovskii VO, Larionov KB, Serkova AN, Vedyagin AA. Water Purification from Chlorobenzenes Using Heteroatom-Functionalized Carbon Nanofibers Produced on Self-Organizing Ni-Pd Catalyst. *J Environ Chem Eng. Elsevier*. 2022;10:107873.
- [236] Feng M, Luo ZH, Chen RQ, Yi S, Lu H, Cao GP, Lu C, Feng SY, Li CY. Palladium Supported on Carbon Nanotube Modified Nickel Foam as a Structured Catalyst for Polystyrene Hydrogenation. *Appl Catal A Gen. Elsevier*. 2019;570:329–338.
- [237] Reddy KR, Jyothi MS, Raghu AV, Sadhu V, Naveen S, Aminabhavi TM. Nanocarbons-Supported and Polymers-Supported Titanium Dioxide Nanostructures as Efficient Photocatalysts for Remediation of Contaminated Wastewater and Hydrogen Production. *Springer, Cham*. 139–169.
- [238] Aghaei A, Shaterian M, Hosseini Monfared H, Farokhi A. Designing a Strategy for Fabrication of Single-Walled Carbon Nanotube via CH₄/N₂ Gas by the Chemical Vapor Deposition Method. *Adv Powder Technol. Elsevier*. 2022;33:103500.
- [239] Thapa A, Wang X, Li W. Synthesis and Field Emission Properties of Cu-Filled Vertically Aligned Carbon Nanotubes. *Appl Surf Sci. North-Holland*. 2021;537:148086.
- [240] Zhang H, Liu Y, Tao J, Liu Y, Bao R, Li F, Yi J. Direct Synthesis of Carbon Nanotube-Graphene Hybrids on Copper Powders and the Mechanical Properties of Corresponding Composites. *Mater Sci Eng A. Elsevier*. 2021;825:141861.
- [241] Liu W, Zhang S, Qian L, Lin D, Zhang J. Growth of High-Density Horizontal SWNT Arrays Using Multi-Cycle in-Situ Loading Catalysts. *Carbon. Pergamon*. 2020;157:164–168.
- [242] Fu S, Chen X, Liu P. Preparation of CNTs/Cu Composites with Good Electrical Conductivity and Excellent Mechanical Properties. *Materials Science and Engineering: A. Elsevier*. 2020;771:138656.
- [243] Olson S, Zietz O, Tracy J, Li Y, Tao C, Jiao J. Low-Temperature Chemical Vapor Deposition Growth of Graphene Films Enabled by Ultrathin Alloy Catalysts. *J Vacuum Sci Technol B. American Vacuum Society*. 2020;38:032202.
- [244] Lv S, Wu Q, Xu Z, Yang T, Jiang K, He M. Chirality Distribution of Single-Walled Carbon Nanotubes Grown from Gold Nanoparticles. *Carbon. Pergamon*. 2022;192:259–264.
- [245] Manawi YM, Ihsanullah, Samara A, Al-Ansari T, Atieh MA. A Review of Carbon Nanomaterials' Synthesis via the Chemical Vapor Deposition (CVD) Method. *Materials. Multidisciplinary Digital Publishing Institute*. 2018;11:822.
- [246] Yao C, Bai W, Geng L, He Y, Wang F, Lin Y. Experimental Study on Microreactor-Based CNTs Catalysts: Preparation and Application. *Colloids Surf A Physicochem Eng Asp. Elsevier*. 2019;583:124001.
- [247] Lim YD, Avramchuck AV, Grapov D, Tan CW, Tay BK, Aditya S, Labunov V. Enhanced Carbon Nanotubes Growth Using Nickel/Ferrocene-Hybridized Catalyst. *ACS Omega. American Chemical Society*. 2017;2:6063–6071.
- [248] Abdulkareem AS, Kariim I, Bankole MT, Tijani JO, Abodunrin TF, Olu SC. Synthesis and Characterization of Tri-Metallic Fe–Co–Ni Catalyst Supported on CaCO₃ for Multi-Walled Carbon Nanotubes Growth via Chemical Vapor Deposition Technique. *Arab J Sci Eng. Springer Verlag*. 2017;42:4365–4381.
- [249] Yao D, Wu C, Yang H, Zhang Y, Nahil MA, Chen Y, Williams PT, Chen H. Co-Production of Hydrogen and Carbon Nanotubes from Catalytic Pyrolysis of Waste Plastics on Ni-Fe Bimetallic Catalyst. *Energy Convers Manage. Pergamon*. 2017;148:692–700.
- [250] Yesudhas Jayakumari B, Nattanmai Swaminathan E, Partheeban P. A Review on Characteristics Studies on Carbon Nanotubes-Based Cement Concrete. *Constr Build Mater. Elsevier*. 2023;367:130344.
- [251] Al-Zu'bi M, Fan M, Anguilano L. Advances in Bonding Agents for Retrofitting Concrete Structures with Fibre Reinforced Polymer Materials: A Review. *Constr Build Mater. Elsevier*. 2022;330:127115.
- [252] Wu H, Xia H, Zhang X, Zhang H, Liu H, Sun J. Polydimethylsiloxane/Multi-Walled Carbon Nanotube Nanocomposite Film Prepared by Ultrasonic-Assisted Forced Impregnation with a Superior Photoacoustic Conversion Efficiency of 9.98×10^{-4} . *SPIE*. 2020;14:046003.
- [253] Nguyen YH, Mai PT, Phan N, Nguyen T, Tran HV, Nguyen DV, Thi T, Nguyen N, Pham TV, Doan PD, Phan MN. Fabrication of Graphene from Graphite Using High-Powered Ultrasonic Vibrators.

- [254] Diego M, Gandolfi M, Casto A, Bellussi FM, Vialla F, Crut A, Roddaro S, Fasano M, Vallée F, Del Fatti N, Maioli P, Banfi F. Ultrafast Nano Generation of Acoustic Waves in Water via a Single Carbon Nanotube. *Photoacoustics*. Elsevier. 2022;28:100407.
- [255] Kudr J, Haddad Y, Richtera L, Heger Z, Cernak M, Adam V, Zitka O. *Magnetic Nanoparticles: From Design and Synthesis to Real World Applications*. Nanomaterials. Multidisciplinary Digital Publishing Institute. 2017;7:243.
- [256] Khan FSA, Mubarak NM, Tan YH, Khalid M, Karri RR, Walvekar R, Abdullah EC, Nizamuddin S, Mazari SA. A Comprehensive Review on Magnetic Carbon Nanotubes and Carbon Nanotube-Based Buckypaper for Removal of Heavy Metals and Dyes. *J Hazard Mater*. Elsevier. 2021;413:125375.
- [257] Lavagna L, Nisticò R, Musso S, Pavese M. Functionalization as a Way to Enhance Dispersion of Carbon Nanotubes in Matrices: A Review. *Mater Today Chem*. Elsevier. 2021;20:100477.
- [258] Pandey A, Qamar SF, Das S, Basu S, Kesarwani H, Saxena A, Sharma S, Sarkar J. Advanced Multi-Wall Carbon Nanotube-Optimized Surfactant-Polymer Flooding for Enhanced Oil Recovery. *Fuel*. Elsevier. 2024;355:129463.
- [259] Li Y, Li R, Fu X, Wang Y, Zhong WH. A Bio-Surfactant for Defect Control: Multifunctional Gelatin Coated MWCNTs for Conductive Epoxy Nanocomposites. *Compos Sci Technol*. Elsevier. 2018;159:216–224.
- [260] Bricha M, El Mabrouk K. Effect of Surfactants on the Degree of Dispersion of MWNTs in Ethanol Solvent. *Colloids Surf A Physicochem Eng Asp*. Elsevier. 2019;561:57–69.
- [261] Sezer N, Koç M. Stabilization of the Aqueous Dispersion of Carbon Nanotubes Using Different Approaches. *Thermal Sci Eng Progress*. Elsevier. 2018;8:411–417.
- [262] Price GJ, Nawaz M, Yasin T, Bibi S. Sonochemical Modification of Carbon Nanotubes for Enhanced Nanocomposite Performance. *Ultrason Sonochem*. Elsevier. 2018;40:123–130.
- [263] Ni C, Zhu L. Investigation on Machining Characteristics of TC4 Alloy by Simultaneous Application of Ultrasonic Vibration Assisted Milling (UVAM) and Economical-Environmetal MQL Technology. *J Mater Process Technol*. Elsevier. 2020;278:116518.
- [264] Santha Kumar ARS, Padmakumar A, Kalita U, Samanta S, Baral A, Singha NK, Ashokkumar M, Qiao GG. *Ultrasonics in Polymer Science: Applications and Challenges*. Prog Mater Sci. Pergamon. 2023;136:101113.
- [265] Namathoti S, Ravindra R Kumar, Rama RS. A Review on Progress in Magnetic, Microwave, Ultrasonic Responsive Shape-Memory Polymer Composites. *Mater Today: Proc*. Elsevier. 2022;56:1182–1191.
- [266] Gavriş V, Chayka T, Baranov G, Fedorova S, Gavriş O. Effect of Additives Being WC, TiC, TaC Nanopowder Mixtures on Strength Property of Concrete. *Mater Today: Proc*. Elsevier. 2019;19:1961–1964.
- [267] Gavriş V, Chayka T, Baranov G, Oleynik AY, Shagova YO. Investigation of the Influence of Tungsten Carbide Nanopowder WC and the Mixture of Tungsten Carbides and Titanium Carbides (WC, TiC) on the Change of Concrete Performance Properties. *J Phys: Conf Ser*. IOP Publishing. 2021;1866:012008.
- [268] Dinesh A, Yuvaraj S, Abinaya S, Bhanushri S. Nanopowders as an Additive for Strength and Durability Enhancement of Cement Composite: Review and Prospects. *Mater Today: Proc*. Elsevier. 2023.
- [269] Kockerbeck Z, TabkhPaz M, Hugo R, Park S. Robust Nanocomposite Coatings Inspired by Structures of Nacre. *Proc Biennial Int Pipeline Conf. IPC*. American Society of Mechanical Engineers Digital Collection. 2018;3.
- [270] Juhim F, Chee FP, Awang A, Duinong M, Rasmidi R, Rumaling MI. Review—Radiation Shielding Properties of Tellurite and Silicate Glass. *ECS J Solid State Sci Technol*. IOP Publishing. 2022;11:076006.
- [271] Eslami-Farsani R, Aghamohammadi H, Khalili SMR, Ebrahimnezhad-Khaljiri H, Jalali H. Recent Trend in Developing Advanced Fiber Metal Laminates Reinforced with Nanoparticles: A Review Study. *J Ind Text*. SAGE Publications Ltd. 2022;51:7374S-7408S.
- [272] Manoj A, Ramachandran R, Menezes PL. Self-Healing and Superhydrophobic Coatings for Corrosion Inhibition and Protection. *Int J Adv Manuf Technol*. Springer. 2020;106:2119–2131.
- [273] Othman NH, Che Ismail M, Mustapha M, Sallih N, Kee KE, Ahmad Jaal R. Graphene-Based Polymer Nanocomposites as Barrier Coatings for Corrosion Protection. *Prog Org Coat*. Elsevier. 2019;135:82–99.
- [274] Gao F, Mu J, Bi Z, Wang S, Li Z. Recent Advances of Polyaniline Composites in Anticorrosive Coatings: A Review. *Prog Org Coat*. Elsevier. 2021;151:106071.
- [275] Nazeer AA, Madkour M. Potential Use of Smart Coatings for Corrosion Protection of Metals and Alloys: A Review. *J Mol Liq*. Elsevier. 2018;253:11–22.
- [276] Han W, Zhou J, Shi Q. Research Progress on Enhancement Mechanism and Mechanical Properties of FRP Composites Reinforced with Graphene and Carbon Nanotubes. *Alexandria Eng J*. Elsevier. 2023;64:541–579.
- [277] Li Y, Wang Q, Wang S. A Review on Enhancement of Mechanical and Tribological Properties of Polymer Composites Reinforced by Carbon Nanotubes and Graphene Sheet: Molecular Dynamics Simulations. *Compos Part B Eng*. Elsevier. 2019;160:348–361.

- [278] Gumede JI, Carson J, Hlangothi SP, Bolo LL. Effect of Single-Walled Carbon Nanotubes on the Cure and Mechanical Properties of Reclaimed Rubber/Natural Rubber Blends. *Mater Today Commun.* Elsevier. 2020;23:100852.
- [279] Geng H, Zhao P, Mei J, Chen Y, Yu R, Zhao Y, Ding A, Peng Z, Liao L, Liao J. Improved Microwave Absorbing Performance of Natural Rubber Composite with Multi-Walled Carbon Nanotubes and Molybdenum Disulfide Hybrids. *Polym Adv Technol.* John Wiley & Sons, Ltd. 2020;31:2752–2762.
- [280] Lin JL, Su SM, He YB, Kang FY. Improving Thermal and Mechanical Properties of the Alumina Filled Silicone Rubber Composite by Incorporating Carbon Nanotubes. *New Carbon Mater.* Elsevier. 2020;35:66–72.
- [281] Gao Y, Jing H, Yu Z, Li L, Wu J, Chen W. Particle Size Distribution of Aggregate Effects on the Reinforcing Roles of Carbon Nanotubes in Enhancing Concrete ITZ. *Construction and Building Materials.* Elsevier. 2022;327:126964.
- [282] Wang J, Dong S, Pang SD, Zhou C, Han B. Pore Structure Characteristics of Concrete Composites with Surface-Modified Carbon Nanotubes. *Cement and Concrete Composites.* Elsevier. 2022;128:104453.
- [283] Adhikary SK, Rudžionis Ž, Tučkutė S, Ashish DK. Effects of Carbon Nanotubes on Expanded Glass and Silica Aerogel Based Lightweight Concrete. *Scientific Reports.* Nature Publishing Group. 2021;11:1-11.
- [284] Jongvivatsakul P, Thongchom C, Mathuros A, Prasertsri T, Adamu M, Orasutthikul S, et al. Enhancing Bonding Behavior between Carbon Fiber-Reinforced Polymer Plates and Concrete Using Carbon Nanotube Reinforced Epoxy Composites. *Case Studies in Construction Materials.* Elsevier. 2022;17:e01407.
- [285] Siahkouhi M, Razaqpur G, Hoult NA, Hajmohammadian Baghban M, Jing G. Utilization of Carbon Nanotubes (CNTs) in Concrete for Structural Health Monitoring (SHM) Purposes: A Review. *Construction and Building Materials.* Elsevier. 2021;309:125137.
- [286] Dinesh A, Ashwathi R, Kamal B, Akash C, Sujith S. Influence of Carbon Nanotube on the Mechanical and Electrical Characteristics of Concrete – A Review. *Materials Today: Proceedings.* Elsevier. 2023.
- [287] Kumar A, Sinha S. Performance of Multiwalled Carbon Nanotube Doped Fired Clay Bricks. *Journal of Materials in Civil Engineering.* American Society of Civil Engineers. 2022;34:04022349.
- [288] Pan Q, Hu J, Hu C, Yan Y. Reparation and Characterization of Carbon Nanotubes Coated on Expanded Perlite as Sound Absorption Composite Materials. *Materials Science and Engineering: B.* Elsevier. 2023;296:116697.
- [289] Singh Rajput N, Dilipbhai Shukla D, Ishan L, Dass V. Effect of MWCNT on Mechanical Properties of Polymer Based Composite Brick. *Materials Today: Proceedings.* Elsevier. 2021;47:6522–6525.
- [290] Zhang JJ, Yang CH, Zhang JS. Thermal Characteristics of Aluminium HOLLOWED Bricks Filled with Phase Change Materials: Experimental and Numerical Analyses. *Applied Thermal Engineering.* Pergamon. 2019;155:70–81.
- [291] Thethwayo BM, Steenkamp JD. A Review of Carbon-Based Refractory Materials and Their Applications. *Journal of the Southern African Institute of Mining and Metallurgy.* The Southern African Institute of Mining and Metallurgy. 2020;120:641–650.
- [292] Nor AFM, Sultan MTH, Jawaid M, Azmi AMR, Shah AUM. Analysing Impact Properties of CNT Filled Bamboo/Glass Hybrid Nanocomposites through Drop-Weight Impact Testing, UWPI and Compression-after-Impact Behaviour. *Composites Part B: Engineering.* Elsevier. 2019;168:166–174.
- [293] Kamesh B, Singh LK, Kassa MK, Arumugam AB. Synergetic Effect of Incorporating Graphene, CNT and Hybrid Nanoparticles on the Mechanical Properties of Glass Fiber Reinforced Epoxy Laminated Composites. *Cogent Engineering.* Cogent. 2023;10.
- [294] Tan YJ, Li J, Cai JH, Tang XH, Liu JH, Hu Z qian, et al. Comparative Study on Solid and Hollow Glass Microspheres for Enhanced Electromagnetic Interference Shielding in Polydimethylsiloxane/Multi-Walled Carbon Nanotube Composites. *Composites Part B: Engineering.* Elsevier. 2019;177:107378.
- [295] Uribe-Riestra G, Ayuso-Faber P, Rivero-Ayala M, Cauch-Cupul J, Gamboa F, Avilés F. Structural Health Monitoring of Carbon Nanotube-Modified Glass Fiber-Reinforced Polymer Composites by Electrical Resistance Measurements and Digital Image Correlation. *Structural Health Monitoring.* SAGE Publications Ltd. 2023.
- [296] Krishnamurthy A, Tao R, Senses E, Doshi SM, Burni FA, Natarajan B, et al. Multiscale Polymer Dynamics in Hierarchical Carbon Nanotube Grafted Glass Fiber Reinforced Composites. *ACS Applied Polymer Materials.* American Chemical Society. 2019;1:1905–1917.
- [297] Idumah CI. Novel Trends in Conductive Polymeric Nanocomposites, and Bionanocomposites. *Synthetic Metals.* Elsevier. 2021;273:116674.
- [298] Fang X, Chen X, Liu Y, Li Q, Zeng Z, Maiyalagan T, et al. Nanocomposites of Zr(IV)-Based Metal-Organic Frameworks and Reduced Graphene Oxide for Electrochemically Sensing Ciprofloxacin in Water. *ACS Applied Nano Materials.* American Chemical Society. 2019;2:2367–2376.
- [299] Alavi M, Rai M. Recent Advances in Antibacterial Applications of Metal Nanoparticles (MNPs) and Metal Nanocomposites (MNCs) against Multidrug-Resistant (MDR) Bacteria. *Expert Review of Anti-infective Therapy.* Taylor & Francis. 2019;17:419–428.

- [300] Zaghoul MMY, Zaghoul MMY, Fuseini M. Recent Progress in Epoxy Nanocomposites: Corrosion, Structural, Flame Retardancy and Applications — A Comprehensive Review. *Polymers for Advanced Technologies*. John Wiley & Sons, Ltd. 2023.
- [301] Zhou MY, Ren LB, Fan LL, Zhang YWX, Lu TH, Quan GF, et al. Progress in Research on Hybrid Metal Matrix Composites. *Journal of Alloys and Compounds*. Elsevier. 2020;838:155274.
- [302] Khanna V, Kumar V, Bansal SA. Mechanical Properties of Aluminium-Graphene/Carbon Nanotubes (CNTs) Metal Matrix Composites: Advancement, Opportunities and Perspective. *Materials Research Bulletin*. Pergamon. 2021;138:111224.
- [303] Hassan T, Salam A, Khan A, Khan SU, Khanzada H, Wasim M, et al. Functional Nanocomposites and Their Potential Applications: A Review. *Journal of Polymer Research*. Springer. 2021;28:2.
- [304] Kumar A, Sharma K, Dixit AR. A Review on the Mechanical Properties of Polymer Composites Reinforced by Carbon Nanotubes and Graphene. *Carbon Letters*. Springer. 2021;31:149–165.
- [305] Nurazzi NM, Sabaruddin FA, Harussani MM, Kamarudin SH, Rayung M, Asyraf MRM, et al. Mechanical Performance and Applications of CNTs Reinforced Polymer Composites—A Review. *Nanomaterials*. Multidisciplinary Digital Publishing Institute. 2021;11:2186.
- [306] Basheer BV, George JJ, Siengchin S, Parameswaranpillai J. Polymer Grafted Carbon Nanotubes—Synthesis, Properties, and Applications: A Review. *Nano-Structures & Nano-Objects*. Elsevier. 2020;22:100429.
- [307] Wu H, Fahy WP, Kim S, Kim H, Zhao N, Pilato L, et al. Recent Developments in Polymers/Polymer Nanocomposites for Additive Manufacturing. *Progress in Materials Science*. Pergamon. 2020;111:100638.
- [308] Sementsov Y, Yang W, Ivanenko K, Makhno S, Kartel M. Modification of Rubber Compositions by Carbon Nanotubes. *Applied Nanoscience (Switzerland)*. Springer Science and Business Media Deutschland GmbH. 2022;12:621–628.
- [309] Kumar Singaravel D, Sharma S, Kumar P. Recent Progress in Experimental and Molecular Dynamics Study of Carbon Nanotube Reinforced Rubber Composites: A Review. *Polymer-Plastics Technology and Materials*. Taylor & Francis. 2022;61:1792–1825.
- [310] Hsiao FR, Wu IF, Liao YC. Porous CNT/Rubber Composite for Resistive Pressure Sensor. *Journal of the Taiwan Institute of Chemical Engineers*. Elsevier. 2019;102:387–393.
- [311] Shao J, Zhu H, Zhao B, Haruna SI, Xue G, Jiang W, et al. Combined Effect of Recycled Tire Rubber and Carbon Nanotubes on the Mechanical Properties and Microstructure of Concrete. *Construction and Building Materials*. Elsevier. 2022;322:126493.
- [312] Wang Y, Suo J, Wang H, Wang D, Wei L, Zhu H. Preparation and Reinforcement Performance of RGO-CNTs-SiO₂ Three-Phase Filler for Rubber Composites. *Composites Science and Technology*. Elsevier. 2022;228:109633.
- [313] Lee J, Kim J, Shin Y, Jung I. Ultra-Robust Wide-Range Pressure Sensor with Fast Response Based on Polyurethane Foam Doubly Coated with Conformal Silicone Rubber and CNT/TPU Nanocomposites Islands. *Composites Part B: Engineering*. Elsevier. 2019;177:107364.
- [314] Lin M, Zheng Z, Yang L, Luo M, Fu L, Lin B, et al. A High-Performance, Sensitive, Wearable Multifunctional Sensor Based on Rubber/CNT for Human Motion and Skin Temperature Detection. *Advanced Materials*. John Wiley & Sons, Ltd. 2022;34:2107309.
- [315] Sankhla AM, Patel KM, Makhesana MA, Giasin K, Pimenov DY, Wojciechowski S, et al. Effect of Mixing Method and Particle Size on Hardness and Compressive Strength of Aluminium Based Metal Matrix Composite Prepared through Powder Metallurgy Route. *Journal of Materials Research and Technology*. Elsevier. 2022;18:282–292.
- [316] Qian L, Zheng Y, Or T, Park HW, Gao R, Park M, et al. Advanced Material Engineering to Tailor Nucleation and Growth towards Uniform Deposition for Anode-Less Lithium Metal Batteries. *Small*. John Wiley & Sons, Ltd. 2022;18:2205233.
- [317] Ali N, Bahman AM, Aljuwayhel NF, Ebrahim SA, Mukherjee S, Alsayegh A. Carbon-Based Nanofluids and Their Advances towards Heat Transfer Applications—A Review. *Nanomaterials*. Multidisciplinary Digital Publishing Institute. 2021;11:1628.
- [318] Gao F, Tian W, Wang Z, Wang F. Effect of Diameter of Multi-Walled Carbon Nanotubes on Mechanical Properties and Microstructure of the Cement-Based Materials. *Construction and Building Materials*. Elsevier. 2020;260:120452.
- [319] Gao F, Tian W, Wang Z, Wang F. Effect of Diameter of Multi-Walled Carbon Nanotubes on Mechanical Properties and Microstructure of the Cement-Based Materials. *Construction and Building Materials*. Elsevier. 2020;260:120452.
- [320] Barra G, Guadagno L, Vertuccio L, Simonet B, Santos B, Zarrelli M, Arena M, Viscardi M. Different Methods of Dispersing Carbon Nanotubes in Epoxy Resin and Initial Evaluation of the Obtained Nanocomposite as a Matrix of Carbon Fiber Reinforced Laminate in Terms of Vibroacoustic Performance and Flammability. *Materials*. Multidisciplinary Digital Publishing Institute. 2019;12:2998.
- [321] Stroganov V, Sagadeev E, Ibragimov R, Potapova L. Mechanical Activation Effect on the Biostability of Modified Cement Compositions. *Construction and Building Materials*. Elsevier. 2020;246:118506.

- [322] Egorov AM, Putsylov IA, Smirnov SE, Fateev SA. Effect of Mechanical Activation on Characteristics of Electrodes Based on Fluorinated Carbon Nanotubes. Russian Journal of Applied Chemistry. Maik Nauka-Interperiodica Publishing. 2016;89:451–454.
- [323] Stroganov V, Sagadeev E, Ibragimov R, Potapova L. Mechanical Activation Effect on the Biostability of Modified Cement Compositions. Construction and Building Materials. Elsevier. 2020;246:118506.
- [324] Chen Y, Chadderton LT. Improved Growth of Aligned Carbon Nanotubes by Mechanical Activation. Journal of Materials Research. Springer. 2004;19:2791–2794.
- [325] Shchegolkov AV, Jang S-H, Shchegolkov AV, Rodionov YV, Glivenkova OA, Shchegolkov S-H, Rodionov AV, Glivenkova YV, Multistage OA, Bartolomeo D. Multistage Mechanical Activation of Multilayer Carbon Nanotubes in Creation of Electric Heaters with Self-Regulating Temperature. Materials. Multidisciplinary Digital Publishing Institute. 2021;14:4654.
- [326] Reva VP, Filatenkov A, Mansurov YN, Kuryavyi VG. Stages in Multilayer Carbon Nanotube Formation with Mechanical Activation of Amorphous Carbon. Refractories and Industrial Ceramics. Springer New York LLC. 2016;57:141–145.
- [327] Wang Y, Xiao W, Ma K, Dai C, Wang D, Wang J. In-Situ Growth and Anticorrosion Mechanism of a Bilayer CaCO₃/MgO Coating via Rapid Electrochemical Deposition on AZ41 Mg Alloy Concrete Formwork. Journal of Materials Research and Technology. Elsevier. 2023;25:6628–6643.
- [328] Dumore NS, Mukhopadhyay M. Development of Novel Electrochemical Sensor Based on PtNPs-SenPs-FTO Nanocomposites via Electrochemical Deposition for Detection of Hydrogen Peroxide. Journal of Environmental Chemical Engineering. Elsevier. 2022;10:107058.
- [329] Ata MS, Poon R, Syed AM, Milne J, Zhitomirsky I. New Developments in Non-Covalent Surface Modification, Dispersion and Electrophoretic Deposition of Carbon Nanotubes. Carbon. Pergamon. 2018;130:584–598.
- [330] Islam S, Mia MM, Shah SS, Naher S, Shaikh MN, Aziz MA, Ahammad AJS. Recent Advancements in Electrochemical Deposition of Metal-Based Electrode Materials for Electrochemical Supercapacitors. The Chemical Record. John Wiley & Sons, Ltd. 2022;22:e202200013.
- [331] Zhou A, Bai J, Hong W, Bai H. Electrochemically Reduced Graphene Oxide: Preparation, Composites, and Applications. Carbon. Pergamon. 2022;191:301–332.
- [332] Lota G, Fic K, Frackowiak E. Carbon Nanotubes and Their Composites in Electrochemical Applications. Energy & Environmental Science. The Royal Society of Chemistry. 2011;4:1592–1605.
- [333] Souza VHR, Husmann S, Neiva EGC, Lisboa FS, Lopes LC, Salvatierra RV, Zarbin AJG. Flexible, Transparent and Thin Films of Carbon Nanomaterials as Electrodes for Electrochemical Applications. Electrochimica Acta. Pergamon. 2016;197:200–209.
- [334] Toth PS, Rodgers ANJ, Rabi AK, Dryfe RAW. Electrochemical Activity and Metal Deposition Using Few-Layer Graphene and Carbon Nanotubes Assembled at the Liquid–Liquid Interface. Electrochemistry Communications. Elsevier. 2015;50:6–10.
- [335] Kim H, Jeong NJ, Lee SJ, Song KS. Electrochemical Deposition of Pt Nanoparticles on CNTs for Fuel Cell Electrode. Korean Journal of Chemical Engineering. Springer. 2008;25:443–445.
- [336] Li SM, Wang YS, Yang SY, Liu CH, Chang KH, Tien HW, Wen NT, Ma CCM, Hu CC. Electrochemical Deposition of Nanostructured Manganese Oxide on Hierarchically Porous Graphene–Carbon Nanotube Structure for Ultrahigh-Performance Electrochemical Capacitors. Journal of Power Sources. Elsevier. 2013;225:347–355.
- [337] Shahrokhian S, Rastgar S. Electrochemical Deposition of Gold Nanoparticles on Carbon Nanotube Coated Glassy Carbon Electrode for the Improved Sensing of Tinidazole. Electrochimica Acta. Pergamon. 2012;78:422–429.
- [338] Tang D, Yin H, Mao X, Xiao W, Wang DH. Effects of Applied Voltage and Temperature on the Electrochemical Production of Carbon Powders from CO₂ in Molten Salt with an Inert Anode. Electrochimica Acta. Pergamon. 2013;114:567–573.
- [339] Velamakanni A, Magnuson CW, Ganesh KJ, Zhu Y, An J, Ferreira PJ, Ruoff RS. Site-Specific Deposition of Au Nanoparticles in CNT Films by Chemical Bonding. ACS Nano. American Chemical Society. 2010;4:540–546.
- [340] Kim GM, Nam IW, Yang B, Yoon HN, Lee HK, Park S. Carbon Nanotube (CNT) Incorporated Cementitious Composites for Functional Construction Materials: The State of the Art. Composite Structures. Elsevier. 2019;227:111244.
- [341] Zhu F, Liu W, Liu Y, Shi W. Construction of Porous Interface on CNTs@NiCo-LDH Core-Shell Nanotube Arrays for Supercapacitor Applications. Chemical Engineering Journal. Elsevier. 2020;383:123150.
- [342] Tambrallimath V, Keshavamurthy R, Koppad PG, Sethuram D. Mechanical Characterization of PC-ABS Reinforced with CNT Nanocomposites Developed by Fused Deposition Modelling. Journal of Physics: Conference Series. IOP Publishing. 2020;1455:012003.
- [343] Shetty V, Patil BJ. Evaluation of the Mechanical Properties and Microstructure Analysis of Heat Treated LM-12 Alloy with SiO₂ and CNT Hybrid Metal Matrix Composites. Materials Today: Proceedings. Elsevier. 2021;46:2880–2883.

- [344] Lee ER, Shin SE, Takata N, Kobashi M, Kato M. Manufacturing Aluminum/Multiwalled Carbon Nanotube Composites via Laser Powder Bed Fusion. *Materials*. Multidisciplinary Digital Publishing Institute. 2020;13:3927.
- [345] Upadhyay G, Saxena KK, Sehgal S, Mohammed KA, Prakash C, Dixit S, Buddhi D. Development of Carbon Nanotube (CNT)-Reinforced Mg Alloys: Fabrication Routes and Mechanical Properties. *Metals*. Multidisciplinary Digital Publishing Institute. 2022;12:1392.
- [346] Pejak Simunec D, Sola A. Emerging Research in Conductive Materials for Fused Filament Fabrication: A Critical Review. *Advanced Engineering Materials*. John Wiley & Sons, Ltd. 2022;24:2101476.
- [347] Dorigato A, Moretti P, Dul S, Unterberger SH, Pegoretti A. Electrically Conductive Nanocomposites for Fused Deposition Modelling. *Synthetic Metals*. Elsevier. 2017;226:7–14.
- [348] Ghaemi F, Amiri A, Yunus R. Methods for Coating Solid-Phase Microextraction Fibers with Carbon Nanotubes. *TrAC Trends in Analytical Chemistry*. Elsevier. 2014;59:133–143.
- [349] Sathies T, Senthil P, Anoop MS. A Review on Advancements in Applications of Fused Deposition Modelling Process. *Rapid Prototyping Journal*. Emerald Group Holdings Ltd. 2020;26:669–687.
- [350] Kang HH, Lee DH. Fabrication and Characterization of Cauliflower-like Silica Nanoparticles with Hierarchical Structure through Ion Beam Irradiation. *Journal of Solid State Chemistry*. Academic Press. 2020;289:121528.
- [351] Kim DH, Lee DH. Effect of Irradiation on the Surface Morphology of Nanostructured Superhydrophobic Surfaces Fabricated by Ion Beam Irradiation. *Applied Surface Science*. North-Holland. 2019;477:154–158.
- [352] Yang H, Li X, Wang G, Zheng J. Lead Selenide Polycrystalline Coatings Sensitized Using Diffusion and Ion Beam Methods for Uncooled Mid-Infrared Photodetection. *Coatings*. Multidisciplinary Digital Publishing Institute. 2018;8:444.
- [353] Li P, Chen S, Dai H, Yang Z, Chen Z, Wang Y, Chen Y, Peng W, Shan W, Duan H. Recent Advances in Focused Ion Beam Nanofabrication for Nanostructures and Devices: Fundamentals and Applications. *Nanoscale*. The Royal Society of Chemistry. 2021;13:1529–1565.
- [354] Nesov SN, Korusenko PM, Sachkov VA, Bolotov VV, Povoroznyuk SN. Effects of Preliminary Ion Beam Treatment of Carbon Nanotubes on Structures of Interfaces in MO_x/Multi-Walled Carbon Nanotube (M =Ti,Sn) Composites: Experimental and Theoretical Study. *Journal of Physics and Chemistry of Solids*. Pergamon. 2022;169:110831.
- [355] Das P, Möller W, Elliman RG, Chatterjee S. Ion Beam Joining of Ceramic and Carbon-Based Nanostructures. *Applied Surface Science*. North-Holland. 2021;554:149616.
- [356] Lee CM, Buyukkaya MA, Aghaeimeibodi S, Karasahin A, Richardson CJK, Waks E. A Fiber-Integrated Nanobeam Single Photon Source Emitting at Telecom Wavelengths. *Applied Physics Letters*. American Institute of Physics Inc. 2019;114:171101.
- [357] Liu C, Cao Y, Wang B, Zhang Z, Lin Y, Xu L, Yang Y, Jin C, Peng LM, Zhang Z. Complementary Transistors Based on Aligned Semiconducting Carbon Nanotube Arrays. *ACS Nano*. American Chemical Society. 2022;16:21482–21490.
- [358] Liu X, Wu Z, Hong D, Wu W, Xue C, Cai X, Ding S, Yao F, Jin C, Wang S. Hf-Contacted High-Performance Air-Stable n-Type Carbon Nanotube Transistors. *ACS Applied Electronic Materials*. American Chemical Society. 2021;3:4623–4629.
- [359] Kudinova ES, Vorobyeva EA, Ivanova NA, Tishkin VV, Alekseeva OK. A Magnetron Sputtering Method for the Application of the Ni Catalyst for the Synthesis Process of Carbon Nanotube Arrays. *Nanotechnologies in Russia*. Pleiades journals. 2020;15:715–722.
- [360] Aleksanyan M, Sayunts A, Shahkhatuni G, Simonyan Z, Kasparyan H, Kopecký D. Growth, Characterization, and Application of Vertically Aligned Carbon Nanotubes Using the RF-Magnetron Sputtering Method. *ACS Omega*. American Chemical Society. 2023;8:20949–20958.
- [361] Ma Y, Li L, Qian J, Qu W, Luo R, Wu F, Chen R. Materials and Structure Engineering by Magnetron Sputtering for Advanced Lithium Batteries. *Energy Storage Materials*. 2021;39:203–224.
- [362] Luan H, Zhang Q, Cheng GA, Huang H. As(III) Removal from Drinking Water by Carbon Nanotube Membranes with Magnetron-Sputtered Copper: Performance and Mechanisms. *ACS Applied Materials and Interfaces*. 2018;10:20467–20477.
- [363] Yang H, Zhang L, Wang H, Huang S, Xu T, Kong D, Zhang Z, Zang J, Li X, Wang Y. Regulating Na Deposition by Constructing a Au Sodiophilic Interphase on CNT Modified Carbon Cloth for Flexible Sodium Metal Anode. *Journal of Colloid and Interface Science*. 2022;611:317–326.
- [364] Zhang Y, Sun Z, Liu Y, Liu B, Luo L, Su P, Lan C, Guo S, Zhang Z, Han X, Huang W, Wu ZP, Wang M-S, Chen SY. Face-to-Face Conducting Mechanism Enabled by Si-C Bonds for Binder Free Si@CNTs Electrode. *Chemical Engineering Journal*. 2023;146504.
- [365] Chen Z, Lv H, Zhang Q, Wang H, Chen G. Construction of a Cement-Rebar Nanoarchitecture for a Solution-Processed and Flexible Film of a Bi₂Te₃/CNT Hybrid toward Low Thermal Conductivity and High Thermoelectric Performance. *Carbon Energy*. 2022;4:115–128.

- [366] Ma Y, Li L, Qian J, Qu W, Luo R, Wu F, Chen R. Materials and Structure Engineering by Magnetron Sputtering for Advanced Lithium Batteries. *Energy Storage Materials*. 2021;39:203–224.
- [367] Toma S, Asaka K, Irita M, Saito Y. Bulk Synthesis of Linear Carbon Chains Confined inside Single-Wall Carbon Nanotubes by Vacuum Discharge. *Surface and Interface Analysis*. 2019;51:131–135.
- [368] Kolosko AG, Filippov SV, Popov EO. Vacuum Discharge Analysis of CNT Field Cathode Using a Computerized Field Projector. *Journal of Vacuum Science & Technology B*. 2023;41.
- [369] Wei Y, Jiang K, Liu L, Chen Z, Fan S. Vacuum-Breakdown-Induced Needle-Shaped Ends of Multiwalled Carbon Nanotube Yarns and Their Field Emission Applications. *Nano Letters*. 2007;7:3792–3797.
- [370] Yu R, Fan W, Guo X, Dong S. Highly Ordered and Ultra-Long Carbon Nanotube Arrays as Air Cathodes for High-Energy-Efficiency Li-Oxygen Batteries. *Journal of Power Sources*. 2016;306:402–407.
- [371] Yu YY, Park KC. Focusing Electrode on Focal Spot Size and Dose by Carbon Nanotube Based Cold Cathode Electron Beam (C-Beam). 36th IEEE International Vacuum Nanoelectronics Conference, IVNC 2023. Institute of Electrical and Electronics Engineers Inc. 2023;137–138.
- [372] Carpena-Núñez J, Davis B, Islam AE, Brown J, Sargent G, Murphy N, Back T, Maschmann MR, Maruyama B. Water-Assisted, Electron-Beam Induced Activation of Carbon Nanotube Catalyst Supports for Mask-Less, Resist-Free Patterning. *Carbon*. 2018;135:270–277.
- [373] Han SJ, Tang J, Kumar B, Falk A, Farmer D, Tulevski G, Jenkins K, Afzali A, Oida S, Ott J, Hannon J, Haensch W. High-Speed Logic Integrated Circuits with Solution-Processed Self-Assembled Carbon Nanotubes. *Nature Nanotechnology*. 2017;12:861–865.
- [374] Busà C, Rickard JJS, Chun E, Chong Y, Navaratnam V, Goldberg Oppenheimer P. Tunable Superapolar Lotus-to-Rose Hierarchical Nanosurfaces via Vertical Carbon Nanotubes Driven Electrohydrodynamic Lithography. *Nanoscale*. 2017;9:1625–1636.
- [375] Wang A, Zhao J, Chen K, Li Z, Li C, Dai Q. Ultracoherent Single-Electron Emission of Carbon Nanotubes. *Advanced Materials*. 2023;35:2300185.
- [376] Zhang J, Wang X, Mei H, Cheng Y, Xu M. Self-Assembly of Single-Walled Carbon Nanotubes Arrays with Different Line Width. *Ferroelectrics*. 2019;549:78–86.
- [377] Kodama T, Ohnishi M, Park W, Shiga T, Park J, Shimada T, Shinohara H, Shiomi J, Goodson KE. Modulation of Thermal and Thermoelectric Transport in Individual Carbon Nanotubes by Fullerene Encapsulation. *Nature Materials*. 2017;16:892–897.
- [378] Kim E, Lee BJ, Maleski K, Chae Y, Lee Y, Gogotsi Y, Ahn CW. Microsupercapacitor with a 500 Nm Gap between MXene/CNT Electrodes. *Nano Energy*. 2021;81:105616.
- [379] Helke C, Canpolat-Schmidt CH, Heldt G, Schermer S, Hartmann S, Voigt A, Reuter D. Intra-Level Mix and Match Lithography with Electron Beam Lithography and i-Line Stepper Combined with Resolution Enhancement for Structures below the CD-Limit. *Micro and Nano Engineering*. 2023;19:100189.
- [380] Yang Y, Kulandaivel A, Mehrez S, Mahariq I, Elbadawy I, Mohanavel V, Jalil AT, Saleh MM. Developing a High-Performance Electromagnetic Microwave Absorber Using BaTiO₃/CoS₂/CNTs Triphase Hybrid. *Ceramics International*. 2023;49:2557–2569.
- [381] Gong C, Ding J, Wang C, Zhang Y, Guo Y, Song K, Shi C, He F. Defect-Induced Dipole Polarization Engineering of Electromagnetic Wave Absorbers: Insights and Perspectives. *Composites Part B: Engineering*. 2023;252:110479.
- [382] Zhou C, Lin F, Tang Y, Liu Y, Luo X, Qi Y, Xu S, Qiu Y, Yan H, Tong X, Neogi A, Liu Z, Zhou X, Wang C, Bao J, Wang Z. Highly Effective Electromagnetic Interference Shielding Composites with Solvent-Dispersed Uniformly Aligned Graphene Nanosheets Enabled by Strong Intrinsic Diamagnetism under Magnetic Field. *Materials Today Physics*. 2023;31:100985.
- [383] Dubey KA, Bhardwaj YK. High-Performance Polymer-Matrix Composites: Novel Routes of Synthesis and Interface-Structure-Property Correlations. Springer, Singapore. 2021;1–25.
- [384] Kazakova MA, Semikolenova NV, Korovin EY, Zhuravlev VA, Selyutin AG, Velikanov DA, Moseenkov SI, Andreev AS, Lapina OB, Suslyayev VI, Matsko MA, Zakharov VA, Lacaille JBdE. Co/Multi-Walled Carbon Nanotubes/Polyethylene Composites for Microwave Absorption: Tuning the Effectiveness of Electromagnetic Shielding by Varying the Components Ratio. *Composites Science and Technology*. 2021;207:108731.
- [385] Zhu T, Shen W, Wang X, Song YF, Wang W. Paramagnetic CoS₂@MoS₂ Core-Shell Composites Coated by Reduced Graphene Oxide as Broadband and Tunable High-Performance Microwave Absorbers. *Chemical Engineering Journal*. 2019;378:122159.
- [386] Liang J, Li H, Qi L, Tian W, Li X, Chao X, Wei J. Fabrication and Mechanical Properties of CNTs/Mg Composites Prepared by Combining Friction Stir Processing and Ultrasonic Assisted Extrusion. *Journal of Alloys and Compounds*. 2017;728:282–288.
- [387] Kundalwal SI, Rathi A. Improved Mechanical and Viscoelastic Properties of CNT-Composites Fabricated Using an Innovative Ultrasonic Dual Mixing Technique. *Journal of the Mechanical Behavior of Materials*. 2020;29:77–85.
- [388] Rennhofer H, Zanghellini B. Dispersion State and Damage of Carbon Nanotubes and Carbon Nanofibers by Ultrasonic Dispersion: A Review. *Nanomaterials*. 2021;11:1469.

- [389] Marcotte A, Mouterde T, Niguès A, Siria A, Bocquet L. Mechanically Activated Ionic Transport across Single-Digit Carbon Nanotubes. *Nature Materials*. 2020;19:1057–1061.
- [390] El Moumen A, Tarfaoui M, Nachtane M, Lafdi K. Carbon Nanotubes as a Player to Improve Mechanical Shock Wave Absorption. *Composites Part B: Engineering*. 2019;164:67–71.
- [391] Domagalski Ł, Kubacka E, Marczak J, Herisanu N, Marinca B, Marinca V. Nonlinear Vibration of Double-Walled Carbon Nanotubes Subjected to Mechanical Impact and Embedded on Winkler–Pasternak Foundation. *Materials*. 2022;15:8599.
- [392] Schlagenhauf L, Nüesch F, Wang J. Release of Carbon Nanotubes from Polymer Nanocomposites. *Fibers*;2014;2:108–127.
- [393] Ozden S, Autreto PAS, Tiwary CS, Khatiwada S, Machado L, Galvao DS, Vajtai R, Barrera EV, Ajayan PM. Unzipping Carbon Nanotubes at High Impact. *Nano Letters*. 2014;14:4131–4137.
- [394] Tseluikin VN, Koreschkova AA. Electrochemical Deposition and Properties of Composite Coatings Consisting of Zinc and Carbon Nanotubes. *Russian Journal of Applied Chemistry*. 2015;88:272–274.
- [395] Pei X, Zeng Y, He R, Li Z, Tian L, Wang J, Wan Q, Li X, Bao H. Single-Walled Carbon Nanotubes/Hydroxyapatite Coatings on Titanium Obtained by Electrochemical Deposition. *Applied Surface Science*. 2014;295:71–80.
- [396] Zeng Y, Pei X, Yang S, Qin H, Cai H, Hu S, Sui L, Wan Q, Wang J. Graphene Oxide/Hydroxyapatite Composite Coatings Fabricated by Electrochemical Deposition. *Surface and Coatings Technology*. 2016;286:72–79.
- [397] Mishra P, Jain R. Electrochemical Deposition of MWCNT-MnO₂/PPy Nano-Composite Application for Microbial Fuel Cells. *International Journal of Hydrogen Energy*. 2016;41:22394–22405.
- [398] Zhang R, Fan L, Fang Y, Yang S. Electrochemical Route to the Preparation of Highly Dispersed Composites of ZnO/Carbon Nanotubes with Significantly Enhanced Electrochemiluminescence from ZnO. *Journal of Materials Chemistry*. 2008;18:4964–4970.
- [399] Ren C, Yan Y, Sun B, Gu B, Chou TW. Wet-Spinning Assembly and in Situ Electrodeposition of Carbon Nanotube-Based Composite Fibers for High Energy Density Wire-Shaped Asymmetric Supercapacitor. *Journal of Colloid and Interface Science*. 2020;569:298–306.
- [400] Khazeni D, Saremi M, Soltani R. Development of HA-CNTs Composite Coating on AZ31 Magnesium Alloy by Cathodic Electrodeposition. Part 1: Microstructural and Mechanical Characterization. *Ceramics International*. 2019;45:11174–11185.
- [401] Safavi MS, Walsh FC, Surmeneva MA, Surmenev RA, Khalil-Allafi J. Electrodeposited Hydroxyapatite-Based Biocoatings: Recent Progress and Future Challenges. *Coatings*;2021;11:110.
- [402] Song G, Sun L, Li S, Sun Y, Fu Q, Pan C. Synergistic Effect of Gr and CNTs on Preparing Ultrathin Cu-(CNTs+Gr) Composite Foil via Electrodeposition. *Composites Part B: Engineering*. 2020;187:107841.
- [403] Yan F, Liu L, Li M, Zhang M, Shang L, Xiao L, Ao Y. One-Step Electrodeposition of Cu/CNT/CF Multiscale Reinforcement with Substantially Improved Thermal/Electrical Conductivity and Interfacial Properties of Epoxy Composites. *Composites Part A: Applied Science and Manufacturing*. 2019;125:105530.
- [404] Zheng H, Zhang W, Li B, Zhu J, Wang C, Song G, Wu G, Yang X, Huang Y, Ma L. Recent Advances of Interphases in Carbon Fiber-Reinforced Polymer Composites: A Review. *Composites Part B: Engineering*. 2022;233:109639.
- [405] Guo H, Lv R, Bai S. Recent Advances on 3D Printing Graphene-Based Composites. *Nano Materials Science*. 2019;1:101–115.
- [406] Zheng M, Chi Y, Hu Q, Tang H, Jiang X, Zhang L, Zhang S, Pang H, Xu Q. Carbon Nanotube-Based Materials for Lithium–Sulfur Batteries. *Journal of Materials Chemistry A*. 2019;7:17204–17241.
- [407] Zhang Z, Kong L-L, Liu S, Li G-R, Gao X-P, Zhang Z, Kong L-L, Liu S, Li G-R.X., Gao P. A High-Efficiency Sulfur/Carbon Composite Based on 3D Graphene Nanosheet@Carbon Nanotube Matrix as Cathode for Lithium–Sulfur Battery. *Advanced Energy Materials*. 2017;7:1602543.
- [408] Chai L, Hu Z, Wang X, Xu Y, Zhang L, Li T-T, Hu Y, Qian J, Huang S, Chai L.L., Hu Z.Y., Wang X., Xu Y.W., Hu Y., Qian J.J., Huang S.M., Zhang L.J. Stringing Bimetallic Metal–Organic Framework-Derived Cobalt Phosphide Composite for High-Efficiency Overall Water Splitting. *Advanced Science*. 2020;7:1903195.
- [409] Milowska KZ, Ghorbani-Asl M, Burda M, Wolanicka L, Čatić N, Bristowe PD, Kozioł KKK. Breaking the Electrical Barrier between Copper and Carbon Nanotubes. *Nanoscale*. 2017;9:8458–8469.
- [410] Chu K, Wang F, Wang X. hu, Li Y. biao, Geng Z. rong, Huang D. jian, Zhang H. Interface Design of Graphene/Copper Composites by Matrix Alloying with Titanium. *Materials & Design*. 2018;144:290–303.
- [411] Yuan Q. hong, Zhou G. hua, Liao L, Liu Y, Luo L. Interfacial Structure in AZ91 Alloy Composites Reinforced by Graphene Nanosheets. *Carbon*. 2018;127:177–186.
- [412] Yuan M, Sun L, Lu X.W., Jiang P, Bao X.H. Enhancing the Thermoelectric Performance of Cu–Ni Alloys by Introducing Carbon Nanotubes. *Materials Today Physics*. 2021;16:100311.
- [413] Korusenko PM, Nesov SN, Bolotov V. V., Povoroznyuk SN, Pushkarev AI, Ivlev KE, Smirnov DA. Formation of Tin–Tin Oxide Core–Shell Nanoparticles in the Composite SnO₂–x/Nitrogen-Doped Carbon Nanotubes by Pulsed Ion Beam Irradiation. *Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms*. 2017;394:37–43.

- [414] Athanasiou CE, Zhang H, Ramirez C, Xi J, Baba T, Wang X, Zhang W, Padture NP, Szlufarska I, Sheldon BW. High Toughness Carbon-Nanotube-Reinforced Ceramics via Ion-Beam Engineering of Interfaces. *Carbon*. 2020;163:169–177.
- [415] Chou J.S., Cheng M.Y., Hsieh Y.M., Yang I.T., Hsu H.T. Optimal Path Planning in Real Time for Dynamic Building Fire Rescue Operations Using Wireless Sensors and Visual Guidance. *Automation in Construction*. 2019;99:1–17.
- [416] Mazari SA, Ali E, Abro R, Khan F.S.A., Ahmed I, Ahmed M, Nizamuddin S, Siddiqui T.H., Hossain N, Mubarak NM, Shah A. Nanomaterials: Applications, Waste-Handling, Environmental Toxicities, and Future Challenges – A Review. *Journal of Environmental Chemical Engineering*. 2021;9:105028.
- [417] Sun M, Wu J, Lu P, Zhang Z, Zhang Y, Li D. Sphere-like MoS₂ and Porous TiO₂ Composite Film on Ti Foil as Lithium-Ion Battery Anode Synthesized by Plasma Electrolytic Oxidation and Magnetron Sputtering. *Journal of Alloys and Compounds*. 2022;892:162075.
- [418] Yang L, Jiang S, Chen Y, Xu Z, Ni Q. Effect of Carbon/Tantalum Hybrid Film on the Properties of Carbon Fiber and Its Composites Based on Magnetron Sputtering. *Composites Science and Technology*. 2023;243:110224.
- [419] Aslan N, Kurt M.S., Mehmet Koç M. Morpho-Structural and Optoelectronic Properties of Diamond like Carbon–Germanium (DLC-Ge) Composite Thin Films Produced by Magnetron Sputtering. *Optical Materials*. 2022;126:112229.
- [420] Yang L, Jiang S, Chen Y, Li C, Xu Z, Ni Q. Effect of Multi-Scale Film Interfaces on CFEP Composite Mechanical Properties Based on Magnetron Sputtering Technology. *Diamond and Related Materials*. 2023;139:110355.
- [421] Yang L, Xia H, Xu Z, Lihua Z, Ni Q. Influence of Surface Modification of Carbon Fiber Based on Magnetron Sputtering Technology on Mechanical Properties of Carbon Fiber Composites. *Materials Research Express*. 2020;7:105602.
- [422] Hussain S, Erikson H, Kongi N, Merisalu M, Ritslaid P, Sammelselg V, Tammeveski K. Heat-Treatment Effects on the ORR Activity of Pt Nanoparticles Deposited on Multi-Walled Carbon Nanotubes Using Magnetron Sputtering Technique. *International Journal of Hydrogen Energy*. 2017;42:5958–5970.
- [423] Yang P, Xi X, Huang T, Zhong Q, Jiang B, Liu R, Wu D. An Acid-Assisted Vacuum Filtration Approach towards Flexible PDI/SWCNT Cathodes for Highly Stable Organic Lithium Ion Batteries. *Electrochimica Acta*. 2020;338:135771.
- [424] Luo L, Shen Y, Han D, Qin X, Liang J, Li B, Zhang Y, Deng S. Study on Optimization of Carbon Nanotube Nano-Cold Cathode Array for an Electron Beam Pumping Ultraviolet Light Emitting Device. 36th IEEE International Vacuum Nanoelectronics Conference, IVNC 2023. Institute of Electrical and Electronics Engineers Inc. 2023;169–171.
- [425] Rodiansyah A, Park K.C. Functionalize of Vertically Aligned CNTs Emitter (C-Beam) for Surface Modification and Patterning of Self-Assembled Monolayers (SAM). 2021 34th International Vacuum Nanoelectronics Conference, IVNC 2021. Institute of Electrical and Electronics Engineers Inc.
- [426] Harito C, Bavykin D. V., Yuliarto B, Dipojono H.K., Walsh F.C. Polymer Nanocomposites Having a High Filler Content: Synthesis, Structures, Properties, and Applications. *Nanoscale*. 2019;11:4653–4682.
- [427] Guo J, Jiang H, Teng Y, Xiong Y, Chen Z, You L, Xiao D. Recent Advances in Magnetic Carbon Nanotubes: Synthesis, Challenges and Highlighted Applications. *Journal of Materials Chemistry B*. 2021;9:9076–9099.
- [428] Llusar J, Climente J.I. Shell Filling and Paramagnetism in Few-Electron Colloidal Nanoplatelets. *Physical Review Letters*. 2022;129:066404.
- [429] Kozak N, Matzui L, Vovchenko L, Kosyanchuk L, Oliynyk V, Antonenko O, Nesin S, Gagulnikina Z. Influence of Coordination Complexes of Transition Metals on EMI-Shielding Properties and Permeability of Polymer Blend/Carbon Nanotube/Nickel Composites. *Composites Science and Technology*. 2020;200:108420.
- [430] Datsyuk V, Trotsenko S, Trakakis G, Boden A, Vyzas-Asimakopoulos K, Parthenios J, Galiotis C, Reich S, Papagelis K. Thermal Properties Enhancement of Epoxy Resins by Incorporating Polybenzimidazole Nanofibers Filled with Graphene and Carbon Nanotubes as Reinforcing Material. *Polymer Testing*. 2020;82:106317.
- [431] Kotop MA, El-Feky MS, Alharbi YR, Abadel AA, Binyahya AS. Engineering Properties of Geopolymer Concrete Incorporating Hybrid Nano-Materials. *Ain Shams Engineering Journal*. 2021;12:3641–3647.
- [432] Atinafu DG, Wi S, Yun BY, Kim S. Engineering Biochar with Multiwalled Carbon Nanotube for Efficient Phase Change Material Encapsulation and Thermal Energy Storage. *Energy*. 2021;216:119294.
- [433] Dong W, Li W, Shen L, Sun Z, Sheng D. Piezoresistivity of Smart Carbon Nanotubes (CNTs) Reinforced Cementitious Composite under Integrated Cyclic Compression and Impact. *Composite Structures*. 2020;241:112106.
- [434] Choi YC. Cyclic Heating and Mechanical Properties of CNT Reinforced Cement Composite. *Composite Structures*. 2021;256:113104.
- [435] Soni SK, Thomas B, Kar VR. A Comprehensive Review on CNTs and CNT-Reinforced Composites: Syntheses, Characteristics and Applications. *Materials Today Communications*. 2020;25:101546.

- [436] Patil SP, Shendye P, Markert B. Molecular Dynamics Simulations of Silica Aerogel Nanocomposites Reinforced by Glass Fibers, Graphene Sheets and Carbon Nanotubes: A Comparison Study on Mechanical Properties. *Composites Part B: Engineering*. 2020;190:107884.
- [437] Bagherzadeh F, Shafighard T. Ensemble Machine Learning Approach for Evaluating the Material Characterization of Carbon Nanotube-Reinforced Cementitious Composites. *Case Studies in Construction Materials*. 2022;17:e01537.
- [438] Mousavi MA, Sadeghi-Nik A, Bahari A, Jin C, Ahmed R, Ozbakkaloglu T, de Brito J. Strength Optimization of Cementitious Composites Reinforced by Carbon Nanotubes and Titania Nanoparticles. *Construction and Building Materials*. 2021;303:124510.
- [439] Shi T, Li Z, Guo J, Gong H, Gu C. Research Progress on CNTs/CNFs-Modified Cement-Based Composites – A Review. *Construction and Building Materials*. 2019;202:290–307.
- [440] Jung M, Lee YS, Hong SG, Moon J. Carbon Nanotubes (CNTs) in Ultra-High Performance Concrete (UHPC): Dispersion, Mechanical Properties, and Electromagnetic Interference (EMI) Shielding Effectiveness (SE). *Cement and Concrete Research*. 2020;131:106017.
- [441] Thomoglou AK, Falara MG, Voutetaki ME, Fantidis JG, Tayeh BA, Chalioris CE. Electromechanical Properties of Multi-Reinforced Self-Sensing Cement-Based Mortar with MWCNTs, CFs, and PPs. *Construction and Building Materials*. 2023;400:132566.
- [442] Kumar R, Jana P. Exact Modal Analysis of Multilayered FG-CNT Plate Assemblies Using the Dynamic Stiffness Method. *Mechanics of Advanced Materials and Structures*. 2023;30:4501–4520.
- [443] Li J, Zhao Y, Hao W, Miao L, Zhao G, Li J, Sang Y, Cheng G, Sui C, Wang C. Improvement in Compressive Stiffness of Graphene Aerogels by Sandwiching Carbon Nanotubes. *Diamond and Related Materials*. 2023;135:109897.
- [444] Emin ÇETİN M. Investigation of Carbon Nanotube Reinforcement to Polyurethane Adhesive for Improving Impact Performance of Carbon Fiber Composite Sandwich Panels. *International Journal of Adhesion and Adhesives*. 2022;112:103002.
- [445] Shanmugam L, Kazemi ME, Li Z, Luo W, Xiang Y, Yang L, Yang J. Low-Velocity Impact Behavior of UHMWPE Fabric/Thermoplastic Laminates with Combined Surface Treatments of Polydopamine and Functionalized Carbon Nanotubes. *Composites Communications*. 2020;22:100527.
- [446] Çetin ME. The Effect of Carbon Nanotubes Modified Polyurethane Adhesive on the Impact Behavior of Sandwich Structures. *Polymer Composites*. 2021;42:4353–4365.
- [447] Obradović V, Simić D, Zrilić M, Stojanović DB, Uskoković PS. Novel Hybrid Nanostructures of Carbon Nanotube/Fullerene-like Tungsten Disulfide as Reinforcement for Aramid Fabric Composites. *Fibers and Polymers*. 2021;22:528–539.
- [448] Naqi A, Abbas N, Zahra N, Hussain A, Shabbir SQ. Effect of Multi-Walled Carbon Nanotubes (MWCNTs) on the Strength Development of Cementitious Materials. *Journal of Materials Research and Technology*. 2019;8:1203–1211.
- [449] Haider MZ, Jin X, Sharma R, Pei J, Hu JW. Enhancing the Compressive Strength of Thermal Energy Storage Concrete Containing a Low-Temperature Phase Change Material Using Silica Fume and Multiwalled Carbon Nanotubes. *Construction and Building Materials*. 2022;314:125659.
- [450] Arrechea S, Guerrero-Gutiérrez EMA, Velásquez L, Cardona J, Posadas R, Callejas K, Torres S, Díaz R, Barrientos C, García E. Effect of Additions of Multiwall Carbon Nanotubes (MWCNT, MWCNT-COOH and MWCNT-Thiazol) in Mechanical Compression Properties of a Cement-Based Material. *Materialia*. 2020;11:100739.
- [451] Abdalla JA, Thomas BS, Hawileh RA, Syed Ahmed Kabeer KI. Influence of Nanomaterials on the Workability and Compressive Strength of Cement-Based Concrete. *Materials Today: Proceedings*. 2022;65:2073–2076.
- [452] Zhang S, Sun K, Liu H, Chen X, Zheng Y, Shi X, Zhang D, Mi L, Liu C, Shen C. Enhanced Piezoresistive Performance of Conductive WPU/CNT Composite Foam through Incorporating Brittle Cellulose Nanocrystal. *Chemical Engineering Journal*. 2020;387:124045.
- [453] Silvestro L, Jean Paul Gleize P. Effect of Carbon Nanotubes on Compressive, Flexural and Tensile Strengths of Portland Cement-Based Materials: A Systematic Literature Review. *Construction and Building Materials*. 2020;264:120237.
- [454] Han J, Wang S, Zhu S, Huang C, Yue Y, Mei C, Xu X, Xia C. Electrospun Core-Shell Nanofibrous Membranes with Nanocellulose-Stabilized Carbon Nanotubes for Use as High-Performance Flexible Supercapacitor Electrodes with Enhanced Water Resistance, Thermal Stability, and Mechanical Toughness. *ACS Applied Materials and Interfaces*. 2019;11:44624–44635.
- [455] Tajzad I, Ghasali E. Production Methods of CNT-Reinforced Al Matrix Composites: A Review. *Journal of Composites and Compounds*. 2020;2:1–9.
- [456] Zare Y, Rhee KY. Evaluation of the Tensile Strength in Carbon Nanotube-Reinforced Nanocomposites Using the Expanded Takayanagi Model. *JOM*. 2019;71:3980–3988.
- [457] Xiong N, Bao R, Yi J, Tao J, Liu Y, Fang D. Interface Evolution and Its Influence on Mechanical Properties of CNTs/Cu-Ti Composite. *Materials Science and Engineering: A*. 2019;755:75–84.

- [458] Taylor LW, Dewey OS, Headrick RJ, Komatsu N, Peraca NM, Wehmeyer G, Kono J, Pasquali M. Improved Properties, Increased Production, and the Path to Broad Adoption of Carbon Nanotube Fibers. *Carbon*. 2021;171:689–694.
- [459] Wu Y, Dong C, Yuan C, Bai X, Zhang L, Tian Y. MWCNTs Filled High-Density Polyethylene Composites to Improve Tribological Performance. *Wear*. 2021;477:203776.
- [460] Nyanor P, El-Kady O, Yehia HM, Hamada AS, Hassan MA. Effect of Bimodal-Sized Hybrid TiC–CNT Reinforcement on the Mechanical Properties and Coefficient of Thermal Expansion of Aluminium Matrix Composites. *Metals and Materials International*. 2021;27:753–766.
- [461] Rimamnya ND, Samson AO, Bunmi DC, Abass GF, Olaniyan AJ, Samson IA, Moyofoluwa OO, Kolawole BT. Evolution of Carbon Nanotubes, Their Methods, And Application as Reinforcements in Polymer Nanocomposites: A Review. *Journal of Advanced Mechanical Engineering Applications*. 2023;4:49–63.
- [462] Jeon H, Kim Y, Yu WR, Lee JU. Exfoliated Graphene/Thermoplastic Elastomer Nanocomposites with Improved Wear Properties for 3D Printing. *Composites Part B: Engineering*. 2020;189:107912.
- [463] Kalangi C. Carbon Nanotubes Enhance the Mechanical and Corrosion Properties of Thermally Sprayed Ceramic Coatings.
- [464] Han D, Yan G, Wang C. Influence of Multi-Walled Carbon Nanotubes (MWCNTs) Content on Metal Friction and Wear in Thermally Cracked Carbon Black (CBp) Formulation System during Mixing. *Polymer Testing*. 2022;113:107674.
- [465] Nayak C, Balani K. Effects of Reinforcements and Gamma-Irradiation on Wear Performance of Ultra-High Molecular Weight Polyethylene as Acetabular Cup Liner in Hip-Joint Arthroplasty: A Review. *Journal of Applied Polymer Science*. 2021;138:51275.
- [466] Lv C, Wang H, Liu Z, Wang C, Zhang W, Li M, Zhu Y. Fabrication of Durable Fluorine-Free Polyphenylene Sulfide/Silicone Resin Composite Superhydrophobic Coating Enhanced by Carbon Nanotubes/Graphene Fillers. *Progress in Organic Coatings*. 2019;134:1–10.
- [467] Hussain AK, Seetharamaiah N, Pichumani M, Chakra CS. Research Progress in Organic Zinc Rich Primer Coatings for Cathodic Protection of Metals – A Comprehensive Review. *Progress in Organic Coatings*. 2021;153:106040.
- [468] Wang Z, Yu J, Li G, Zhang M, Leung CKY. Corrosion Behavior of Steel Rebar Embedded in Hybrid CNTs-OH/Polyvinyl Alcohol Modified Concrete under Accelerated Chloride Attack. *Cement and Concrete Composites*. 2019;100:120–129.
- [469] Nayak SR, Mohana KNS, Hegde MB, Rajitha K, Madhusudhana AM, Naik SR. Functionalized Multi-Walled Carbon Nanotube/Polyindole Incorporated Epoxy: An Effective Anti-Corrosion Coating Material for Mild Steel. *Journal of Alloys and Compounds*. 2021;856:158057.
- [470] Rui M, Jiang Y, Zhu A. Sub-Micron Calcium Carbonate as a Template for the Preparation of Dendrite-like PANI/CNT Nanocomposites and Its Corrosion Protection Properties. *Chemical Engineering Journal*. 2020;385:123396.
- [471] Zhou B, Li Y, Li Z, Ma J, Zhou K, Liu C, Shen C, Feng Y. Fire/Heat-Resistant, Anti-Corrosion and Folding Ti2C3Tx MXene/Single-Walled Carbon Nanotube Films for Extreme-Environmental EMI Shielding and Solar-Thermal Conversion Applications. *Journal of Materials Chemistry C*. 2021;9:10425–10434.
- [472] Rui M, Zhu A. The Synthesis and Corrosion Protection Mechanisms of PANI/CNT Nanocomposite Doped with Organic Phosphoric Acid. *Progress in Organic Coatings*. 2021;153:106134.
- [473] Sivaraj D, Vijayalakshmi K. Enhanced Antibacterial and Corrosion Resistance Properties of Ag Substituted Hydroxyapatite/Functionalized Multiwall Carbon Nanotube Nanocomposite Coating on 316L Stainless Steel for Biomedical Application. *Ultrasonics Sonochemistry*. 2019;59:104730.
- [474] Sharma V, Goyat MS, Hooda A, Pandey JK, Kumar A, Gupta R, Upadhyay AK, Prakash R, Kirabira JB, Mandal P, Bhargav PK. Recent Progress in Nano-Oxides and CNTs Based Corrosion Resistant Superhydrophobic Coatings: A Critical Review. *Progress in Organic Coatings*. 2020;140:105512.
- [475] Say Y, Guler O, Dikici B. Carbon Nanotube (CNT) Reinforced Magnesium Matrix Composites: The Effect of CNT Ratio on Their Mechanical Properties and Corrosion Resistance. *Materials Science and Engineering: A*. 2020;798:139636.
- [476] Shin B, Mondal S, Lee M, Kim S, Huh YI, Nah C. Flexible Thermoplastic Polyurethane-Carbon Nanotube Composites for Electromagnetic Interference Shielding and Thermal Management. *Chemical Engineering Journal*. 2021;418:129282.
- [477] Jin X, Wang J, Dai L, Wang W, Wu H. Largely Enhanced Thermal Conductive, Dielectric, Mechanical and Anti-Dripping Performance in Polycarbonate/Boron Nitride Composites with Graphene Nanoplatelet and Carbon Nanotube. *Composites Science and Technology*. 2019;184:107862.
- [478] Wei J, Liao M, Ma A, Chen Y, Duan Z, Hou X, Li M, Jiang N, Yu J. Enhanced Thermal Conductivity of Polydimethylsiloxane Composites with Carbon Fiber. *Composites Communications*. 2020;17:141–146.
- [479] Wentao he, Gao J, Liao S, Wang X, Qin S, Song P. A Facile Method to Improve Thermal Stability and Flame Retardancy of Polyamide 6. *Composites Communications*. 2019;13:143–150.

- [480] Liu Z, Chen Z, Yu F. Enhanced Thermal Conductivity of Microencapsulated Phase Change Materials Based on Graphene Oxide and Carbon Nanotube Hybrid Filler. *Solar Energy Materials and Solar Cells*. 2019;192:72–80.
- [481] An D, Cheng S, Zhang Z, Jiang C, Fang H, Li J, Liu Y, Wong CP. A Polymer-Based Thermal Management Material with Enhanced Thermal Conductivity by Introducing Three-Dimensional Networks and Covalent Bond Connections. *Carbon*. 2019;155:258–267.
- [482] Guo Y, Ruan K, Shi X, Yang X, Gu J. Factors Affecting Thermal Conductivities of the Polymers and Polymer Composites: A Review. *Composites Science and Technology*. 2020;193:108134.
- [483] Zhang F, Feng Y, Feng W. Three-Dimensional Interconnected Networks for Thermally Conductive Polymer Composites: Design, Preparation, Properties, and Mechanisms. *Materials Science and Engineering: R: Reports*. 2020;142:100580.
- [484] Ding D, Wang J, Yu X, Xiao G, Feng C, Xu W, Bai B, Yang N, Gao Y, Hou X, He G. Dispersing of Functionalized CNTs in Si–O–C Ceramics and Electromagnetic Wave Absorbing and Mechanical Properties of CNTs/Si–O–C Nanocomposites. *Ceramics International*. 2020;46:5407–5419.
- [485] Fang X, Jiang L, Pan L, Yin S, Qiu T, Yang J. High-Thermally Conductive AlN-Based Microwave Attenuating Composite Ceramics with Spherical Graphite as Attenuating Agent. *Journal of Advanced Ceramics*. 2021;10:301–319.
- [486] Vajdi M, Sadegh Moghanlou F, Nekahi S, Ahmadi Z, Motallebzadeh A, Jafarzadeh H, Shahedi Asl M. Role of Graphene Nano-Platelets on Thermal Conductivity and Microstructure of TiB₂–SiC Ceramics. *Ceramics International*. 2020;46:21775–21783.
- [487] Liao N, Jia D, Yang Z, Zhou Y. Enhanced Mechanical Properties and Thermal Shock Resistance of Si₂BC₃N Ceramics with SiC Coated MWCNTs. *Journal of Advanced Ceramics*. 2019;8:121–132.
- [488] Wei H, Yin X, Jiang F, Hou Z, Cheng L, Zhang L. Optimized Design of High-Temperature Microwave Absorption Properties of CNTs/Sc₂Si₂O₇ Ceramics. *Journal of Alloys and Compounds*. 2020;823:153864.
- [489] Wang S, Gong H, Zhang Y, Ashfaq MZ. Microwave Absorption Properties of Polymer-Derived SiCN(CNTs) Composite Ceramics. *Ceramics International*. 2021;47:1294–1302.
- [490] Dai W, Ma T, Yan Q, Gao J, Tan X, Lv L, Hou H, Wei Q, Yu J, Wu J, Yao Y, Du S, Sun R, Jiang N, Wang Y, Kong J, Wong C, Maruyama S, Lin C Te. Metal-Level Thermally Conductive yet Soft Graphene Thermal Interface Materials. *ACS Nano*. 2019;13:11561–11571.
- [491] Park YG, Min H, Kim H, Zhexembekova A, Lee CY, Park JU. Three-Dimensional, High-Resolution Printing of Carbon Nanotube/Liquid Metal Composites with Mechanical and Electrical Reinforcement. *Nano Letters*. 2019;19:4866–4872.
- [492] Sun X, Liu L, Mo Y, Li J, Li C. Enhanced Thermal Energy Storage of a Paraffin-Based Phase Change Material (PCM) Using Nano Carbons. *Applied Thermal Engineering*. 2020;181:115992.
- [493] Jin C, Wu Q, Yang G, Zhang H, Zhong Y. Investigation on Hybrid Nanofluids Based on Carbon Nanotubes Filled with Metal Nanoparticles: Stability, Thermal Conductivity, and Viscosity. *Powder Technology*. 2021;389:1–10.
- [494] Aodkeng S, Sinthupinyo S, Chamnankid B, Hanpongpan W, Chaipanich A. Effect of Carbon Nanotubes/Clay Hybrid Composite on Mechanical Properties, Hydration Heat and Thermal Analysis of Cement-Based Materials. *Construction and Building Materials*. 2022;320:126212.
- [495] Viana TM, Bacelar BA, Coelho ID, Ludvig P, Santos WJ. Behaviour of Ultra-High Performance Concretes Incorporating Carbon Nanotubes under Thermal Load. *Construction and Building Materials*. 2020;263:120556.
- [496] Yang Z, Yang J, Shuai B, Niu Y, Yong Z, Wu K, Zhang C, Qiao X, Zhang Y. Superflexible yet Robust Functionalized Carbon Nanotube Fiber Reinforced Sulphoaluminate Cement-Based Grouting Materials with Excellent Mechanical, Electrical and Thermal Properties. *Construction and Building Materials*. 2022;328:126999.
- [497] Irshidat MR, Al-Nuaimi N, Rabie M. Hybrid Effect of Carbon Nanotubes and Polypropylene Microfibers on Fire Resistance, Thermal Characteristics and Microstructure of Cementitious Composites. *Construction and Building Materials*. 2021;266:121154.
- [498] Gu X, Peng L, Liu P, Bian L, Wei B. Enhanced Thermal Properties and Lab-Scale Thermal Performance of Polyethylene Glycol/Modified Halloysite Nanotube Form-Stable Phase Change Material Cement Panel. *Construction and Building Materials*. 2022;323:126550.
- [499] Zhu Y, Qian Y, Zhang L, Bai B, Wang X, Li J, Bi S, Kong L, Liu W, Zhang L. Enhanced Thermal Conductivity of Geopolymer Nanocomposites by Incorporating Interface Engineered Carbon Nanotubes. *Composites Communications*. 2021;24:100691.
- [500] Shahpari M, Bamonte P, Jalali Mosallam S. An Experimental Study on Mechanical and Thermal Properties of Structural Lightweight Concrete Using Carbon Nanotubes (CNTs) and LECA Aggregates after Exposure to Elevated Temperature. *Construction and Building Materials*. 2022;346:128376.
- [501] Hadipeykani M, Aghadavoudi F, Toghraie D. A Molecular Dynamics Simulation of the Glass Transition Temperature and Volumetric Thermal Expansion Coefficient of Thermoset Polymer Based Epoxy

- Nanocomposite Reinforced by CNT: A Statistical Study. *Physica A: Statistical Mechanics and its Applications*. 2020;546:123995.
- [502] Wang G, Zhang D, Wan G, Li B, Zhao G. Glass Fiber Reinforced PLA Composite with Enhanced Mechanical Properties, Thermal Behavior, and Foaming Ability. *Polymer*. 2019;181:121803.
- [503] Papageorgiou DG, Terzopoulou Z, Fina A, Cuttica F, Papageorgiou GZ, Bikiaris DN, Chrissafis K, Young RJ, Kinloch IA. Enhanced Thermal and Fire Retardancy Properties of Polypropylene Reinforced with a Hybrid Graphene/Glass-Fibre Filler. *Composites Science and Technology*. 2018;156:95–102.
- [504] Rafiee M, Nitzsche F, Laliberte J, Hind S, Robitaille F, Labrosse MR. Thermal Properties of Doubly Reinforced Fiberglass/Epoxy Composites with Graphene Nanoplatelets, Graphene Oxide and Reduced-Graphene Oxide. *Composites Part B: Engineering*. 2019;164:1–9.
- [505] Shen Z, Bateman S, Wu DY, McMahon P, Dell'Olio M, Gotama J. The Effects of Carbon Nanotubes on Mechanical and Thermal Properties of Woven Glass Fibre Reinforced Polyamide-6 Nanocomposites. *Composites Science and Technology*. 2009;69:239–244.
- [506] Sharma S, Tiwari SK, Shakya S. Mechanical Properties and Thermal Conductivity of Pristine and Functionalized Carbon Nanotube Reinforced Metallic Glass Composites: A Molecular Dynamics Approach. *Defence Technology*. 2021;17:234–244.
- [507] Safari Tarbozagh A, Rezaifar O, Gholhaki M, Abavisani I. Magnetic Enhancement of Carbon Nanotube Concrete Compressive Behavior. *Construction and Building Materials*. 2020;262:120772.
- [508] Liu Y, Cheng X. Effect of Carbon Nanotube Size on Electrical Properties of Cement Mortar under Different Temperatures and Water Content. *Geofluids*. 2022.
- [509] Shen X, Mao T, Li C, Mao F, Xue Z, Xu G, Amirfazli A. Durable Superhydrophobic Coatings Based on CNTs-SiO₂gel Hybrids for Anti-Corrosion and Thermal Insulation. *Progress in Organic Coatings*. 2023;181:107602.
- [510] Chousidis N, Zacharopoulou A, Zeris C, Batis G. Corrosion Resistance and Physical-Mechanical Properties of Reinforced Mortars with and without Carbon Nanotubes. *Journal of Materials Science and Chemical Engineering*. 2022;10:1–23.
- [511] Lan Y, Zheng B, Shi T, Ma C, Liu Y, Zhao Z. Crack Resistance Properties of Carbon Nanotube-Modified Concrete. *Thomas Telford Ltd*. 2022;74:1165–1175.
- [512] Mohsen MO, Al Ansari MS, Taha R, Al Nuaimi N, Taqa AA. Carbon Nanotube Effect on the Ductility, Flexural Strength, and Permeability of Concrete. *Journal of Nanomaterials*. 2019.
- [513] Mohsen MO, Alansari M, Taha R, Senouci A, Abutaka A. Impact of CNTs' Treatment, Length and Weight Fraction on Ordinary Concrete Mechanical Properties. *Construction and Building Materials*. 2020;264:120698.
- [514] Hawreen A, Bogas JA, Kurda R. Mechanical Characterization of Concrete Reinforced with Different Types of Carbon Nanotubes. *Arabian Journal for Science and Engineering*. 2019;44:8361–8376.
- [515] Hassan A, Elkady H, Shaaban IG. Effect of Adding Carbon Nanotubes on Corrosion Rates and Steel-Concrete Bond. *Scientific Reports*. 2019;9:1–12.
- [516] Vikulova M, Nikityuk T, Artyukhov D, Tsyganov A, Bainyashv A, Burmistrov I, Gorshkov N. High-k Three-Phase Epoxy/K1.6(Ni0.8Ti7.2)O16/CNT Composites with Synergetic Effect. *Polymers*. 2022;14:448.
- [517] Dehrooyeh S, Vaseghi M, Sohrabian M, Sameezadeh M. Glass Fiber/Carbon Nanotube/Epoxy Hybrid Composites: Achieving Superior Mechanical Properties. *Mechanics of Materials*. 2021;161:104025.
- [518] Kundalwal SI, Rathii A. Improved Mechanical and Viscoelastic Properties of CNT-Composites Fabricated Using an Innovative Ultrasonic Dual Mixing Technique. *Journal of the Mechanical Behavior of Materials*. 2020;29:77–85.
- [519] David ME, Ion RM, Grigorescu RM, Iancu L, Constantin M, Stirbescu RM, Gheboianu AI. Wood Surface Modification with Hybrid Materials Based on Multi-Walled Carbon Nanotubes. *Nanomaterials*. 2022;12:1990.
- [520] Mei S, Wang J, Wan J, Wu X. Preparation Methods and Properties of CNT/CF/G Carbon-Based Nano-Conductive Silicone Rubber. *Applied Sciences*. 2023;13:6726.
- [521] Kumar A, Sinha S. Performance of Multiwalled Carbon Nanotube Doped Fired Clay Bricks. *Journal of Materials in Civil Engineering*. 2022;34:04022349.
- [522] Tijjani Y. High Temperature Applications of Carbon Nanotubes (CNTs) [v]: Thermal Conductivity of CNTs Reinforced Silica Nanocomposite. *Bayero Journal of Pure and Applied Sciences*. 2022;15:136–140.
- [523] Abdeen DH, Atieh MA, Merzougui B, Khalfauui W. Corrosion Evaluation of 316L Stainless Steel in CNT-Water Nanofluid: Effect of CNTs Loading. *Materials*. 2019;12:1634.
- [524] Radhamani AV, Lau HC, Kamaraj M, Ramakrishna S. Structural, Mechanical and Tribological Investigations of CNT-316 Stainless Steel Nanocomposites Processed via Spark Plasma Sintering. *Tribology International*. 2020;152:106524.
- [525] Eisa MS, Mohamady A, Basiouny ME, Abdulhamid A, Kim JR. Mechanical Properties of Asphalt Concrete Modified with Carbon Nanotubes (CNTs). *Case Studies in Construction Materials*. 2022;16:e00930.